



**QUEEN'S
UNIVERSITY
BELFAST**

Metal Redispersion Strategies for Recycling of Supported Metal Catalysts: A Perspective

Morgan, K., Goguet, A., & Hardacre, C. (2015). Metal Redispersion Strategies for Recycling of Supported Metal Catalysts: A Perspective. *ACS Catalysis*, 5(6), 3430-3445. <https://doi.org/10.1021/acscatal.5b00535>

Published in:
ACS Catalysis

Document Version:
Early version, also known as pre-print

Queen's University Belfast - Research Portal:
[Link to publication record in Queen's University Belfast Research Portal](#)

Publisher rights

This document is the unedited Author's version of a Submitted Work that was subsequently accepted for publication in ACS Catalysis, © 2015 American Chemical Society after peer review. To access the final edited and published work see <http://pubs.acs.org/doi/abs/10.1021/acscatal.5b00535>.

General rights

Copyright for the publications made accessible via the Queen's University Belfast Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

The Research Portal is Queen's institutional repository that provides access to Queen's research output. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact openaccess@qub.ac.uk.

Open Access

This research has been made openly available by Queen's academics and its Open Research team. We would love to hear how access to this research benefits you. – Share your feedback with us: <http://go.qub.ac.uk/oa-feedback>

Metal Re-dispersion Strategies for Recycling of Supported Metal Catalysts: A Perspective

Kevin Morgan, Alexandre Goguet and Christopher Hardacre**

CenTACat, School of Chemistry and Chemical Engineering, Queen's University Belfast,

David Keir Building, Stranmillis Road, Belfast, BT9 5AG, UK

*corresponding authors: kmorgan08@qub.ac.uk; c.hardacre@qub.ac.uk

ABSTRACT

Catalyst deactivation is ultimately inevitable, and one of the processes known to cause deactivation is sintering of metal particles. Consequently, numerous methods to reverse the sintering process by re-dispersing metal nanoparticles have been developed. These methods are discussed in this perspective, and the reported mechanisms of re-dispersion are summarized. Additionally, the longer term practical use of such treatments, and the benefits this can bring, is briefly disclosed.

KEYWORDS: Catalyst recycling, catalyst regeneration, metal re-dispersion, catalyst deactivation, supported metal catalysts

1 Introduction

In the field of heterogeneous catalysis, it is well documented that deactivation of catalysts is not only problematic, but that it is also eventually inevitable.¹⁻³ Such deactivations can be as a result of both chemical and physical changes and in the case of metal supported catalysts, this can occur by way of a number of mechanisms, such as poisoning, coking and sintering/agglomeration of metal nanoparticles.^{1, 2} Process technology considerations often mean that methods of reversing catalyst deactivations are developed. These can occur either during process operation (e.g. only a change of feed is required) or during a separate regeneration process (where multiple conditions may need to be varied).³

In order to fully assess deactivation and/or reactivation due to changes in metal dispersions one has to be mindful of the limitations of physio-chemical techniques (such as chemisorption, UV, TEM and X-Ray based methods) that are used for such analysis. For example, chemisorption techniques assess particle size based on adsorption. This is subject to error since the adsorption provides a measure of the surface area and from this a particle size is inferred based on a number of assumptions, for example the shape of the particle and the geometry of the adsorbed molecule on the surface. Similarly, it is known that the electrons generated in techniques such as TEM have the ability to change metal dispersions. Hence the best practice is to use a combination of techniques, including, where possible, synchronous characterization methods. There have been many reports of such studies combining, for instance, numerous spectroscopic techniques. Recently, the emergence of pair distribution function (PDF) to be utilized with traditional X-Ray adsorption spectroscopy (XAS) studies has also been discussed.⁴

In the future, the use of computed tomography with experimental techniques, such as XRD-PDF⁵, may prove to be very useful given the ability to determine structural changes of “minor” components⁶, such as smaller metallic nanoparticles.

Catalytic activity and durability are often inversely proportional to the diameter of the supported metal particles, with smaller particles typically resulting in higher activities.^{7, 8}.

Consequently, the activity of supported metal catalysts is highly dependent on metal particle size.⁹ For instance, for gold, the highest activity observed for CO oxidation was with gold particles of 2-3 nm in diameter, whereas other reactions have their own optimum gold particle size.^{10, 11} However, it is also worth noting that in the case of gold, changes in electronic properties due to decreasing particle size (and lower coordination) can increase gold’s ability to adsorb small molecules.¹²

The driving force for sintering is the thermodynamic instability of small crystallite particles (nm range), which possess a high surface to volume ratio¹³. This driving force increases exponentially with decreasing particle size;¹⁴ i.e. the greater the instability of the particles, the greater the driving force is for sintering.¹⁵ Hence, larger metal particles are formed by the aggregation of smaller particles, meaning that the total accessible metallic surface is significantly reduced.¹⁶ In some instances, preventative measures have been taken in the catalyst synthesis steps, but these may only delay the deactivation. For instance, the use of “capping agents” which are designed to protect against agglomeration only delay the growth of the nanoparticles¹⁷, and hence deactivation will still ultimately follow. An example of this is the use of Re to retard Pt sintering as it results in the dispersion to smaller aggregates, thereby,

increasing the catalyst lifetime before regeneration is required.¹⁸ It has also been reported that the presence of Re can, in fact, restrict Pt migration and, thereby, limit sintering.¹⁹⁻²¹ A similar restriction in Pt sintering as a result of addition of Sn has also been reported²² and this is thought to be as a result of Sn poisoning acidic sites of the support²³, although alloying with Sn is also reported to inhibit the Pt activity. A similar inhibition has also been reported when Ir/Al₂O₃ was impregnated with CaO, SrO or BaO, although the concentration of these metals (Ca, Sr or Ba) must be higher than the concentration of acid sites.²⁴ It is also noteworthy that addition of BaO to a sintered Ir/Al₂O₃ and subsequent oxidation (in air at 600 °C) caused the Ir metal to re-disperse.²⁴

The use of ligands (e.g. thiols) which can form strong sulphur-metal bonds (for instance with Au and Pt) can stabilize mobile metal atoms on a CuO surface resulting in highly dispersed metal particles upon removal of the ligands.⁷ For example, tris(phenylthio)benzene (TPB) was adsorbed on gold nanoparticles resulting in a decrease in the gold particle size from ~4 nm to ~1.5 nm. This was thought to be due to the TPB affecting the migration of the gold particles on the oxide, resulting in a change in particle size distribution.

Additionally, when core shell structures were prepared, it was suggested that the encapsulated nanoparticles were more resistant to sintering²⁵⁻²⁸ and this is a possible explanation for catalytic activity being maintained.²⁹

Another synthesis method which has the potential to limit sintering and/or promote dispersion of metals (including Cu, Pt and Pd) is the use a support of a solid solution of mixed oxides containing at least one reducible metal oxide, such as ceria.³⁰⁻³³ The presence of the reducible

metal oxide facilitates the creation of metal-metal oxide interfaces under reducing conditions, which allows for the metal to be re-dispersed under oxidizing conditions.

Another possible route to prevent aggregation of nanoparticles is in the utilization of strong metal-oxide/support interactions (SMOI or SMSI). It has been suggested that strong adhesion energy of nanoparticles of metal (Ag, Ir and other late transition metals) to supports (including ceria, magnesia and perovskites) is responsible for their resistance to sintering.^{34, 35} Obviously SMSI effects are both metal and support dependent, so one can consider the thermal stability of the metal as a guide to this. For example, over Al_2O_3 , in O_2 environment the SMSI effect decreases from $\text{Rh} > \text{Pt} > \text{Ir} > \text{Ru}$ whereas in an H_2 environment the trend is $\text{Ir} \sim \text{Ru} > \text{Rh} > \text{Pt}$.³⁶ In addition to this, it has been reported that the use of non-reducible metal oxides (SiO_2 , Al_2O_3 , MgO) as supports can stabilize very small particles, specifically gold.³⁷ More recent work has reported a new type of SMSI for Pt nanoparticles on ceria³⁸, where the Pt (as Pt_8) has been observed as a fluxional system where the charge distribution and geometry are able to change, thereby facilitating an enhancement of catalytic activity.

Another factor to be considered is the role of the support in the re-dispersion process.³⁹ For instance, it has been reported that Pt supported on zeolite HY is much more prone to sintering than $\text{Pt}/\text{Al}_2\text{O}_3$ catalysts.⁴⁰ The ability to disperse Pt over a range of metal oxide supports (TiO_2 , SnO_2 , NbO_2 , ZrO_2 , SiO_2 , Ta_2O_5 and Nb_2O_5) in low temperature fuel cells (under the operating conditions of PEMFC cathode) has also been reported.³⁹ As Pt re-dispersion is considered an activated process it was calculated that, under such conditions, only NbO_2 was suitable for Pt re-dispersion in the desired potential interval, although SnO_2 has some promise also. This

process is also affected by the acidity of the support. For example, using oxidative treatments (at 550 °C), increased Pt dispersion was observed in the case of acidic supports (Al_2O_3 and MgO), but decreased over basic/neutral supports (SiO_2 , silica alumina, silicalite).⁴¹

Despite attempts to prevent sintering, eventually metal particles will sinter, resulting in deactivation of the catalyst. This is problematic and as a result some precious metal catalysts (particularly for automotive uses) tend to be loaded with excess metal to enhance lifetime.⁴² For instance, in automotive catalysts, the monoliths could contain as much as 2000 g t^{-1} of metal. This excess loading is to ensure that the catalyst remains effective even at the end of its guaranteed lifetime to comply with the environmental legislation.⁴³ Conversely, the demands on precious metal resources are ever growing, due to increased industrialization and legislation concerning emissions.⁴² Therefore, ways that can be developed resulting in the regeneration of catalysts through the re-dispersion of supported metals in sintered catalysts are critical for the future of emission control and chemical industries.

2 Metal re-dispersion strategies

With catalyst deactivation comes the obvious pursuit of catalyst reactivation/recycling. In the case of deactivation by sintering this will require the rejuvenation of the metallic sites. The regeneration process whereby the original metal dispersion of a sintered catalyst is achieved, or even improved upon, is known as “re-dispersion”.¹⁶ It is possible to regain or even improve upon the original dispersion and, in most cases, with this ability to re-disperse the metal particles comes the ability to recover the catalytic activity. Note, however, that this will not always result in the original activity being recovered.⁴⁴

The use of re-dispersion of metal nanoparticles in the reversal of sintering has existed almost from the point that sintering was identified as a deactivation process.⁴⁵ It has been argued that sintering and re-dispersion are two sides to the same process, which have a dependence on both temperature and atmosphere.⁴⁶ It has also been postulated that re-dispersion is in itself actually part of the sintering mechanism, whereby the metallic atoms become initially liberated from larger particles.⁴⁷ Hence, if the process is halted abruptly (normally by cooling), this dispersion will be maintained or frozen. There is some evidence that this does occur since it has been reported that catalysts which were rapidly cooled retained a higher dispersion than those allowed to cool slowly, in what was referred to as a “freezing of agglomeration”.⁴⁸

The ability to re-disperse a metal is dependent on a number of factors, including temperature, redox environment, interaction between the metal and the support which affects the activation energy of atom moving from metal nanoparticle to the support⁴⁷ and the surface area of the support. It has also been reported (from Monte Carlo simulations) that the greater the initial particle size, the slower the re-dispersion process.⁴⁹ Similarly, the higher the initial metal content, then the more difficult it will be to re-disperse the metal.^{49, 50}

Numerous re-dispersion strategies have been utilized for a wide range of metals (e.g. Pt, Au and Ag) and these are discussed in the subsequent sections. The strategies for metal re-dispersion are summarized in Table 1.

Table 1: Summary of references for metal re-dispersion strategies

Strategy	Metals	References
Oxidation and reduction	Fe	73-75
	Pt	16, 22, 40, 76-93
	Pd	94-107
	Rh	18, 79, 108-112
	Ag	113-119
	Au	10, 37, 120
	Other metals and bi-metallics	16, 18, 22, 79, 80, 121-123
Chlorination and oxychlorination	Pt	19, 44, 50, 84, 158-170
	Pd	171, 172
	Other metals and bi-metallics	18, 19, 22, 79, 80, 169, 173-184
Thermal treatment with iodomethane	Au	9, 188-190, 192-194
	Rh	191
Treatment with halohydrocarbons other than iodomethane	Au	9

2.1 Oxidation and Reduction

One of the most common approaches to re-dispersion are techniques using cycles of oxidation and reduction, primarily with oxygen and hydrogen, respectively.⁵¹ Such techniques are commonly used in industry, as indicated by the number of patents related to oxidation and/or reduction methods for catalyst regeneration, for example references 52-71, although not all of these refer to re-dispersion. During oxidation/reduction re-dispersion processes it has been proposed that oxidations result in metal oxide particles, followed by mobilization of these particles. Thereafter, heated hydrogen treatments (typically short in duration) form the

catalytically active metal particles through the reduction of the metal oxide. Short timescales for this process are necessary as sintering can occur after prolonged heating, particularly in reducing environments, although sintering can also occur while heating under oxidizing atmospheres.⁷²

The temperature of such treatments dictates the ability to re-disperse or sinter the metal.⁷³⁻⁷⁵ For instance, in the case of iron on titanium oxide, reductive treatments (Fe^{3+} being reduced to Fe^{2+})⁷⁴ below 370 °C result in particles < 10 nm (as observed via TEM).⁷³ However, in the temperature range of 404 to 434 °C, the Fe particles have been reported to grow to > 10 nm.⁷³ Reductions at 500 °C resulted in Fe particles ~ 10 nm in size, while reductions in the temperature range of 602 to 700 °C gave Fe particles which were \leq 10 nm.⁷³ In these instances, the active catalyst is actually a mixed oxide of Fe and Ti, which is formed via oxidation at 677 °C, where a high iron dispersion is still maintained in the form of FeTi_2O_5 species. It should be noted that the first oxidation could not completely reverse the changes caused by the first reduction, nor were subsequent reductions found to completely reverse the effect of the corresponding oxidation step, reportedly a consequence of SMSI.⁷⁵ Such SMSI and temperature dependencies for the sintering/re-dispersion (and reversibility thereof) will be metal and support specific.

It should be noted that oxidation may not always result in re-dispersion to smaller particles. For instance, in the case of Pt, the oxidation process is thought to disrupt the metal lattice. When these particles are subsequently reduced, fissures appear in the Pt particles⁷⁶ which can result in a higher Pt surface area even though the Pt particle size remains apparently relatively

unchanged. For this reason, one should not use chemisorption experiments alone to assess the extent of re-dispersion since any increase in Pt surface area will result in increased chemisorption due to the porosity changes. Therefore, any link between a change in H/Pt ratio (from chemisorption) and sintering/re-dispersion in the absence of further characterization is the subject of some debate.⁷⁷ Hence, it is preferable to make use of a combination of additional techniques to definitively monitor changes in metallic particle size (e.g. TEM).

2.1.1 Platinum

The ability to re-disperse platinum over a range of supports with oxidation-reduction cycles has been well documented in the literature. However, it should be noted that it can take numerous cycles of oxidation-reduction before any re-dispersion is actually observed.⁷⁸ The effect of oxidation-reduction cycles on Pt/Al₂O₃ catalysts has been examined through activity studies^{18, 22} and using CO adsorption IR spectroscopy.^{79, 80} Interestingly, it was also found that repeated oxidation cycles actually resulted in Pt sintering.²²

TEM studies have shown that the re-dispersion of Pt particles was observed from 10.7 nm to 4.1 nm after heating a Pt/ γ -Al₂O₃ catalyst in air at 600 °C for 18 h, followed by heating at 500 °C, also in air, for a further 18 h.⁸¹ Prior to analysis with TEM, the samples were immersed in mercuric chloride and then rinsed with water, before being stored under high vacuum for several hours to avoid any contamination of the microscope. There was no apparent reduction treatment, although the storage under high vacuum for several hours would have created a significant reducing environment. Some re-dispersion was achieved at lower temperatures (400

°C) following the 600 °C treatment, but to a lesser extent than that observed after heating at 500 °C.⁸¹

A different study reported an optimum temperature for re-dispersion of Pt (in the case of a number of pre-reduced Pt/Al₂O₃ catalysts).⁸² In this case, oxidation at temperatures up to 600 °C, followed by a reduction with H₂ at 500 °C resulted in dispersion of the Pt (30%) which was higher than that obtained with the fresh catalyst (10%). However, the maximum dispersion was observed after oxidation at 550 °C (70 %), and sintering began to occur again at temperatures greater than this. This optimum temperature has been reported elsewhere for oxidation-reduction cycles, and highly dispersed metallic particles have been observed after reduction at 550 °C.⁴⁰ It was actually reported in this instance that the re-dispersed Pt was resistant to any subsequent sintering.⁴⁰ It should be noted, however, that there are also reports in the literature of original dispersions of fresh catalysts being restored at 480 °C.⁸³

XRD and TEM were used to study the hydrogen storage capacity of a range of Pt/MgO catalysts as a mean to assess changes in Pt particle size after oxidation and reduction.⁸⁴ It was found that oxidative treatments between 550 and 800 °C resulted in Pt particles with a reduced average crystallite size.

Using a cyclic oxidative/reductive process, it was found that at all studied temperatures (500 to 800 °C), the particle sizes of Pt were smaller after the oxidation step (2.21 to 9.56 nm) compared with the Pt particle size after the reduction (3.03 to 11.11 nm), although the particle size even after reduction was still smaller than that observed for the fresh catalyst.¹⁶ Similar trends were noted in other studies of the same monometallic Pt catalyst.⁸⁵ It should, however,

be noted that this was quite a prolonged reduction step (16 h at 150 °C and 2 h at 250 °C), in pure hydrogen. Consequently, the fact that some sintering occurred during this reduction step is not surprising. Therefore, as previously stated in this perspective, it is important that any reductive step conducted after oxidations is done under carefully controlled conditions.

XRD, TEM, XAFS and XPS have all been employed to study the sintering and re-dispersion of Pt in Pt/MgO and Pt/ γ -Al₂O₃ catalysts.⁸⁶ Therein, the catalysts were aged at temperature (700, 800 and 900 °C) for 5 h in two ways; in constant air flow (air ageing) or in a flow switching every 5 minutes between 5% O₂ in N₂ and 10 % H₂ in N₂ (redox ageing). Activity tests with simulated exhaust gas (0.7% CO, 0.23% H₂, 0.053% C₃H₆, 0.12% NO, 0.646% O₂, 10% CO₂ and 3% H₂O in N₂) reactions were then conducted with the aged catalysts, with conversion of CO, C₃H₆ and NO_x monitored.

The air ageing tests had little effect on the activity of the Pt/MgO, but caused a significant decrease in the activity of the Pt/ γ -Al₂O₃. Hence, Pt/MgO was more stable under high temperature oxidative conditions than Pt/ γ -Al₂O₃. An explanation for this was that no sintering of Pt occurred on Pt/MgO, but Pt particles as large as 30 nm formed on the air aged Pt/ γ -Al₂O₃ catalyst.

It was previously demonstrated that the interaction of Pt with the support oxide occurs under oxidizing conditions, and that the inhibiting sintering effect on Pt can be controlled by support oxygen electron density through the interaction of Pt oxide with the support.⁸⁷ The formation of Mg₂PtO₄ compounds during the air aging process is thought to inhibit Pt sintering, thereby explaining the stability of Pt/MgO under high temperature oxidizing conditions. This is in

agreement with previous studies which showed that the Pt interactions with alumina were much weaker⁸⁷, thus explaining the lack of Pt re-dispersion in Pt/ γ -Al₂O₃.

The redox ageing tests were found to have an adverse effect on the activity of both the Pt/MgO and Pt/ γ -Al₂O₃ catalysts for simulated exhaust reactions. It was observed that the Pt particle size had grown for both Pt/MgO (15 to 25 nm) and Pt/ γ -Al₂O₃ (20 to 30 nm) following the redox ageing tests. It was determined that the deactivated Pt/MgO catalyst could be regenerated by re-dispersing the Pt nanoparticles following to a process of sequential treatments involving 20 % O₂/N₂ for 5 h and then 10 % H₂/N₂ for 5 h at 800 °C. However, under the same conditions, the activity of the Pt/ γ -Al₂O₃ continued to decrease. Consequently, it was reported that the formation of Mg₂PtO₄ was the driving force of the re-dispersion process. This is further evidence that a strong metal support interaction is desirable for catalyst regeneration via redox treatments, in the case of Pt at least.

Similar conclusions were drawn when a Pt/Al₂O₃ catalyst was compared with a Pt/CeZrY mixed oxide catalyst using in situ time resolved Turbo-XAS.⁸⁸ For the Pt/Al₂O₃ catalyst, it was observed that as temperature increased so too did the Pt particle size (>20 nm); it was also noted that the particle size did not decrease again upon cooling. However, in the case of Pt/CeZrY mixed oxide, the particle size increased from 1.8 nm, for the untreated catalyst, to 4.4 nm as temperature was increased from 400 to 800 °C, while particle size decreased again to 2.7 nm when cooled to 550 °C. Hence, this sintering/re-dispersion could be controlled reversibly by temperature. Again, the strong interactions between Pt oxide and support (primarily ceria) was thought to be the reason for the re-dispersion process.

The nature of the Pt re-dispersion was further studied in terms of how the initial Pt particle size affected the rate of Pt re-dispersion.⁸⁸ It was determined that the larger the initial particle size, then the slower the re-dispersion process, in agreement with Monte Carlo simulations.⁴⁹

The effect of temperature on the rate of re-dispersion was also investigated.⁸⁸ Unsurprisingly, the re-dispersion occurs faster at higher temperatures, indicating an activated process, a fact which is reinforced considering no re-dispersion occurred at 400 °C or below. Additionally, it was found that re-dispersion occurred much faster at higher oxygen concentrations, which supports the theory that Pt oxide interactions with the support are important to the re-dispersion process.

It has been reported, that the agglomeration of Pt can occur in both reducing and oxidizing atmospheres, particularly at temperatures above which Pt^{2+} species typically decompose.⁸⁹ However, subsequent oxidation at lower temperatures results in a mobile PtO phase, which can result in highly dispersed metallic particles after a controlled reduction.

In general, it has been reported that Pt dispersions of Pt/ Al_2O_3 catalysts after treatment with oxygen are higher than the dispersions found after hydrogen treatments.⁹⁰ It has been reported that when increasing oxygen concentration during oxidative treatments of a Pt/ Al_2O_3 catalyst, PtO forms, which promotes the formation of Pt- Al_2O_3 complexes and subsequent migration of Pt species into the bulk lattice of the support.⁹¹ Upon reduction, these PtO and Pt- Al_2O_3 species form Pt metal, resulting in a greater Pt dispersion being observed. However, it has also been reported that heating in oxygen can cause catalyst deactivation, whereas heating in hydrogen (or nitrogen) resulted in activation (at temperatures > 400 °C) for the hydrogenation of

cyclohexane and decomposition of hydrogen peroxide.⁹² At temperatures below 400 °C (for all atmospheres) sintering and deactivation occurred. At higher temperatures in hydrogen (and to a lesser extent, nitrogen) oxygen is removed from the surface of the support, which in fact promotes dissociation of Pt crystallites and surface mobility of the Pt, towards these vacancies.⁹² A similar mechanism (and trends; sintering in oxidizing and re-dispersion in reducing conditions) has also been proposed for a Pt/TiO₂ catalyst.⁹³ In this case, a change in the titania was observed (from TiO₂ to Ti₄O₇) due to the reduction of the surface removing oxygen and creation of vacancies.⁹³ In this case, the Pt metal is thought to interact with exposed Ti cations to form Pt-Ti bonds, which rupture under oxidizing conditions, reforming the TiO₂ and causing Pt agglomeration.⁹³

2.1.2 Palladium

Previously, the dependency of catalytic activity on the Pd particle size has been observed under CO/NO cycling.⁹⁴⁻⁹⁶ Therein, from the CO/NO cycling experiments it was reported that an increased size of Pd nanoparticles was found to have a negative effect on the production of CO₂. In a study using EXAFS, DRIFTS and MS of NO reduction/CO removal it has been reported that rapid, reversible sintering and a novel, non-oxidative re-dispersion of Pd nanoparticles occurred during cycles between CO and NO flows.⁹⁷ This occurred without chlorine present, and without significant Pd oxidation. Experiments were conducted at 400 °C on a 1 wt.% Pd supported on 10% ceria-zirconia on alumina (10ZCA) catalyst, cycling between flows of 5% CO/He and 5% NO/He. While the fresh catalyst was found to contain PdO nanoparticles almost exclusively, in both the CO and NO environments there was no PdO detected, and the Pd-Pd

bond lengths observed were characteristic of metallic Pd and Pd nanoparticles. However, the Pd-Pd coordination was higher in the CO environment than in the NO environment, with particles of ~100 Pd atoms forming due to sintering by CO. Under the NO environment, non-oxidative dispersion of these large particles occurred, resulting in particles of ~20-25 Pd atoms. The sintering/re-dispersion mechanism involved removal of adsorbed oxygen from the fresh catalyst by CO (reductant). Once the adsorbed oxygen was depleted, the sintering of the Pd occurred in tandem with the CO adsorbing on metallic Pd as observed with IR spectroscopy. Under the NO feed, the adsorbed CO was removed from the surface and Pd re-dispersion occurred, most likely, by a combination of both particle splitting and flattening.⁹⁷

EXAFS studies were also conducted on a chloride free Pd/Al₂O₃ catalyst during redox cycles with CO as the reductant and NO as the oxidant both in the absence and presence of oxygen.^{98, 99} The same overall trend was observed during the CO/NO cycles as that discussed previously⁹⁷, i.e. sintering in CO, re-dispersing in NO. However, in the presence of O₂ during the NO cycle, the amount of re-dispersion achieved was found to significantly increase, although this occurred without oxidation of Pd.^{98, 99} The postulated mechanism involves an initiation step of significant Pd re-dispersion, prior to the formation of the more stable PdO^{98, 99} which, as already discussed, can migrate further over the support ultimately resulting in a higher metallic dispersion upon reduction.

A similar observation has been made for Pd supported on perovskite used in catalytic convertors.¹⁰⁰ Samples were cycled between lean (oxidative) and rich (reductive) engine conditions at 800 °C using a sequence of oxidation (in air at for 1 h), reduction (10% H₂ for 1 h)

and re-oxidation (in air for 1 h). It was reported that the oxidation-reduction-oxidation cycle caused Pd migration in and out of the lattice of the perovskite, hindering sintering of Pd. This provided an explanation for the longevity of these catalysts due to apparent “self-regeneration”, as has been previously reported.⁴² Crucially, with a refined methodology, the perovskite material was also found to be equally effective in promoting self-regeneration in Pt and Rh as well as Pd.¹⁰¹ It is also noteworthy that these self-regenerating catalysts have been utilized in non-automotive applications, such as organic synthesis reactions like Suzuki coupling.^{102, 103}

2.1.3 Rhodium

While studying CO hydrogenation using Rh catalysts ($\text{RhVO}_4/\text{SiO}_2$, Rh/SiO_2 and $\text{V}_2\text{O}_5\text{-Rh}/\text{SiO}_2$), the mean sizes of the Rh particles was assessed.¹⁰⁴ After reduction (at 500 °C), it was found that the Rh precursors used for catalyst preparation decomposed to form highly dispersed Rh particles, the size of which varied for $\text{RhVO}_4/\text{SiO}_2$ (4 nm), Rh/SiO_2 (9-10 nm) and $\text{V}_2\text{O}_5\text{-Rh}/\text{SiO}_2$ (9-10 nm). It was further determined that, after reaction, when the catalyst was sintered, it was possible to regenerate the rhodium vanadate complexes via oxidation at 700 °C, and then recover the highly dispersed Rh through a subsequent reduction step.

High resolution electron microscopy (HREM) studies looked at the influence of reduction/re-oxidation conditions on the particle size distribution of a series of Rh/CeO_2 catalysts prepared from $\text{Rh}(\text{NO}_3)_3$ and RhCl_3 .¹⁰⁵ Reductions and re-oxidations were conducted using a flow of H_2 or O_2 while heating the catalyst from 25 °C up to selected reduction temperatures (350, 500 and 900 °C) at a rate of 10 °C min^{-1} , before dwelling for 1 h. Reduction at 700 °C and re-oxidation at

800 °C were also investigated. Progressive sintering was observed during reduction up to 700 °C, and significant sintering occurred at 900 °C. Rh re-dispersion was only observed during the re-oxidation treatments at 800 and 900 °C, while the re-oxidation at 500 °C induced sintering. In previous studies^{106, 107} employing TPO experiments it was determined that metallic and oxidized Rh phase were both present following re-oxidation treatments at lower temperatures (100 and 250 °C). However, polycrystalline Rh₂O₃ particles were found to be the almost exclusive phase after re-oxidation at 500 °C. Re-oxidation at higher temperatures was found to encourage the migration of these Rh₂O₃ particles across the CeO₂, which then could be reduced to highly dispersed metallic Rh.

2.1.4 Rhenium

For a Re/Al₂O₃ catalyst studied using chemisorption, ESR and TPR a dispersed oxide phase had a high level of interaction with the support, which readily reduced to metallic Re at temperatures >500 °C, while maintaining dispersion.¹⁰⁸ The crystallite oxide phase could be oxidized further to Re⁷⁺, and then subsequently reduced to metal Re in hydrogen at 350 °C. This metallic Re could be dispersed via oxidation, followed by exposure to vacuum or inert gas at 500 °C. This dispersed oxide phase could then be reduced to Re metal as mentioned previously.¹⁰⁸ Such characteristics (spreading of oxide phase and reduction of oxide) have been further confirmed by similar experiments using XPS.¹⁰⁹

The Re dispersion of 1 and 10 wt.% Re/γ-Al₂O₃ catalysts following four different oxidation-reduction treatments was monitored using hydrogen chemisorption, TEM, XRD, electron diffraction and electron spin resonance¹¹⁰ and in terms of the activity and selectivity of the

catalysts for hydrogenation and hydrogenolysis of benzene.¹¹¹ The 1 wt.% Re catalyst was subjected to 20 oxidation-reduction cycles while 10 wt.% Re catalyst underwent 10 oxidation-reduction cycles.

The chemisorption results of both 1 and 10 wt.% Re/ γ -Al₂O₃ indicated that surface area and Re dispersion increased relative to the untreated catalyst after oxidation at 400 °C. An increased dispersion was also noted for the catalysts stored in air at room temperature for several months, which undergo a low temperature oxidation in this time. The Re dispersion only increased slightly after calcination of the long term, low temperature oxidized catalyst. XRD and TEM were unable to satisfactorily detect the Re of 1 wt.% Re/ γ -Al₂O₃, and it was assumed that Re was highly dispersed in all the cases studied. No metallic Re was observed in the XRD and TEM of the passivated 10 wt.% Re/ γ -Al₂O₃ and it was concluded that Re was completely oxidized to Re₂O₇. After the reduction at 550 °C, metallic Re particles of ~4 nm were observed with TEM as well as in the XRD. It was found that re-oxidising at 400 °C resulted in rhenium oxide again, and it was assumed that this was highly dispersed as it was not observed with TEM or XRD. After the subsequent reduction at 500 °C, Re was once again present in metallic form (observed by TEM), but the particle size had decreased further (to ~3 nm).¹¹⁰

From these results, two possible mechanisms (oxidation at low temperature and 400 °C) for the Re re-dispersion were proposed. At low temperatures, while the catalyst was stored in air, the Re slowly oxidized, resulting in hydrated rhenium oxide. This caused the Re₂O₇ clusters to split into smaller particles, which are mobile via surface diffusion. The reduction process then resulted in Re₂O₇ particles reducing to highly dispersed metallic Re particles. The mechanism for

the oxidation at 400 °C occurred through the formation of Re_2O_7 , which has a low melting point and high vapor pressure, meaning that Re_2O_7 could migrate via the gas phase as well as through surface diffusion. Once again, subsequent reduction yielded metallic Re of a smaller particle size and uniform dispersion.¹¹⁰

This study also highlighted that the re-dispersion of the active metal is not always beneficial. For example, in the hydrogenolysis reaction, the dispersion of the Re which yielded the highest TOF was 26 % and the activity was found to decrease rapidly at higher dispersions. Furthermore, the selectivity during hydrogenolysis while relatively constant (~60 %) for dispersions up to 60 %, was found to decrease at higher dispersions. The opposite trend was observed for the hydrogenation, where selectivity was steady at 40 % up to 60 % dispersion, before increasing up to 80 % selectivity at higher dispersions. Importantly, it was found that the re-dispersion process did not result in any loss of Re.

In a follow up study¹¹², HRTEM, H_2 chemisorption, O_2 uptake and XRD were utilized to further understand the mechanism of the oxidative re-dispersion process. In the proposed scheme for oxidation and re-dispersion, a number of temperature dependent processes were proposed. At low temperatures (20 to 150 °C) superficial Re oxides (including Re_2O_7) are formed due to dissociative oxygen chemisorption. In the 200-250 °C range, oxidation and sublimation of Re occurs, with HRTEM showing that metallic Re particles were present, without any surface oxide layer. At 300 °C, complete oxidation of Re to Re_2O_7 occurs, with only small traces of metallic Re observed with HRTEM. Between 400 and 600 °C, surface compounds of ReO_4 form. These compounds decompose at 800 °C, with some sublimation to Re_2O_7 . In the case of the sample

oxidized at 500 °C, further reduction at 550 °C resulted in re-dispersion via the reduction of the surface compounds to small metallic Re particles.

In the studies of Re/Al₂O₃ catalysts under the conditions discussed previously^{18, 79} the Re dispersion increased (along with increased activity for the heptane-H₂ reactions) after oxidation at 550 °C; however, these catalysts were still prone to deactivation via coking.^{18, 79}

2.1.5 Silver

Changes in morphology of Ag nanoclusters supported on titania due to oxygen have also been reported.¹¹³ XPS and STM were used to observe the changes in Ag morphology following to redox treatments. Initially, a unimodal Ag particle size distribution was observed (2.0 to 6.5 nm) for the untreated catalyst. Following oxidation of the catalyst, it was found that Ag₂O particles were formed in a bimodal size distribution with sizes of 1.0 to 5.0 nm and 5.0 to 11 nm. This meant that while some clusters became reduced in size, others increased. It was determined that the clusters which increased in size did so through Ostwald ripening, a form of intercluster transport where clusters grow at the expense of others. In this work it was noted that under vacuum or reductive conditions, migration of Ag from clusters could only occur in the form of free metallic Ag atoms.¹¹³

It has also been observed with DRUV, EXAFS and UV-Vis, that even under mild reduction conditions¹¹⁴⁻¹¹⁶ including vacuum conditions¹¹⁷ silver has a tendency to aggregate. For instance, EXAFS showed that upon exposure to a SCR mix, Ag⁺ ions aggregate to form a range of active clusters of Ag_n^{δ+} (average *n* value of 3).¹¹⁵ In XRD and EXAFS study of similar Ag/γ-Al₂O₃

found that samples aged in the SCR reaction feeds between 600 and 800 °C underwent similar reconstruction.¹¹⁸ After ageing at 600 °C, the Ag atoms coalesced into small clusters of ~ 3 atoms. However, using the same feed conditions at 800 °C, the Ag-Ag coordination number began to decrease (from 3.2 to 2.1) as the larger particles began to re-disperse to form smaller Ag clusters. These smaller clusters are thought to be a precursor to silver aluminate compounds.¹¹⁹ The changes in Ag dispersion during the aging process had different effects on the SCR in the presence and in the absence of hydrogen. For instance, increased dispersion actually had an adverse effect on the activity of the hydrogen promoted SCR reactions, whereas in the absence of hydrogen, there was a promotional effect for the SCR reaction from the Ag reconstruction at 600 °C.

2.1.6 Gold

A DRIFTS, MS and XRD study of an Au/CeO₂ catalyst used for CO oxidation has revealed the dependence of gold particle size on redox conditions.¹⁰ The results indicated that during the reductive conditions of CO adsorption studies, the metal dispersion increased as the Au species became oxidized and diffused from the metal oxide bulk to the surface. This was attributed to Au-support interaction, the formation of (O)Au⁺-CO species due to CO creating oxygen vacancies on the surface. These gold-ceria interactions promote migration of gold particles, resulting in re-dispersion of the gold through etching of the larger gold particles.¹⁰

Similar conclusions were also drawn from in situ XRD and Raman studies of Au supported on a cerium-europium mixed oxide used for the CO oxidation.³⁷ It was reported that doping with europium increased the number of oxygen vacancies, thereby promoting the ability of Au to

diffuse through the support via stronger Au-support interactions. It was determined that the number of oxygen vacancies increased during reductive conditions (H_2), which resulted in increased gold dispersion. Oxidative treatments (in synthetic air), where oxygen vacancies were replenished, make the Au-support interactions became less favorable than the reducing conditions, causing Au particles to sinter. This sinter/re-dispersion process was found to be reversible due to its dependency on the existence of oxygen vacancies, and therefore the oxidative/reductive nature of the environment.

During EXAFS, TEM and SEM studies, Au/TiO₂ catalysts used for liquid phase hydrogenations were found to undergo re-dispersion from particles of 8 nm to smaller particles of 2-3 nm.¹²⁰ In contrast, larger particles (8-10 nm) formed during the reduction (H_2 , 60 to 300 °C) of the fresh catalyst. After the liquid phase hydrogenation reactions, it was found that the average Au particle size decreased to ~2-3 nm, and these particles were stable under reaction conditions. Such re-dispersions did not occur over Al₂O₃ support. Figure 1 reports a comparison of TEM and particle size distribution of an Au/TiO₂ reduced in hydrogen at 60 °C (on the left) and then this treated catalyst following the hydrogenation reaction, and the differences in particle size are clearly observed.

The proposed mechanism of the re-dispersion, in this case, involves Au interaction with oxygen vacancies of the support, and the presence of H_2 (or reducing conditions) increasing the quantity of these vacancies, and hence promoting re-dispersion of the gold. This is in agreement with other studies in the literature.^{10, 37}

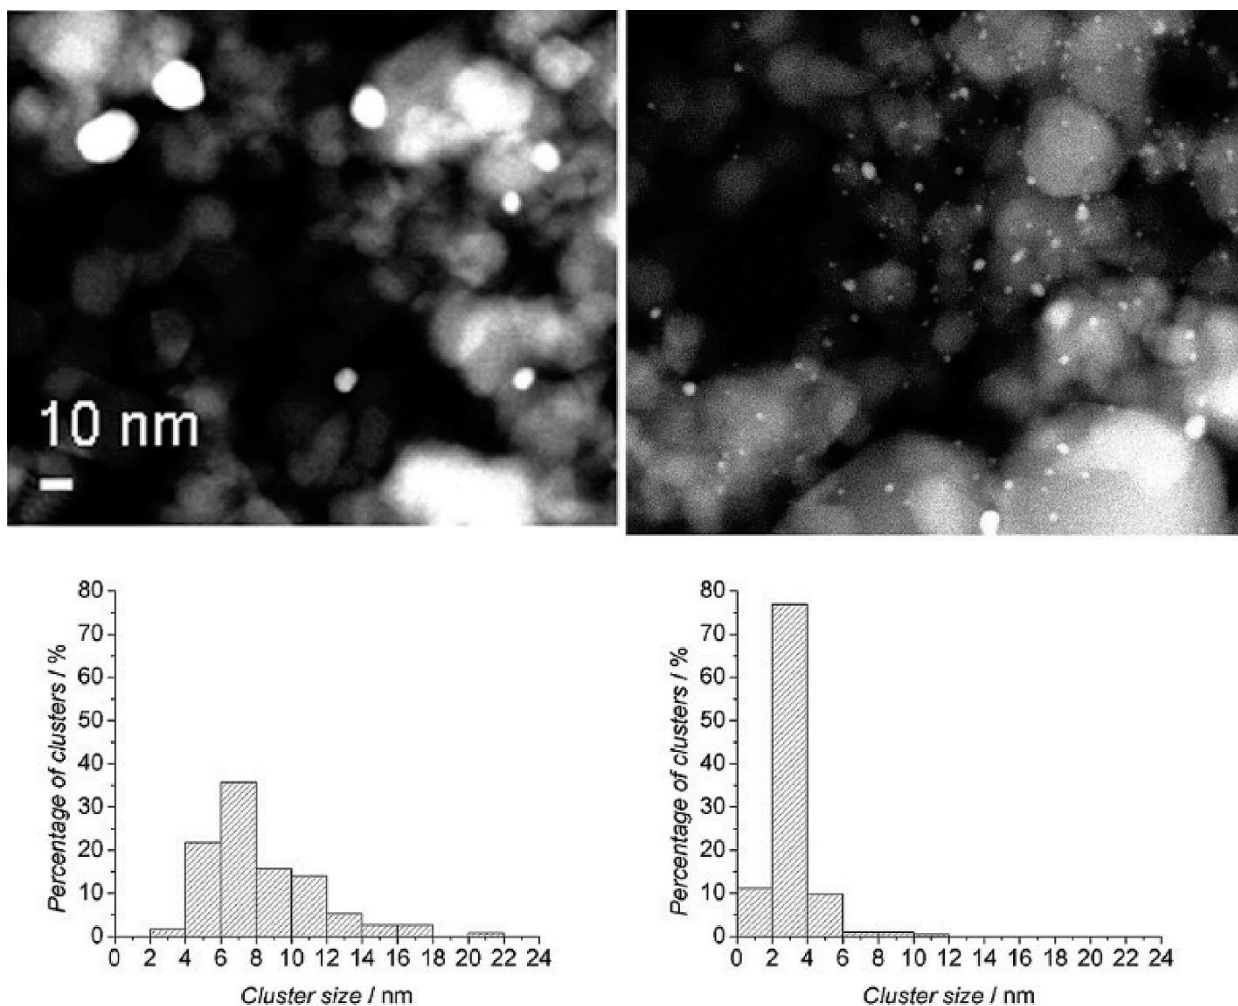


Figure 1:¹²⁰ HAADF-STEM Micrographs and particle size distributions of Au/TiO₂ catalysts treated in H₂ at 60 °C and then again after hydrogenation of 4-nitrobenzaldehyde at 100 °C and 10 bar H₂.

2.1.7 Other metals and bimetallic catalyst systems

The dependency of metal dispersion on oxidative and reductive treatments has also been observed for a Co/TiO₂ catalyst.¹²¹ Reduction was found to generate smaller particle sizes at 700 °C than at lower temperatures. It was proposed that the Co particles are originally bound

chemically to the oxygen of the support, and these bonds can be broken at higher temperature, while a phase transformation from anatase to rutile proceeds, thereby, causing the Co to re-disperse.

The effect of oxidation and reduction cycles on Pt-Sn/Al₂O₃ has also been studied using pulsed CO chemisorption and IR spectroscopy,^{22,80} as well as XRD.⁸⁰ The samples were first calcined in air during a 15 °C min⁻¹ temperature ramp up to 400 °C (followed by a 30 min dwell), followed by reduction at 400 °C for 1 h in H₂. A series of 6 consecutive oxidation (1 h at 550 °C; 60 ml min⁻¹ of air) and reduction (1 h at 400 °C; H₂) cycles were then employed.²² The results indicated that the Sn partially hindered sintering of Pt, although the ability to re-disperse the Pt via oxidation-reduction was also significantly diminished.

The deactivation and regeneration of a range of Pd/Rh monolith catalysts (removed from a commercial automobile exhaust gas system) using oxidation and reduction treatments at temperatures up to 500 °C has also been investigated.¹²² TEM images of fresh samples, combined with EDX analysis, confirmed that no noble metal particles of size > 3 nm were present on the monolith. In the aged samples, large agglomerates of metal were observed, including some Pt and Pd particles as large as 100 nm. TEM of aged samples after oxidation (10 h, 20 % O₂ in N₂) showed a reduction in some of the agglomerates and while activity in terms of HC and NO_x conversion were recovered, the authors pointed out that the removal of contaminants from the surface could also be a factor.

As mentioned previously, a pulse chemisorption technique has also been used to study Pt-Re bimetallic catalysts.¹⁶ It was found that the bimetallic catalyst was more resilient to sintering

than the monometallic Pt system. This was shown by the fact that, when the catalysts were sintered at 800 °C, only the bimetallic catalyst was catalytically active after re-dispersion. The bimetallic system was found to sinter in reducing environments, and re-disperse in oxidizing environments. It was concluded that the Re inhibited the sintering. It was further concluded that a temperature threshold existed below which metal-support interactions in the form of PtO-Al₂O₃ complexes did not occur, and it was above this temperature where re-dispersion could proceed.¹⁶

Similar studies on the oxidation-reduction cycles of Pt-Re/Al₂O₃ catalysts have been conducted using the conditions discussed previously.^{18, 79} In this case, similar trends in dispersion to those for the Pt/Al₂O₃ catalyst were observed (i.e. Pt sintering), indicating little effect of the Re, although evidence of formation of bimetallic particles was reported.^{18, 79}

While studying methanol carbonylation over Ir-La/C it was found that the addition of La inhibited the deactivation of Ir catalysts which occurred by sintering and reduction to metallic Ir.¹²³ With the Ir-La/C catalyst it was observed that a greater dispersion of the metal(s) was achieved following an activation treatment in syngas (CO to H₂ ratio of 4:1), with particles mostly being 1-3 atoms in size. This high dispersion has been attributed to formation of Ir-La hydrocarbonyl species after exposure to CO) along with the role of La in stabilizing Ir and Ir⁺ species.

2.1.8 Summary

Oxidation and reduction cycles have been reported to be successful in the re-dispersion of a number of metals. However, under certain conditions, this process has its limitations. For instance, it has been reported that the oxidation and reduction can be useful for re-dispersion, provided:¹²⁴

1. the metal can be oxidized under the conditions used;
2. reduction can occur without sintering (i.e, sintering temperature is higher than temperature for metal oxide decomposition).

It has also been stated that this process may not be ideal for metals forming oxides which are highly stable and highly mobile.¹²⁴ In instances where oxidation and reduction are found not to be ideal for the re-dispersion, it has been suggested that reduction after the formation of metal sulfides, carbides or chlorides could be a viable alternative.¹²⁴ For instance, in the case of Pt on different supports, the metal can re-disperse in O₂ only (at 600 °C) if the support is Al₂O₃.¹²⁵ If the support is TiO₂, chlorine (from CCl₄) was needed to enable re-dispersion.¹²⁵

The mechanism of re-dispersion via oxidation/reduction cycles is in the form of the “strain” model⁸¹ and can be summarized as follows:

- oxidation causes the large metallic agglomerates to undergo oxidation;
- oxymetal species form on the surface of the particle;
- the variation in metal-metal distances in the metal oxide surface layer and those in the unoxidized metal causes induces a metal strain energy;

- oxymetal particles progressively fragment from the large particle (by fracture of the larger particle);
- fragmented oxymetal species undergo dispersion through interactions with the support.

2.2 Chlorination and Oxchlorination

The use of halogen species (primarily chlorine based) to boost re-dispersion is commonplace and has been in existence for decades. Halogens are used widely for catalyst regeneration, as indicated by the number of patents related to such processes.¹²⁶⁻¹⁵⁷ Although chlorine is primarily used for re-dispersion (and the discussion in this section will reflect this), it has also been reported that Br can be used for the re-dispersion of metals, and in particular Pt on Al₂O₃.⁴⁴

2.2.1 Platinum

It has been reported that the rate of Pt re-dispersion was greatly increased in the presence of chlorine species⁸⁴, and total metallic dispersion has been reported when small concentrations (0.9-1.0 %) of chloride have been utilized.¹⁵⁸ Interestingly, the use of halogenated precursors (e.g. aqueous H₂PtCl₆) for the preparation of a catalyst can result in an initial higher Pt dispersion than if a non-halogenated precursor (acetone solution of Pt(C₅H₇O₂)₂) is used.^{84, 159} Residual chlorine from the precursor can form HCl vapour under reaction conditions, and increase the dispersion/accessibility of the metal (specifically Pt in the reported case).¹⁶⁰ This is also the case when a catalyst has been chlorinated after preparation.¹⁵⁹ It has been proposed

that chlorine inhibits growth of Pt (on alumina)¹⁵⁹ and stabilizes Pt,⁵⁰ thereby increasing its ability to be dispersed.⁵⁰

Pt/Al₂O₃ catalysts have been monitored under oxygen and hydrogen treatments for re-dispersion¹⁶¹ and sintering¹⁶², using TPR and UV-Vis, respectively. Three samples of highly dispersed Pt catalysts supported on alumina were studied, including one which had been chlorinated. Re-dispersion during oxygen treatment was only observed in the presence of chloride, a process which was associated with an oxychloroplatinum surface complex species, Pt^{IV}O_xCl_y, the existence of which was confirmed by TPR.¹⁶¹ The presence of this complex was also confirmed with UV-Vis in the re-dispersed catalysts prior to sintering.¹⁶² The Pt re-dispersion process on pre chlorided Pt/Al₂O₃ catalysts has also been investigated in IR studies^{163, 164} as well as XRD and TEM.⁸⁴ It was noted that Pt re-dispersion was accompanied by an increase in Pt oxidation state; the oxidation of crystalline Pt and Pt re-dispersion were found to be conjoined processes. As the “re-dispersing oxidation” only occurred in the presence of the chloride, it was concluded that mobile Pt^{IV}O_xCl_y was responsible for the re-dispersion. This was reinforced by the temperature range in which re-dispersion occurred (500 to 600 °C), which corresponds to the temperature range where the Pt^{IV}O_xCl_y complex can be formed.¹⁶¹

The effect of chlorine (in the form of HCl, Cl₂ or CCl₄) on the dispersion of Pt has been known for some time.¹⁶⁵ There are other reported studies on the effect of Cl₂ and HCl on the re-dispersion of Pt over a range of materials, including zeolites.¹⁶⁶ The oxychlorination consisted of heated treatments (at 450, 620 or 720 °C) under a flow of 400 ppm CCl₄ in O₂, which were followed by reduction (500 °C for 16 h). The reported optimum temperature for the Pt dispersion was 620

°C. The results of the study with CCl_4 reinforced the previously reported view^{163, 164, 166} that the creation of oxychloroplatinum or chloroplatinum species was the important step in the re-dispersion process.

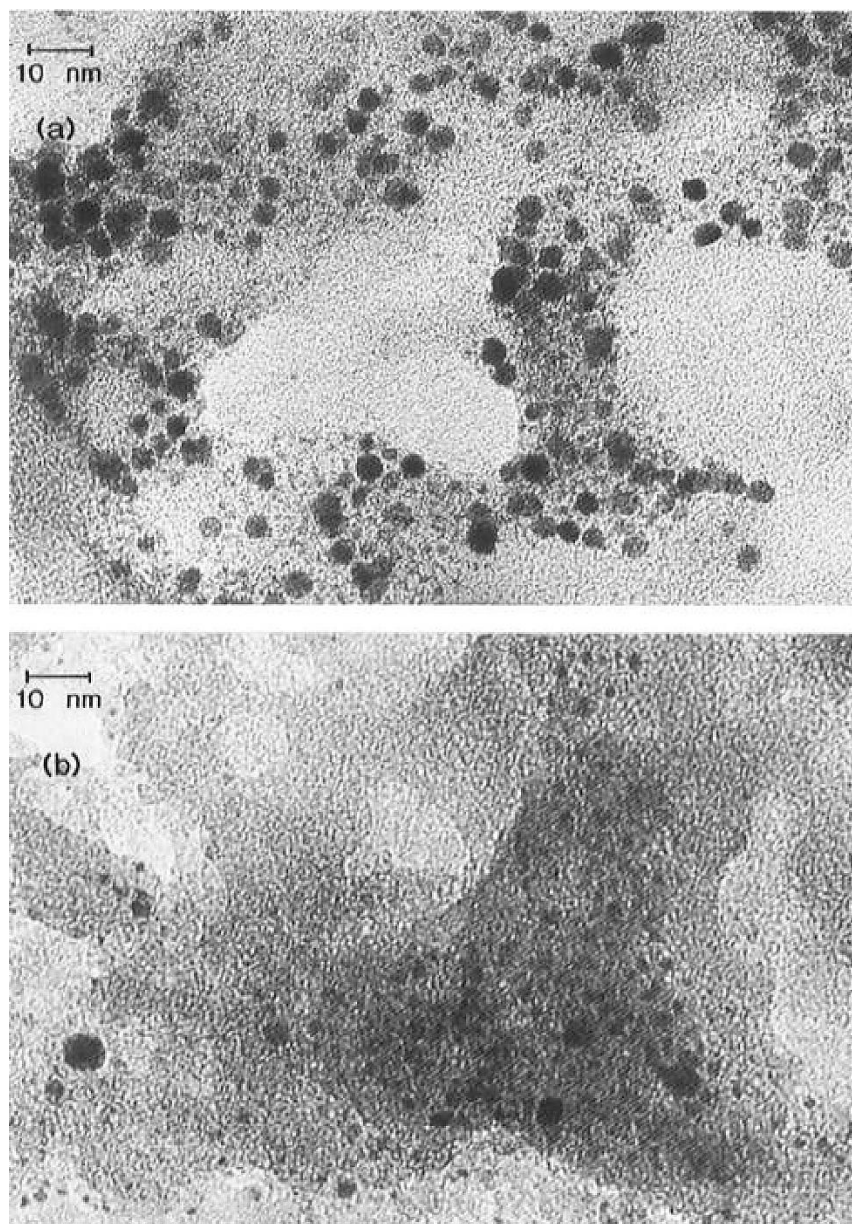


Figure 2:¹⁶⁷ TEM Micrographs of 0.6 wt. % Pt/Al₂O₃; sintered (a) and re-dispersed (b)

Two sintered Pt/Al₂O₃ catalysts (0.6 and 1 wt.% Pt) underwent successful Pt re-dispersion at 500 °C in an oxychlorination treatment with 2% O₂ in a HCl/H₂O/N₂ feed (H₂O to HCl molar ratio of 56) for up to 8 h.¹⁶⁷ The treated samples were analysed using TPR, hydrogen chemisorption, TEM and EXAFS. Chemisorption results indicated that the oxychlorination led to an increased Pt dispersion. TEM results (See Figure 2) indicated the presence of particles of 15 to 20 nm in size in the sintered sample, compared with particles of 6 to 8 nm in size over the re-dispersed catalyst. EXAFS results reported that the Pt-Pt co-ordination numbers also decreased due to the oxychlorination treatments. The EXAFS results also indicated the presence of some Pt-O and Pt-Cl co-ordination during the re-dispersion process, which would be indicative of the formation of some oxychloroplatinum species, most likely [Pt₅(OH)₄Cl₂]²⁻.

In another study of a Pt/Al₂O₃ catalyst (which was also prechlorided with HCl during impregnation) which used HCl in the oxychlorination treatment, the effect of oxygen partial pressure (from 0 to 100%) and HCl concentration (from 0.0005 to 0.003 atm) on re-dispersion were assessed.¹⁶⁸ In this case, the sintered catalyst had a Pt dispersion of ~12 %. The most effective temperature range for re-dispersion by oxychlorination was found to be 480 to 500 °C. In the absence of oxygen, further sintering was observed, highlighting the importance of oxygen in the re-dispersion. Furthermore, as the partial pressure of oxygen was increased (at fixed HCl concentration), the rate of re-dispersion was also found to increase. Analogously, when the HCl concentration was increased (at fixed O₂ concentration) it was also found to increase the rate of re-dispersion, as well as increasing the final dispersion achieved. Subsequently, a kinetic model for the sintering and re-dispersion processes of Pt on Al₂O₃ was also developed.¹⁶⁸

XANES has been utilized along with hydrogen chemisorption and *n*-heptane reforming activity screening to monitor the effect of oxychlorination/reduction cycles on Pt/Al₂O₃, as well as a Pt-Re/Al₂O₃ bimetallic catalyst.¹⁶⁹ Oxychlorination in the chemisorption studies was conducted by injecting 1,2-dichloropropane at a rate of 30 μl h⁻¹ in the first cycle and 15 μl h⁻¹ for all subsequent cycles. Reduction at 500 °C followed after the oxychlorination. For the XANES studies, oxychlorination was conducted during a temperature ramp up to 550 °C (at 6.8 °C min⁻¹) and a subsequent dwell time of 30 min. Again, 1, 2-dichloropropane (1270 ppm in He; halved for the subsequent cycles) was used with 45 cm³ min⁻¹ of air delivering ~1% Cl to the sample.

It is also noteworthy that there are cases of Pt re-dispersion being achieved using hydrofluorination with HF.¹⁷⁰ Activation with HF was studied since the fluorine-aluminum bond is much stronger than the chlorine-aluminum bond and as such was seen as an alternate to the need of constant injection of halohydrocarbon, as is typically the case with chloro compounds in industrial reactors.¹⁹ Primarily, this treatment (doping 0.2 wt.% Pt/H-ZSM-5 with up to 3% HF) increases both acid strength and number of acidic sites, which increased selectivity for methylation of toluene to xylenes (and reducing side reaction to trimethyl-benzenes) due to the changes in shape of active site. However, it was also noted from H₂ pulse chemisorption that there was an apparent increase in Pt dispersion when the catalysts were doped with HF. Unfortunately, no microscopy was reported that determined the Pt particle sizes in the catalysts.

2.2.2 Palladium

A monolithic Pd three way catalyst was treated by chlorination using submergence in HCl solution in order to achieve regeneration.¹⁷¹ Hydrogen chemisorption was used to determine the dispersion of Pd and particle diameter, and it was calculated that the Pd dispersion was increased following the HCl treatment, while the particle size decreased from 7 to 3 nm. SEM studies determined that there was a large quantity of particles of size 50 to 100 nm present in the aged (sintered) catalyst. Using the HCl treatment, although there were still some particles ~100 nm in size, the number of these was reduced by ~60%. EDX analysis reported that the Pd/Al ratio increased also following the HCl treatment, which is evidence that the reduction in number of larger gold particles is not due to leaching of Pd. It is worth noting though that the HCl treatment did not recover the original dispersion of the fresh catalyst. However, despite the original dispersion not being regained it is still claimed that such regeneration methods have real prospects for automotive catalyst recycling since there is still the potential to prolong the lifetime of the catalyst.

A further example of Pd re-dispersion has been reported using Cl₂ diluted in a feed of oxygen and helium for the oxychlorination treatment.¹⁷² A Pd/CeO₂-Al₂O₃ catalyst was studied with XRD, XPS, TEM, TPR and OSC measurements, before and after a range of oxychlorination treatments (with varying concentrations of Cl₂) in the 500 to 850 °C temperature range. The results have indicated that the oxychlorination followed by reduction was very effective for re-dispersion of Pd, with average particle sizes decreasing from 17 nm to ~ 8nm. It was further found that at oxychlorination temperatures above 500 °C, there was no further significant re-dispersion of Pd.

2.2.3 Other metals and bimetallic catalyst systems

The results indicated that the oxychlorination resulted in an increased dispersion of the Pt in both the monometallic and bimetallic catalysts. In the case of the monometallic catalyst, this increased dispersion had insignificant impact on the selectivity during the *n*-heptane reforming reactions, but increased selectivity to the hydrogenolysis products was apparent in the case of the bimetallic catalyst. XANES studies found that there was no Pt-Re alloy formation in the calcined catalyst, but that alloy formed during the reduction. Oxychlorination was found to disrupt the alloy, resulting in highly dispersed monometallic particles. All subsequent reductions again resulted in alloy formation, although the physical (particle size) and chemical (active metal distribution) nature of the alloyed species was significantly different from that formed after the initial reduction. This was due to the mobilization of the oxidized species (during oxychlorination) and the presence of chlorine.¹⁶⁹ Similar studies have been reported elsewhere, where particle size reportedly decreased from 70 nm to ~20 nm.¹⁷³

The effect of oxychlorination (followed by reduction) treatment on Pt/Al₂O₃ and Pt-Sn/Al₂O₃ has also been studied.^{22, 80} A series of 6 consecutive oxychlorination (1 h at 550 °C; 31 μmol h⁻¹ of 1, 2-dichloropropane in 60 ml min⁻¹ of air) and reduction (1 h at 400 °C; H₂) cycles were then employed for an IR study.²² Alternatively, the samples were calcined in air during a 15 °C min⁻¹ temperature ramp up to 400 °C (followed by a 30 min dwell), followed by reduction at 400 °C for 1 h in H₂. Then an oxidation (in air, at 550 °C for 1 h) was followed by a further reduction (in H₂, at 400 °C for 1 h). A series of consecutive oxychlorination (1 h at 550 °C; 510 μmol h⁻¹ of 1,

2-dichloropropane per 50 mg of catalyst, in 60 ml min⁻¹ of air) and reduction (1 h at 400 °C; H₂) cycles were then employed.⁸⁰

It was noted that any sintering occurring during oxidation-reduction could be reversed by oxychlorination-reduction treatment. From the IR spectroscopy, it was reported that oxychlorination caused the formation of (oxy)chloroplatinum species on the surface. Hence, in the absence of chlorine the Pt tended to sinter, the re-dispersion in the oxychlorination can be attributed to the formation of these (oxy)chloroplatinum species, which are mobile on the support surface, and decompose during reduction to form small clusters of Pt atoms.²²

For the oxychlorinated Pt-Sn/Al₂O₃ catalysts, the presence of Sn significantly reduced the formation of chloroplatinum and oxychloroplatinum complexes (by up to 50%). Excess Sn favored alloy formation in the presence of chlorine, hindering the migration of Pt through competition for support sites.⁸⁰ Hence, the reduced catalyst (after oxychlorination) also had a significantly lower dispersion than was observed in the absence of Sn.

Similar work on the oxychlorination treatments of Pt/Al₂O₃, Re/Al₂O₃ and Pt-Re/Al₂O₃ catalysts has been conducted, using the same preparation conditions previously mentioned herein.^{18, 79} Instead of the oxidative treatment, however, the oxychlorination involved heating the samples to 550 °C and introducing 1,2-dichloropropane (60 μl h⁻¹ per gram of catalyst) into the 60 ml min⁻¹ feed of CO₂-free air for 1 h.^{18, 79} Similar studies, with similar results, have been reported elsewhere.¹⁵⁸

In the case of the monometallic catalysts, the Pt dispersion was increased during the oxychlorination, but this was not the case for Re. The Pt dispersion of the bimetallic catalyst was also increased. The oxychlorination formed chloroplatinum and oxychloroplatinum complexes (in the case of the bimetallic these were free of Re), and this improved the Pt dispersion (after reduction) as the Pt complexes were able to migrate across the alumina. As before^{22, 80}, the oxychlorination has also been found to reverse the sintering and the existence of Pt-Re bimetallic particles that occurred following oxidation and reduction cycles.^{18, 79}

In combination with the oxidation and reduction cycles (as discussed in previous section), oxychlorination was also investigated for Pd/Rh monolith catalysts.¹²² the addition of chlorine to the oxygen feed (0.8 Cl₂, 18% O₂, balance N₂) resulted in a marked improvement in the activity of the aged catalyst, and this has been attributed to an increased rate of dispersion of the metals on the surface.¹⁷⁴ The greater efficiency of the oxychlorination compared with the oxidation treatment is further reinforced by the fact that the oxychlorination was only conducted for 1 h as opposed to 10 h for the chlorine free treatment.

The use of 1,2-dichloropropane as a source of chlorine for oxychlorination treatments has been further applied to Pd-Rh catalysts supported on a mixed ceria-zirconia-alumina support, albeit with slightly different conditions (80 μL h⁻¹ 1,2-dichloropropane in 50 ml min⁻¹ of N₂).¹⁷⁵ As has been demonstrated already, the oxychlorinations were able to reverse the Pd sintering process of thermal treatments, resulting in higher Pd dispersions, along with the recovery of oxygen storage capacity of the support through stronger metal-ceria zirconia interactions.

In the case of a Pt-Rh catalyst supported on a ceria zirconia alumina support¹⁷⁶, the same recovery of oxygen storage capacity was not achieved, but this could be due to different strength of interaction between metal and support.¹⁷⁵ A similar study has been reported for a Pt-Re/Al₂O₃, except that C₂HCl₃ was used as the source of chlorine.¹⁷⁷

A structured monolith Pd-Rh three way catalyst was also treated with chlorine reagents (1,2-dichloropropane and dichloroacetic acid) using 0.1 M solutions flowing at 0.6 L min⁻¹ at 50 °C for 2 h¹⁷⁸, a procedure which has been reported before for the regeneration of other monolith samples via removal of poisons.^{179, 180} The dichloroacetic acid was found to be more effective than dichloropropane at recovering Pd active sites, which has been attributed to the apparent re-dispersion and restructuring of said Pd due to the chlorination and subsequent reduction. This re-dispersion had the additional benefit of recovering oxygen storage capacity, as has been noted in a number of cases. It should be noted, however, that no microscopy has been utilized to establish any effectual change in metal particle size, and so one cannot rule out that this recovery of Pd active sites is not re-dispersion at all, but rather it is the removal of coke or other poisons.

The promotional effect of chlorine or fluorine on metal (Pt, Ir, Rh, Re or U) or bimetallic (Pt-Ir, Pt-Rh, Pt-Re or Pt-U) dispersion when supported on γ -Al₂O₃ catalysts has also been studied for a number of reactions. The pulsed micro-reactor experiments studied with these catalysts included hydrogenation of aromatics (benzene or toluene)¹⁸¹, the dehydrogenation of cyclohexane¹⁸² and the hydroconversion of cyclohexene.¹⁸³ The catalysts were doped with halogen using ammonium chloride or ammonium fluoride, with an optimum halogen content

found to be 3 %. The dispersion of metallic/bimetallic particles was determined using a hydrogen pulse chemisorption technique. In most cases the treatment with halogen resulted in an apparent higher dispersion of the metallic/bimetallic particles. No other techniques were utilized to determine particle sizes, and as such the study is certainly not definitive in proving that the particle size had changed. In terms of promotion of the catalyst activity, it was reported that chloride was better than fluoride for the monometallic catalysts whereas in the case of the bi-metallic catalysts, chloride inhibited the activity while fluoride promoted activity. The proposed reason was that, in the case of monometallic catalysts, metal fluorides formed, which due to obvious electronegativity differences, form stronger bonds than analogous chloride species, making it more difficult to produce metallic particles in the case of the fluorides. For the bimetallic catalysts, however, clusters of metals are reportedly formed, which reduces the amount of halide formation.

While studying cyclohexene hydroconversion, Pt-Re/H-ZSM-5 catalysts were investigated for activation by doping (3 %) with HCl or HF.¹⁹ Additionally, the monometallic Re catalyst were investigated in a similar manner. The metal dispersion was calculated using hydrogen pulse chemisorption, and doping with the halo acids was found to increase the apparent dispersion. In the case of the monometallic Re catalysts, the HF doping resulted in the best metal dispersion, whereas HCl gave the highest dispersion in the case of the bimetallic catalyst (although this was still less than that of the HF doped monometallic catalyst). Although XRD was used, the diffractograms were not published as it was reported that similar reflection intensities for all samples were observed. Consequently, no quantitative discussion in terms of changes in particle size was reported.

These typical oxychlorination treatments have been found not to be effective for all metals. For instance, while Pt does re-disperse in a Pt-Ir/ γ -Al₂O₃ catalyst, the Ir particle size was unchanged if the chloride content of the catalyst was too low.¹⁸⁴ However, by increasing the chloride content (e.g. up to 1.9 wt. %) of the catalyst, oxychlorinations using low concentrations of chloride species (e.g. HCl) could generate chlorine in situ, a process which was also found to re-disperse the Ir.¹⁸⁴ This may be due to weaker Ir metal-support interactions since in the case of Pt on SiO₂, where the interaction is less than in the case of Pt-Al₂O₃, a higher concentration of chlorine (to form the complex) and a lower temperature (to stabilize the complex) was required.¹⁸⁵ However, in some cases the complex formed may have a low volatility (eg. IrCl₃) compared with the analogous Pt species and so may also require a higher temperature to induce vapor phase mobility¹⁷⁴, a key aspect in re-dispersion. This aspect shows that the re-dispersion process sometimes has to be a trade off in terms of temperatures, since if the temperature is too high and the vapor phase chlorine complex too mobile, then leaching of the metal can occur (> 700 °C in case of Pt/Al₂O₃).¹⁸⁵

2.2.4 Summary

A general mechanism for the re-dispersion by chlorination/oxychlorination has been proposed:^{46, 161, 167}

- surface atoms of metal crystallite oxidized by oxygen;
- oxidized sites are attacked by chloride ions forming MO_xCl_y species;
- the MO_xCl_y species fragment from the larger particle;

- mobile MO_xCl_y migrate to the support surface;
- the metal is removed from the crystallite and re-dispersed.

It should be noted that some reports mention the formation of halo metal complexes,¹⁸⁶ as opposed to oxyhalometal species. It is also important to note that chlorination may not work on all supports. For instance, chlorine could not prevent growth of Pt on SiO_2 support.^{159, 187}

2.3 Thermal treatment with iodomethane

An issue arising from the use of the chlorination and oxychlorinations is the potential for further deactivation of the catalysts due to chlorine poisoning¹⁸⁸. Consequently, other halogens potentially easier to remove from the catalyst post treatment have been investigated. Iodomethane treatments have proven to be successful in the re-dispersion of metals to smaller nanoparticles, primarily in the case of gold¹⁸⁸⁻¹⁹⁰, but also for other metals, for example rhodium.¹⁹¹ A number of patents which use iodomethane as a promoter in an industrial process using a gold catalyst have previously been issued,^{192, 193} although no mention was made regarding an effect on the dispersion. The original treatment consisted of co-feeding iodomethane (or bromomethane¹⁸⁸) in the reaction mixture for vapour phase methanol carbonylation over gold catalysts.¹⁸⁸⁻¹⁹¹ This resulted in structural transformation from gold particles of >10 nm to clusters of two or three gold atoms.¹⁸⁸⁻¹⁹⁰ However, this treatment was originally performed under harsh conditions (240 °C and 16 bar)^{189,192,193} which, although ideal for methanol carbonylation, would not necessarily be well suited for the wider application of re-dispersive treatments with iodomethane. Further investigation found that with treatments

conducted with vapour phase iodomethane at atmospheric pressure and lower temperatures, re-dispersion of gold could still be achieved (atomic dispersion observed for temperature as low as 50 °C).¹⁸⁸ In an additional study using the same atmospheric conditions, similar results were also obtained for Au supported on metal oxides including silica, titania and alumina.¹⁹⁰

In Figure 3, EXAFS data clearly shows that the as received catalyst sample contained large Au particles with the peak at 2.85 Å indicative of Au...Au coordination, and the presence of other peaks at higher coordinations (5 to 6 Å). After 10 h of the methanol carbonylation reaction (which occurred at 16 bar pressure) the amplitude of the peaks at 2.85 Å and above began to decrease, while a new peak at 2.5 Å began to emerge, which was attributed to the restructuring and re-dispersion of gold particles. After 80 h of the methanol carbonylation reaction this restructuring and re-dispersion has continued, as is evident from the complete disappearance of the peak at 2.85 Å and the continued decrease in amplitude of higher coordinations (between 5 and 6 Å), as well as the continued increase in the amplitude of the peak at 2.5 Å.

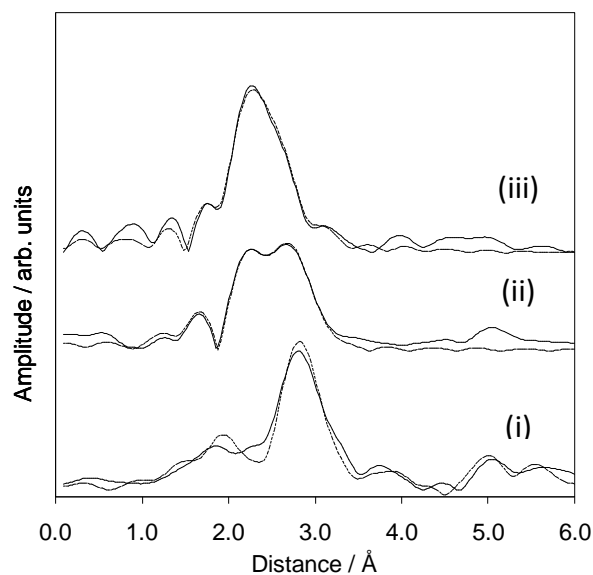


Figure 3:¹⁸⁹ Comparison of experimental (solid) and fitted (dashed) EXAFS data of Au/C catalyst; as received (i) and after 10 h (ii) and 80 h (iii) of methanol carbonylation reaction

Similar observations were made whenever the iodomethane treatment was conducted at atmospheric pressure for 1 h, as is reported in Figure 4. Clearly the as received Au/C catalyst in this case has some very large gold particles, as can be seen in 4A and 4B, the micrograph and particle size distribution of this sample, respectively. Importantly, Figures 4C and 4D show that the iodomethane treatment is very effective at re-dispersion of gold since, after only 1 h, it is apparent that the gold exists as isolated gold atoms, gold dimers or sub-nanometer Au clusters.

These findings were reinforced by the XRD results (Figure 5) where it is shown that the reflections of gold begin to decrease after only 1 minute and, in fact, are no longer present after only 15 minutes of treatment with iodomethane.

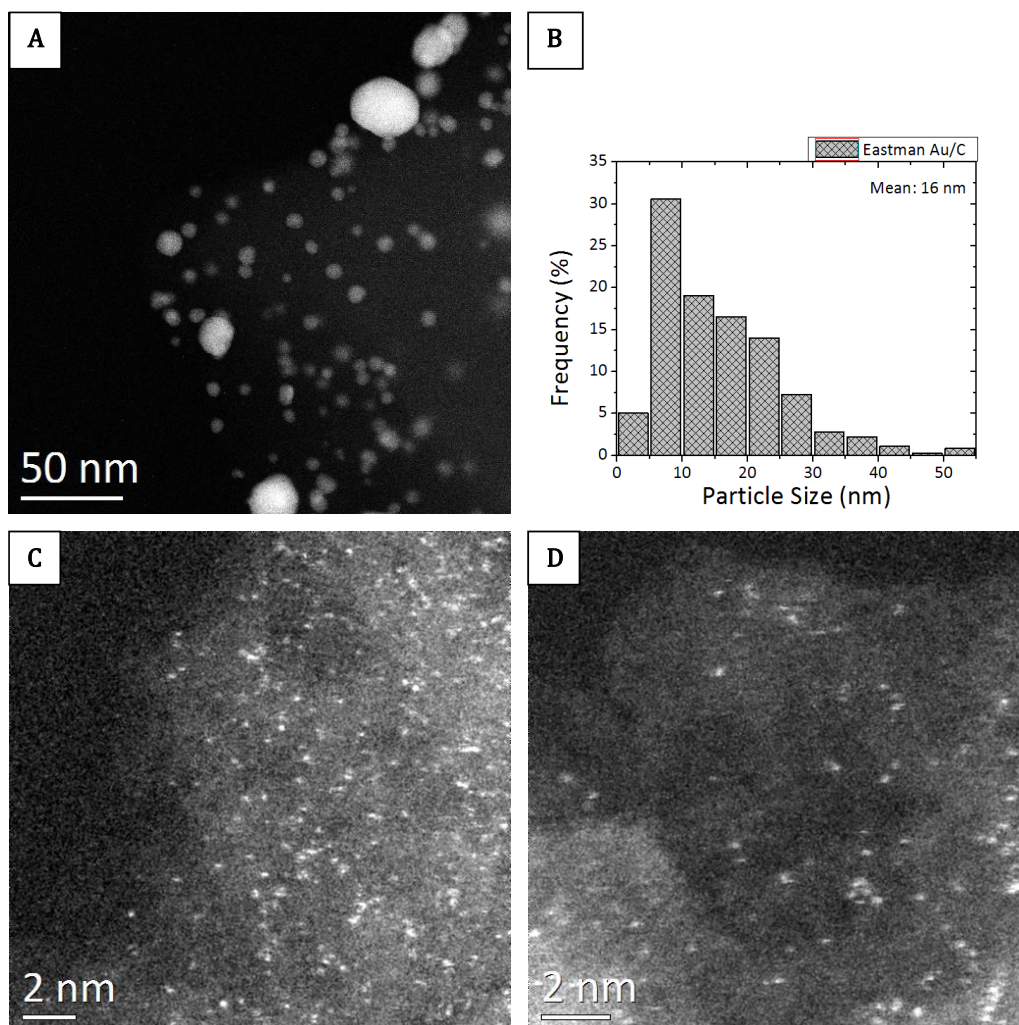


Figure 4:¹⁸⁸ The influence of iodomethane on Au nanoparticles of Au/C. HAADF-STEM images of as received sample (a) and after iodomethane treatment at 240 °C for 1 h (c and d), as well as the particle size distribution of the as received sample (b).

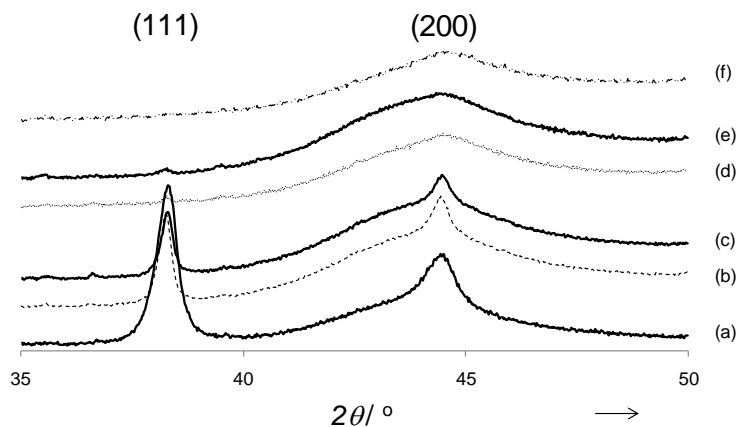


Figure 5:¹⁸⁸ X-ray diffractograms of Au/C catalysts. As received (a), and after treatment with iodomethane for 1 (b), 5 (c), 15 (d), 30 (e) and 60 minutes (f)

With such iodomethane treatments there is an obvious need to remove any residual iodo species to prevent any adverse effect of halide on the catalyst. With this in mind, a reductive treatment at 190 °C was applied using 10% H₂ in Ar (20 cm³ min⁻¹) and was found to be successful for the removal of residual iodo species without significantly affecting the dispersion of the gold particles.

The vapour phase iodomethane treatment has been studied for its potential to recover activity in a previously sintered catalyst, namely Au supported on a ceria zirconia titania mixed oxide.¹⁹⁴ The iodomethane treatment produced an active catalyst (50% conversion at 175 °C), with a higher performance than the sintered catalyst (50% conversion at 375 °C). DRUV characterization of the sintered and treated catalysts indicated that the later had some gold particles which are smaller in size than those found in the sintered sample.

2.3.1 Summary

A general mechanism for the re-dispersion by iodomethane can be proposed:

- surface atoms of large gold clusters are attacked by iodide ions, forming Au_yI_z ;
- these Au_yI_z species become “etched” away from the surface of the cluster;
- mobile Au_yI_z migrates to the support surface;
- a new layer of Au is exposed and attacked by iodide and the process is repeated.

2.4 Treatment with alternative halohydrocarbons

Due to the toxic and carcinogenic nature of iodomethane, a number of alternate halohydrocarbons were studied to develop safer vapour and liquid phase treatments.⁹ Vapour phase treatments focused on iodomethane, *n*-iodobutane, *n*-iodohexane and *n*-iodooctane. These iodoalkanes were also used for liquid phase treatments, as were *p*-iodotoluene and the analogous bromo compounds. All of these compounds have fewer risks associated with them, and also happen to be less expensive than iodomethane.⁹

The catalyst used for this study was a 1 wt.% Au/C, which had an average particle size of 27 nm and a dispersion of 3.3%. The same atmospheric conditions for the previously discussed vapour phase treatments using iodomethane were applied to the other iodoalkanes.

In the pure liquid phase treatments, the pure and hexane diluted halohydrocarbon was mixed directly with the catalyst at 40 °C. Following these treatments, significant changes to the Au/C

as a result of the treatments with halohydrocarbons were observed. In all cases, with the exception of the halotoluene samples, each halohydrocarbon had a varying ability to re-disperse the gold to smaller nanoparticles. More specifically, the iodides were better at the dispersion than the analogous bromides, and the ability to re-disperse gold increased with increasing alkane chain length. This was related to the strength of the alkyl-halide bond; i.e. the weaker this bond strength, then the greater the ability to re-disperse the gold. This also explains the ineffectiveness of the halotoluenes, since the alkyl-halide bond strengths for these compounds are higher than those of the haloalkanes that were investigated. The reported results clearly demonstrated the possibility of using alternate haloalkanes to replace iodomethane for the re-dispersion of gold particles. Added to this, not only were some of these alternate halohydrocarbons less expensive, but some have been found to be just as efficient, if not better, at the re-dispersion of large gold particles.

Clearly, a successful alternate method of treatment has also been established through the use of liquid systems, which is obviously a less demanding process than the vapour phase treatment which requires the catalyst to be heated up to 240 °C. This alternative lower temperature liquid phase method of treatment was essentially as efficient as the vapour phase approach.

Additionally, a trend in ability of re-dispersion of gold has been determined which is based on the bond strength of the R-X bond. It will now be possible to continue gold re-dispersion with alternative haloalkane compounds while reducing the risk of toxic contamination and carcinogenic exposure from iodomethane. A halide free catalyst post treatment was achieved

using the same hydrothermal treatment previously employed for the original vapour phase iodomethane treated samples.

2.4.1 Summary

The mechanism for this process is proposed to be the same as that which has been proposed for the iodomethane process in the previous section which involves formation of gold-halide species on the surface of large gold particles, followed by the etching of these gold-halide species. Hence, the general mechanism for the re-dispersion by haloalkanes can be proposed as:

- surface atoms of large gold clusters are attacked by halide ions, forming Au_yX_z ;
- these Au_yX_z species become “etched” away from the surface of the cluster;
- mobile Au_yX_z migrate to the support surface;
- a new layer of Au is exposed and attacked by halide and the process is repeated.

3 Overview

A number of mechanisms/modes of re-dispersion have been suggested, including molecular or atomic migration caused by changes in wetting angle, SMSI/SMOI effects, surface erosion (resulting in heterogeneous particle sizes) or homogeneous splitting. It should be noted that the same trends are not always observed using identical conditions for catalysts comprised of the same constituents (i.e. model versus real catalysts).¹⁹⁵⁻¹⁹⁷ It has been reported though that this can be simply down to differences in preparation of the catalysts.¹⁹⁵ This is also applicable to

sintering, since Pt-HY catalysts (prepared by ion exchange) are more likely to sinter than Pt/Al₂O₃ (prepared by impregnation).⁴⁰

Predominantly, the mechanism of re-dispersion (sometimes referred to as the “strain model”)¹⁹⁸ is similar in most cases. In terms of oxidation/reduction cycles, oxidation causes the large metallic agglomerates to undergo oxidation, forming oxymetal species on the surface of the particle. The variation in metal-metal distances in the metal oxide surface layer and those in the unoxidized metal induces a metal strain energy.⁸¹ Consequently, the oxymetal particles progressively fragment from the large particle (by fracture of the larger particle)^{78, 81} and migrate and disperse due to interactions with the support.¹⁹⁶⁻¹⁹⁸ Then, the newly exposed surface of the agglomerate is oxidised, and the process continues resulting in highly dispersed oxymetal species throughout the catalyst. Under reducing conditions, these oxymetals revert to metallic form, but remain in a highly dispersed state. However, if reduction conditions are too harsh (e.g. temperature or treatment time), then sintering will occur again. Similar re-dispersion processes occur for halogen treatments (chlorination, oxychlorination, iodomethane, halohydrocarbons) but with the formation of intermediate halometal or oxyhalometal species (as opposed to oxymetal species).

In all cases the smaller halometal/oxyhalometal particles undergo transport in the vapour phase, through the support and subsequent reduction treatments then result in highly dispersed metal particles. There is, however, a difference between chlorinations/oxychlorinations and iodomethane/halohydrocarbons in the process of the removal of halometal/oxyhalometal species from the large particles (See Figure 6). For

chlorinations/oxychlorinations, the larger cluster of halometal/oxyhalometal species fragments/splits (process 1).

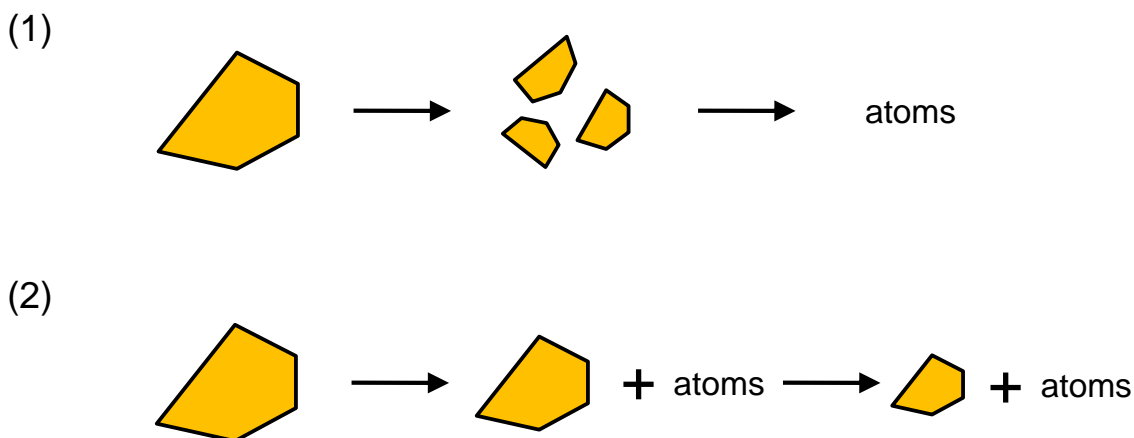


Figure 6: Processes of particle erosion

In the case of the iodomethane and the other halohydrocarbons, re-dispersion occurs rapidly as the large particles diameters shrink and erode due to the progressive removal of Au-X entities from the surface of the main particles (process 2).

In terms of applicability of the different re-dispersion methods, and which of these might be best, it is fair to say that there is not a one size fits all approach. As was indicated previously in this perspective, the strength of interactions between metal and support are specific to both metal and support. Since all the re-dispersion methods are an extension of metal/support interactions, the best method for re-dispersion of metals will also be specific to both the metal and the support. For instance, it is known that oxychlorinations are not suitable for gold, due to chlorine poisoning and/or gold leaching. While poisoning with the iodine can occur, it has also been demonstrated that the residual iodine can be removed with relatively mild treatments.

The applicability of the iodo based treatments to other metals is as yet unknown since there are no reported incidences where this has been investigated for any metal other than gold.

4 Perspective

The prospects of using re-dispersion treatments to regenerate catalysts have been summarised above, and it clear that it is possible to regain or improve upon the original dispersion of catalysts which have been sintered. While some of the reported re-dispersion processes have been conducted ex-situ, there is great potential that any of these treatments could be used within existing processes. For instance, in a system of parallel reactors with a switchable feed, one reactor could be utilised for reaction while the catalyst is regenerated by re-dispersion in the coupled reactor. By doing so, catalyst lifetime could be increased by maintaining catalyst activity for a longer period of time. The additional benefit, in particular from the halohydrocarbon treatments, of the ability to tune the size of the metal nanoparticles has the potential to improve upon activity and selectivity.⁹ As such, the ability of halohydrocarbons to re-disperse metals other than gold is worthy of further investigation.

NOTES

The authors declare no competing financial interests.

Supporting data are openly available on Queen's University Belfast Research Portal <http://pure.qub.ac.uk/portal/en/datasets>.

A number of figures in this perspective have been reproduced and the original work has been cited accordingly. Figure 1 is reprinted with permission from Kartusch *et al.*, J.A. *ACS Catal.*

2012, 2, 1394-1403; © copyright 2012 American Chemical Society. Figure 2 is reprinted with permission from Le Normand *et al.*, *J. Phys. Chem.* **1996**, 100, 9068-9076; © copyright 1996 American Chemical Society. Figure 3 is reprinted with permission from Goguet *et al.*, *J. Am. Chem. Soc.* **2009**, 131, 6973-6975; © copyright 2009 American Chemical Society. Figures 4 and 5 are reprinted with permission from Sá *et al.*, *Chem. Int. Ed.* **2011**, 50, 8912-8916; © copyright 2011 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim.

ACKNOWLEDGEMENTS

We gratefully acknowledge financial support from King Abdulaziz University (grant no. D-005/431), and the CASTech grant (EP/G012156/1) from the EPSRC.

References

- [1] Forzatti, P.; Lietti, L. *Catal. Today* **1999**, 52, 165-181.
- [2] Jackson, S.D. *Chem. Eng. J.* **2006**, 120, 119-125.
- [3] Sie, S.T. *Appl. Catal. A* **2001**, 212, 129-151.
- [4] Rodriguez, J.A.; Hanson, J.C.; Chupas, P.J. *Introduction: Goals and Challenges for the in-situ Characterization of Heterogeneous Catalysts* in *In-situ Characterization of Heterogeneous Catalysts*, Rodriguez, J.A.; Hanson, J.C.; Chupas, P.J. Eds., John Wiley and Sons, Hoboken, New Jersey, USA, **2013**, pp 1-22.
- [5] Jacques, S.D.M.; Di Michiel, M.; Kimber, S.A.J.; Yang, X.; Cernik, R.J.; Beale, A.M.; Billinge, S.J.L. *Nature Commun.* **2014**, 4, 2536.
- [6] Hanson, J.C.; Si, R.; Xu, W.; Senanayake, S.D.; Mudiyansele, K.; Stacchiola, D.; Rodriguez, J.A.; Zhao, H.; Beyer, K.A.; Jennings, G.; Chapman, K.W.; Chupas, P.J.; Martínez-Arias, A. *Catal. Today* **2014**, 229, 64-71.
- [7] Yang, B.; Lin, X.; Nilius, N.; Freund, H.-J.; Hulot, C.; Giraud, A.; Blechert, S.; Tosoni, S.; Sauer, J.; *J. Am. Chem. Soc.* **2012**, 134, 11161-11167.
- [8] Beharfarid, F.; Rodan Cuenya, B. *Top. Catal.* **2013**, 56, 1542-1559.
- [9] Morgan, K.; Burch, R.; Daous, M.; Delgado, J.J.; Goguet, A.; Hardacre, C.; Petrov, L.A.; Rooney, D.W. *Catal. Sci. Technol.* **2014**, 4, 729-737.
- [10] Romero-Sarria, F.; Martínez T., L.M.; Centeno, M.A.; Odriozola, J.A. *J. Phys. Chem. C* **2007**, 111, 14469-14475
- [11] Haruta, M.; *Catal. Today* **1997**, 36, 153-166.
- [12] Boccuzzi, F.; Manzoli, M.; Chiorino, A.; Vindigni, F. *Insights into the Reactivity of Gold: an Analysis of FTIR and HRTEM Studies* in *Environmental Catalysis over Gold-Based Materials*, Avgouropoulos, G.; Tabakova, T. Eds., *RSC Catalysis Series*, The Royal Society of Chemistry, Cambridge, UK, 2013, pp 63-95.
- [13] Heck, R.M.; Farrauto, R.J.; Gulati, S.T. *Catalyst Deactivation* in *Catalytic Air Pollution Control: Commercial Technology*, John Wiley and Sons, Hoboken, New Jersey, USA, 2002, pp 63-73.
- [14] Fang, Z.Z.; Wang, H. *Sintering of ultrafine and nanosized particles* in *Sintering of Advanced Materials*, Fang, Z.Z., Ed., Woodhead Publishing Limited, Cambridge, UK, 2010, pp. 434-474

- [15] Campbell, C.T. *Acc. Chem. Res.* **2013**, *46*, 1712-1719.
- [16] Susu, A.A.; Ogogo, E.O.; Ngomo, H.M. *Trans. IChemE Part A Chem. Eng. Research & Design* **2006**, *84*, 664-676.
- [17] Banerjee, A.; Theron, R.; Scott, R.W.J. *Chem. Commun.* **2013**, *49*, 3227-3229.
- [18] Chong, F.K.; Anderson, J.A.; Rochester, C.H. *Phys. Chem. Chem. Phys.* **2000**, *2*, 5730-5736.
- [19] Kluksdahl, H.E. *US Patent Number 3,415,737* **1968**.
- [20] Aboul-Fotouh, S.M.K.; Aboul-Gheit, N.A.K. *Chinese J. Catal.* **2012**, *33*, 697-705.
- [21] Fung, A.S.; Kelley, M.J.; Koningsberger, D.C.; Gates, B.C. *J. Am. Chem. Soc.* **1997**, *119*, 5877-5887.
- [22] Arteaga, G.J.; Anderson, J.A.; Rochester, C.H. *J. Catal.* **1999**, *184*, 268-279.
- [23] Bacaud, R.; Bussi re, P.; Figueas, F. *J. Catal.* **1981**, *69*, 399-409.
- [24] McVicker, Garten, R.L.; Baker, R.T.K. *J. Catal.* **1978**, *54*, 129-142.
- [25] Arnal, P.M.; Comotti, M.; Sch uth, F.; *Angew. Chem. Int. Ed.* **2006**, *45*, 8224-8227.
- [26] Botella, P.; Corma, A.; Navarro, M.T.; Quesada, M. *J. Mater. Chem.* **2009**, *19*, 3168-3175.
- [27] Somorjai, G.A.; Park, J.Y. *Top. Catal.* **2008**, *49*, 126-135.
- [28] Joo, S.H.; Park, J.Y.; Tsung, C.-K.; Yamada, Y.; Yang, P.; Somorjai, G.A. *Nat. Mater.* **2009**, *8*, 126-131.
- [29] Yin, Y.D.; Rioux, R.M.; Erdonmez, C.K.; Hughes, S.; Somorjai, G.A.; Alivisatos, A.P. *Science* **2004**, *304*, 711-714.
- [30] Wang, X.; Rodriguez, J.A.; Hanson, J.C.; Gamarra, D.; Mart nez-Arias, A.; Fern ndez-Garc a, M. *J. Phys. Chem. B* **2005**, *109*, 19595-19603.
- [31] Hatanaka, M.; Takahashi, N.; Takahashi, N.; Tanabe, T.; Nagai, Y.; Suda, A.; Shinjoh, H. *J. Catal.* **2009**, *266*, 182-190.
- [32] Ciston, J.; Si, R.; Rodriguez, J.A.; Hanson, J.C.; Mart nez-Arias, A.; Fernandez-Garc a, M.; Zhu, Y. *J. Phys. Chem. C* **2011**, *115*, 13851-13859.
- [33] Kurnatowska, M.; Kepinski, L.; Mista, W. *Appl. Catal. B* **2012**, *117-118*, 135-147.
- [34] Farmer, J.A.; Campbell, C.T. *Science* **2010**, *329*, 933-936.
- [35] Aydin, C.; Lu, J.; Browning, N.D.; Gates, B.C. *Angew. Chem. Int. Ed.* **2012**, *51*, 5929-5934.
- [36] Fiedorow, R.M.J.; Chahar, B.S.; Wanke, S.E. *J. Catal.* **1978**, *51*, 193-202.
- [37] Hern ndez, W.Y.; Romero-Sarria, F.; Centeno, M.A.; Odriozola, J.A. *J. Phys. Chem. C* **2010**, *114*, 10857-10865.
- [38] Bruix, A.; Rodriguez, J.A.; Ram rez, P.J.; Senanayake, S.D.; Evans, J.; Park, J.B.; Stacchiola, D.; Liu, P.; Hrbek, J.; Illas, F. *J. Am. Chem. Soc.* **2012**, *134*, 8968-8974.
- [39] Tripkovi , V.; Cerri, I.; Nagami, T.; Bligaard, T.; Rossmeisl, J. *Phys. Chem. Chem. Phys.* **2013**, *15*, 3279-3285.
- [40] Weller, S.W.; Montagna, A.A. *J. Catal.* **1971**, *20*, 394-407.
- [41] Adamiec, J.; Fiedorow, R.M.J.; Wanke, S.E. *J. Catal.* **1985**, *95*, 492-500.
- [42] Tanaka, H.; Taniguchi, M.; Kajita, N.; Uenishi, M.; Tan, I.; Sato, N.; Narita, K.; Kimura, M. *Top. Catal.* **2004**, *30/31*, 389-396.
- [43] Hagel ken, C. *Platinum Metals Rev.* **2012**, *56*, 29-35.
- [44] D'Aniello Jr, M.J.; Monroe, D.R.; Carr, C.J.; Krueger, M.H. *J. Catal.* **1988**, *109*, 407-422.
- [45] Newton, M.A. *Chem Soc. Rev.* **2008**, *37*, 2644-2657.
- [46] Borgna, A.; Le Normand, F.; Garetto, T.F.; Apesteguia, C.R., Moraweck, B., *Studies Surf. Sci. Catal.* **1999**, *126*, 179-186.
- [47] Flynn, P.C.; Wanke, S.E. *J. Catal.* **1974**, *34*, 390-399.
- [48] Flynn, P.C.; Wanke, S.E. *J. Catal.* **1975**, *37*, 432-448.
- [49] Rice, R.W.; Chien, C.C. *J. Catal.* **1987**, *103*, 140-150.
- [50] Yao, H.C.; Sieg, M.; Plummer Jr., H.K. *J. Catal.* **1979**, *59*, 365-374.
- [51] Ruckenstein, E., *Metal-Support Interactions in Catalysis, Sintering and Redispersion*, Van Nostrand Reinhold Catalysis Series, Stevenson, S.A., Dumesic J.A., Baker, R.T.K., Ruckenstein, E., Eds., New York, USA, 1987, pp. 141-308.
- [52] Weiland, J.N. *US Patent Number 2,330,462* **1943**.
- [53] Mekler, L.A. *US Patent Number 2,391,327* **1945**.
- [54] Campbell O.F.; Decker, W.H. *US Patent Number 2,853,455* **1958**.

- [55] Schwarzenbek, E.F. *US Patent Number 3,230,179* **1966**.
- [56] Schutt, H.U. *US Patent Number 3,558,514* **1971**.
- [57] McArthur, D.P. *US Patent Number 4,039,471* **1977**.
- [58] Porcelli, R.V.; Bhise, V.S.; Shapiro, A.J. *US Patent Number 4,252,741* **1978**.
- [59] Dawes, J.L.; Devon, T.J. *US Patent Number 4,196,096* **1980**.
- [60] Chester, A.W. *US Patent Number 4,235,754* **1980**.
- [61] Fung, S.C. *US Patent Number 4,467,045* **1984**.
- [62] Upchurch, B.T.; Miller, I.M.; Brown, K.G.; Hess, R.V.; Schryer, D.R.; Sidney, B.D.; Wood, G.M., Paulin, P.A. *US Patent Number 4,829,035* **1989**.
- [63] Harandi, M.N. *US Patent Number 4,853,103* **1989**.
- [64] McKay, D.L.; Olbrich, M.E. *US Patent Number 4,902,849* **1990**.
- [65] Feldman, R.J.; Dufallo, J.M.; Schwartz, W.A.; Williams, T.S. *US Patent Number 5,315,056* **1994**.
- [66] Hagemeyer, A.; Watzenberger, O.; Deimling, O. *US Patent Number 5,691,262* **1997**.
- [67] Brunet, F.-X.; Bromet, E.; Deves, J.-M. Humeau, D.; Snachez, E. *US Patent Number 6,239,055* **2001**.
- [68] Capelle, M.; Deves, J.-M.; Hoffmann, F.; They, M. *US Patent Number 6,426,052* **2002**.
- [69] Lew, L.E. *US Patent Number 8,372,770* **2013**.
- [70] Sadasivan Vijaykumari, S.; Chewter, L.A.; van Westrenen, J. *International Patent Number 2013079500* **2013**
- [71] Lew, L.E. *US Patent Number 8,815,201* **2014**.
- [72] Glassl, H.; Kramer, R.; Hayek, K. *J. Catal.* **1981**, *68*, 388-396.
- [73] Tatarchuk, B.J.; Dumesic, J.A. *J. Catal.* **1981**, *70*, 308-322.
- [74] Tatarchuk, B.J.; Dumesic, J.A. *J. Catal.* **1981**, *70*, 323-334.
- [75] Tatarchuk, B.J.; Dumesic, J.A. *J. Catal.* **1981**, *70*, 335-346.
- [76] Adler, S.F.; Keavney, J.J. *J. Phys. Chem.* **1960**, *64*, 208-212.
- [77] Dautzenberg, F.M.; Wolters, H.B.M. *J. Catal.* **1978**, *51*, 26-39.
- [78] Ruckenstein, E.; Chu, Y.F. *J. Catal.* **1979**, *59*, 109-122.
- [79] Chong, F.K.; Anderson, J.A.; Rochester, C.H. *J. Catal.* **2000**, *190*, 327-337.
- [80] Arteaga, G.J.; Anderson, J.A.; Becker, S.M.; Rochester, C.H. *J. Mole. Catal. A* **1999**, *145*, 183-201.
- [81] Ruckenstein, E.; Malhorta, M.L. *J. Catal.* **1976**, *41*, 303-311.
- [82] Fiedorow, R.M.J.; Wanke, S.E. *J. Catal.* **1976**, *43*, 34-42.
- [83] Jaworska-Galas, Z.; Wrzyszczy, J. *Int. Chem. Eng.* **1966**, *6*, 604-608.
- [84] Adamiec, J.; Szymura, J.A.; Wanke, S.E. *Studies Surf. Sci. Catal.* **1993**, *75*, 1405-1418.
- [85] Susu, A.A.; Ogogo, E.O. *J. Chem. Technol. Biotechnol.* **2006**, *81*, 694-705.
- [86] Tanabe, T.; Nagai, Y.; Dohmae, K.; Sobukawa, H.; Shinjoh, H. *J. Catal.* **2008**, *257*, 117-124.
- [87] Nagai, Y.; Hirabayashi, T.; Dohmae, K.; Takagi, N.; Minami, T.; Shinjoh, H.; Matsumoto, S. *J. Catal.* **2006**, *242*, 103-109.
- [88] Nagai, Y.; Dohmae, K.; Ikeda, Y.; Takagi, N.; Tanabe, T.; Hara, N.; Guilera, G.; Pascarelli, S.; Netwon, M.A.; Kuno, O.; Jiang, H.; Shinjoh, H.; Matsumoto, S. *Angew. Chem.* **2008**, *120*, 9443-9446.
- [89] Stulga, J.E.; Wynbatt, P.; Tien, J.K. *J. Catal.* **1980**, *62*, 59-69.
- [90] Manga, N.H.; Susu, A.A. *Chem. Eng. Technol.* **1996**, *19*, 263-271.
- [91] Johnson, M.F.L.; Keith, C.D. *J. Phys. Chem.* **1963**, *67*, 200-201.
- [92] Hassan, S.A.; Khalil, F. M.; El-Gahal, F.G. *J. Catal.* **1976**, *44*, 5-14.
- [93] Baker, R.T.K.; Prestridge, E.B.; Garten, R.L. *J. Catal.* **1979**, *59*, 293-302.
- [94] Kubacka, A.; Martínez-Arias, A.; Fernández-García, M.; Di Michel, M.; Newton, M.A. *J. Catal.* **2010**, *270*, 275-284.
- [95] Newton, M.A.; Di Michiel, M.; Kubacka, A.; Fernández-García, M. *J. Am. Chem. Soc.* **2010**, *132*, 4540-4541.
- [96] Kubacka, A.; Iglesias-Juez, A.; Di Michiel, M.; Newton, M.A.; Fernández-García, M. *Phys. Chem. Chem. Phys.* **2013**, *15*, 8640-8647.
- [97] Newton, M.A.; Belver-Coldeira, C.; Matínez-Arias, A.; Fernández-García, M. *Nat. Mater.* **2007**, *6*, 528-532.
- [98] Newton, M.A.; Belver-Coldeira, C.; Matínez-Arias, A.; Fernández-García, M. *Angew. Chem.* **2007**, *119*, 8783-8785.

- [99] Newton, M.A.; Belver-Coldeira, C.; Matínez-Arias, A.; Fernández-García, M. *Angew. Chem. Int. Ed.* **2007**, *46*, 8629-8631.
- [100] Nishihata, Y.; Mizuki, J.; Akao, T.; Tanaka, H.; Uenishi, M.; Kimura, M.; Okamoto, T.; Hamada, N. *Nature* **2002**, *418*, 164-167.
- [101] Tanaka, H.; Taniguchi, M.; Uenishi, M.; Kajita, N.; Tan, I.; Nishihata, Y.; Mizuki, J.; Narita, K.; Kimura, M.; Kaneko, K. *Angew. Chem. Int. Ed.* **2006**, *45*, 5998-6002.
- [102] Smith, M.D.; Stepan, A.F.; Ramarao, C.; Brennan, P.E.; Ley, S.V. *Chem. Comm.* **2003**, 2652-2653.
- [103] Andrews, S.P.; Stepan, A.F.; Tanaka, H.; Ley, S.V.; Smith, M.D. *Adv. Synth. Catal.* **2005**, *347*, 647-654.
- [104] Ito, S.; Ishiguro, S.; Kunimori, K. *Catal. Today* **1998**, *44*, 145-149.
- [105] Bernal, S.; Calvino, J.J.; Cauqui, M.A.; Pérez Omil, J.A.; Pintado, J.M.; Rodríguez-Izquierdo, J.M. *Appl. Catal. B* **1998**, *16*, 127-138.
- [106] Bernal, S.; Blanco, G.; Calvino, J.J.; Cifredo, G.A.; Gatica, J.M.; Pérez, J.A.; Pintado, J.M. *Stud. Surf. Sci. Catal.* **1994**, *82*, 507-514.
- [107] Bernal, S.; Botana, F.J.; Calvino, J.J.; Cifredo, G.A.; Pérez Omil, J.A.; Pintado, J.M. *Catal. Today* **1995**, *23*, 219-250.
- [108] Yao, H.C.; Shelef, M. *J. Catal.* **1976**, *44*, 392-403.
- [109] Olsthoorn, A.A.; Boelhouwer, C. *J. Catal.* **1976**, *44*, 197-206.
- [110] Okal, J.; Kubicka, H.; Kępiński, L.; Krajczyk, L. *App. Catal. A* **1997**, *162*, 161-169.
- [111] Okal, J.; Kubicka, H. *Appl. Catal. A* **1998**, *171*, 351-359.
- [112] Okal, J.; Kępiński, L.; Krajczyk, L.; Drozd, M. *J. Catal.* **1999**, *188*, 140-153.
- [113] Lai, X.; St.Clair, T.P.; Goodman, D.W. *Faraday Discuss.* **1999**, *114*, 279-284.
- [114] Inceesungvorn, B.; López-Castro, J.; Calvino, J.; Bernal, S.; Meunier, F.C.; Hardacre, C.; Griffin, K.; Delgado, J.J. *Appl. Catal. A* **2011**, *391*, 187-193.
- [115] Breen, J.P.; Burch, R.; Hardacre, C.; Hill, C.J. *J. Phys. Chem. B* **2005**, *109*, 4805-4807.
- [116] Shibata, J.; Shimizu, K.I.; Satokawa, S.; Satsuma, A.; Hattori, T. *Phys. Chem. Chem. Phys.* **2003**, *5*, 2154-2160.
- [117] Goguet, A.; Hardacre, C.; Inceesungvorn, B.; Morgan, K.; Shekhtman, S.O. *Catal. Sci. Technol.* **2011**, *1*, 760-767.
- [118] Breen, J.P.; Burch, R.; Hardacre, C.; Hill, C.J.; Krutzsch, B.; Bandl-Konrad, B.; Jobson, E.; Cider, L.; Blakeman, P.G.; Peace, L.J.; Twigg, M.V.; Preis, M.; Gottschling, M. *Appl. Catal. B* **2007**, *70*, 36-44.
- [119] Nakatsujii, T.; Yasukawa, R.; Tabata, K.; Ueda, K.; Niwa, M. *Appl. Catal. B* **1998**, *17*, 333-345.
- [120] Kartusch, C.; Krumeich, F.; Safanova, O.; Hartfelder, U.; Makosch, M.; Sá, J.; van Bokhoven, J.A. *ACS Catal.* **2012**, *2*, 1394-1403.
- [121] Takasaki, S.; Takahashi, K.; Suzuji, H.; Sato, Y.; Ueno, A.; Kotera, Y. *Chem. Lett.* **1983**, 265-268.
- [122] Birgersson, H.; Boutonnet, M.; Järås, S.; Eriksson, L. *Top. Catal.* **2004**, *30/31*, 433-437.
- [123] Kwak, J. H.; Dagle, R.; Tustin, G.C.; Zoeller, J.R.; Allard, L.F.; Wang, Y. *J. Phys. Chem. Lett.* **2014**, *5*, 566-572
- [124] Wang, T.; Schmidt, L.D. *J. Catal.* **1981**, *70*, 187-197.
- [125] Lee, T.J.; Kim, Y.G. *J. Catal.* **1984**, *90*, 279-291.
- [126] Kearby, K.K.; Thorn, J.P.; Hinlicky, J.A. *US Patent Number 3,134,732* **1964**.
- [127] Kimberlin, C.N.; Gladrow, E.M. *US Patent Number 3,201,355* **1965**.
- [128] Brown, H.T.; *US Patent Number 3,407,135* **1968**.
- [129] Glaser, H.; Sennewald, K.; Vogt, W. *US Patent Number 2,488,295* **1966**.
- [130] Greenwood, A.R.; Vesley, K.D. *US Patent Number 3,652,231* **1972**.
- [131] Kluksdahl, H.E. *US Patent Number 3,764,557* **1973**.
- [132] Schott, S.; Lum, D.W.; Mador, I.L. *US Patent Number 3,879,311* **1975**.
- [133] Yates, D.J.C.; Kmak, W.S. *US Patent Number 3,937,660* **1976**.
- [134] Paynter, J.D.; Cecil, R.R. *US Patent Number 3,939,061* **1976**.
- [135] Kmak, W.S.; Yates, D.J.C. *US Patent Number 3,941,682* **1976**.
- [136] Paynter, J.D. *US Patent Number 3,941,716* **1976**.
- [137] Kmak, W.S.; Yates, D.J.C. *US Patent Number 3,943,052* **1976**.
- [138] Liederman, D.; Voltz, S.E. *US Patent Number 3,950,491* **1976**.

- [139] Crowson, R.; Hargrove, J.D.; Pout, C.R. *US Patent Number 3,986,982* **1976**.
- [140] Tauster, S.J.; Montagna, A.A.; Steger, J.J.; Fung, S.C.; Cross, V.R. *US Patent Number 4,634,517* **1987**.
- [141] Borghard, W.S.; Huang, T.J.; McCullen, S.B.; Schoennagel, H.J.; Tsao, Y.-Y.P.; Wong, S. *US Patent Number 4,657,874* **1987**.
- [142] Hucul, D.A. *US Patent Number 4,891,346* **1990**.
- [143] Cross, V.R.; Kao, J.L.; Vanderspurt, T.H.; Nadler, M.; Wortel, T.M. *US Patent Number 4,914,068* **1990**.
- [144] Fung, S.C.; Tauster, S.J.; Koo, J.Y. *US Patent Number 4,925,819* **1990**.
- [145] Tsao, Y.-Y.P.; von Ballmoos, R. *US Patent Number 4,929,576* **1990**.
- [146] Kellner, C.S. *US Patent Number 5,057,470* **1991**.
- [147] Williamson, R.R.; Fettis, M.E.; Cottrell, P.R. *US Patent Number 5,457,077* **1995**.
- [148] Huang, Y.-J.R.; Fung, S.C.; *US Patent Number 5,712,214* **1998**.
- [149] Fung, S.C.; Tauster, S.J.; Koo, J.Y. *US Patent Number 5,763,348* **1998**.
- [150] Fung, S.C.; Tauster, S.J.; Koo, J.Y. *US Patent Number 5,726,112* **1998**.
- [151] Capelle, M.; Deves, J.-M.; Hoffmann, F.; Thery, M. *US Patent Number 6,133,183* **2000**.
- [152] Cottrell, P.R.; Fettis, M.E. *European Patent Number 0,553,520* **1993**.
- [153] Capelle, M.; Deves, J.-M.; Hoffmann, F.; Thery, M. *European Patent Number 0,872,276* **1998**.
- [154] Wu, A.-H. *US Patent Number 8,664,144* **2014**.
- [155] Decoodt, X.; Durand, S.; Le-Goff, P.-Y.; Wermester, S. *US Patent Number 8,673,801* **2014**.
- [156] Decoodt, X.; Durand, S.; Le-Goff, P.-Y.; Wermester, S. *US Patent Number 8,680,000* **2014**.
- [157] Wu, A.-H. *US Patent Number 8,716,161* **2014**.
- [158] Pieck, C.; Jablonski, E.L.; Parera, J.M. *Appl. Catal.* **1990**, *62*, 47-60.
- [159] Baker, R.T.K.; Thomas, C.; Thomas, R.B. *J. Catal.* **1975**, *38*, 510-513.
- [160] Barbier, J.; Bahloul, D.; Marecot, P. *J. Catal.* **1992**, *137*, 377-384.
- [161] Lieske, H.; Lietz, G.; Spindler, H.; Völter, J. *J. Catal.* **1983**, *81*, 8-16.
- [162] Lietz, G.; Lieske, H.; Spindler, H.; Hanke, W.; Völter, J. *J. Catal.* **1983**, *81*, 17-25.
- [163] Anderson, J.A.; Mordente, M.G.V.; Rochester, C.H. *J. Chem. Soc., Faraday Trans. I* **1989**, *85*, 2983-2990.
- [164] Anderson, J.A.; Mordente, M.G.V.; Rochester, C.H. *J. Chem. Soc., Faraday Trans. I* **1989**, *85*, 2991-2998.
- [165] Mordente, M.G.V.; Rochester, C.H. *J. Chem. Soc., Faraday Trans. I* **1989**, *85*, 3495-3504.
- [166] Foger, K.; Jaeger, H. *Appl. Catal.* **1989**, *56*, 137-147.
- [167] Le Normand, F.; Borgna, A.; Garetto, T.F.; Apestegula, C.R.; Moraweck, B. *J. Phys. Chem.* **1996**, *100*, 9068-9076.
- [168] Monzón, A.; Garetto, T.F.; Borgna, A. *Appl. Catal. A* **2003**, *248*, 279-289
- [169] Fernández-García, M.; Chong, F.K.; Anderson, J.A.; Rochester, C.H.; Haller, G.L. *J. Catal.* **1999**, *182*, 199-207.
- [170] Aboul-Gheit, A.K.; Aboul-Enein, A.A.; Awadallah, A.E.; Ghoneim, S.A.; Emam, E.A. *Chinese J. Catal.* **2010**, *31*, 1209-1216.
- [171] Birgersson, H.; Boutonnet, M.; Klingstedt, F.; Murzin, D.Y.; Stefanov, P.; Naydenov, A. *Appl. Catal. B* **2006**, *65*, 93-100.
- [172] Lambrou, P.S.; Polychronopoulou, K.; Petallidou, K.C.; Efstathiou, A.M. *Appl. Catal. B* **2012**, *111-112*, 349-359.
- [173] Cabello Galisteo, F.; Mariscal, R.; López Granados, M.; Fierro, J.L.G.; Daley, R.A.; Anderson, J.A. *Appl. Catal. B* **2005**, *59*, 227-233.
- [174] Foger, K.; Hay, D.; Jaeger, H. *J. Catal.* **1985**, *96*, 154-169.
- [175] Daley, R.A.; Christou, S.Y.; Efstathiou, A.M.; Anderson, J.A. *Appl. Catal. B* **2005**, *60*, 117-127.
- [176] Anderson, J.A.; Daley, R.A.; Christou, S.Y.; Efstathiou, A.M. *Appl. Catal. B* **2006**, *64*, 189-200.
- [177] Pieck, C.L.; Vera, C.R.; Parera, J.M. *9th International Symposium on Catalyst Deactivation* **2001**
- [178] Christou, S.Y.; Efstathiou, A.M. *Top. Catal.* **2013**, *56*, 255-260.
- [179] Christou, S.Y.; Birgersson, H.; Fierro, J.L.G.; Efstathiou, A.M. *Environ. Sci. Technol.* **2006**, *40*, 2030-2036.
- [180] Christou, S.Y.; Birgerssin, H.; Efstathiou, A.M. *Appl. Catal. B* **2007**, *71*, 185-198.
- [181] Ali, A.-G. A.; Ali, L.I.; Aboul-Fotouh, S.M.; Aboul-Gheit, A.K. *Appl. Catal.* **1998**, *170*, 285-296.
- [182] Ali, L.I.; Ali, A.-G. A.; Aboul-Fotouh, S.M.; Aboul-Gheit, A.K. *Appl. Catal.* **1999**, *177*, 99-110.

- [183] Aboul-Fotouh, S.M.; Aboul-Gheit, A.K. *Appl. Catal. A* **2001**, *208*, 55-61.
- [184] Fung, S.C. *Catal. Today* **1999**, *53*, 325-338.
- [185] Foger, K.; Jaeger, H. *J. Catal.* **1985**, *92*, 64-78.
- [186] Foger, K.; Jaeger, H. *Appl. Catal.* **1989**, *56*, 137-147.
- [187] Dorning, T.A.; Moss, R.L. *J. Catal.* **1966**, *5*, 111-115.
- [188] Sá, J.; Goguet, A.; Taylor, S.F.R.; Tiruvalam, R.; Kiely, C.J.; Nachtegaal, M.; Hutchings, G.; Hardacre, C. *Angew. Chem. Int. Ed.* **2011**, *50*, 8912-8916.
- [189] Goguet, A.; Hardacre, C.; Harvey, I.; Narasimharao, K.; Saih, Y.; Sá, J. *J. Am. Chem. Soc.* **2009**, *131*, 6973-6975.
- [190] Sá, J.; Taylor, S.F.R.; Daly, H.; Goguet, A.; Tiruvalam, R.; He, Q.; Kiely, C.J.; Hutchings, G.J.; Hardacre, C. *ACS Catal.* **2012**, *2*, 552-560.
- [191] Li, F.; Qian, Q.; Yan, F.; Yuan, G. *Mater. Chem. Phys.* **2008**, *107*, 310-316.
- [192] Zoeller, J.R.; Singleton, A.H.; Tustin, G.C.; Carver, D.L. *US Patent 6,506,933* **2003**.
- [193] Zoeller, J.R.; Singleton, A.H.; Tustin, G.C.; Carver, D.L. *US Patent 6,509,293* **2003**.
- [194] Morgan, K.; Alhamed, Y.; Al-Zahrani, A.; Arafat, A.; Burch, R.; Daous, M.; Goguet, A.; Hardacre, C.; Petrov, L.A.; Rooney, D.W., Accepted by *Catal. Struct. React.*, **2015**
- [195] Chu, Y.F.; Ruckenstein, E. *J. Catal.* **1978**, *55*, 281-298.
- [196] Lamber, R.; Romanowski, W. *J. Catal.* **1987**, *105*, 213-226.
- [197] Sushumna, I.; Ruckenstein, E. *J. Catal.* **1987**, *108*, 77-96.
- [198] Gollob, R.; Dadyburjor, D.B. *J. Catal.* **1981**, *68*, 473-486.