



**QUEEN'S  
UNIVERSITY  
BELFAST**

## **Mechanism of Alizarin Red S and Methylene Blue Biosorption onto Olive Stone: Isotherm study in Single and Binary Systems**

Albadarin, A. B., & Mangwandi, C. (2015). Mechanism of Alizarin Red S and Methylene Blue Biosorption onto Olive Stone: Isotherm study in Single and Binary Systems. *Journal of Environmental Management*, 164, 86-93. <https://doi.org/10.1016/j.jenvman.2015.08.040>

**Published in:**  
Journal of Environmental Management

**Document Version:**  
Peer reviewed version

**Queen's University Belfast - Research Portal:**  
[Link to publication record in Queen's University Belfast Research Portal](#)

**Publisher rights**  
© 2015 Elsevier Ltd. This manuscript version is made available under the CC-BY-NC-ND 4.0 license <http://creativecommons.org/licenses/by-nc-nd/4.0/> which permits distribution and reproduction for non-commercial purposes, provided the author and source are cited.

**General rights**  
Copyright for the publications made accessible via the Queen's University Belfast Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**  
The Research Portal is Queen's institutional repository that provides access to Queen's research output. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact [openaccess@qub.ac.uk](mailto:openaccess@qub.ac.uk).

**Open Access**  
This research has been made openly available by Queen's academics and its Open Research team. We would love to hear how access to this research benefits you. – Share your feedback with us: <http://go.qub.ac.uk/oa-feedback>

# Mechanism of Alizarin Red S and Methylene Blue Biosorption onto Olive Stone: Isotherm study in Single and Binary Systems

Ahmad B. Albadarin<sup>1,2\*</sup>, Chirangano Mangwandi<sup>2</sup>

<sup>1</sup>Department of Chemical and Environmental Sciences, Materials & Surface Science Institute, University of Limerick, Ireland.

<sup>2</sup>School of Chemistry and Chemical Engineering, Queen's University Belfast, Belfast BT9 5AG, Northern Ireland UK.

## ABSTRACT

The biosorption process of anionic dye Alizarin Red S (ARS) and cationic dye methylene blue (MB) as a function of contact time, initial concentration and solution pH onto olive stone (OS) biomass has been investigated. Equilibrium biosorption isotherms in single and binary systems and kinetics in batch mode were also examined. The kinetic data of the two dyes were better described by the pseudo second-order model. At low concentration, ARS dye appeared to follow a two-step diffusion process, while MB dye followed a three-step diffusion process. The biosorption experimental data for ARS and MB dyes were well suited to the Redlich-Peterson isotherm. The maximum biosorption of ARS dye,  $q_{\max} = 16.10$  mg/g, was obtained at pH 3.28 and the maximum biosorption of MB dye,  $q_{\max} = 13.20$  mg/g, was observed at basic pH values.

In the binary system, it was indicated that the MB dye diffuses firstly inside the biosorbent particle and occupies the biosorption sites forming a monodentate complex and then the ARS dye enters and can only bind to untaken sites; forms a tridentate complex with OS active sites.

**Keywords:** *Anionic Dye; Alizarin Red S; Cationic Dye; Methylene Blue; Dyes Removal; Biosorption; Olive Stone.*

---

\*Corresponding author: Dr Ahmad B. Albadarin: [Ahmad.B.Albadarin@ul.ie](mailto:Ahmad.B.Albadarin@ul.ie). University of Limerick. Tel: +44 74 6080 5982; fax: +353 (0) 61 202568.

## **1. Introduction**

Large amounts of dye contaminated wastewater are being released yearly from leather, cosmetics, pharmaceutical, plastics and textile industries, and results in an impending hazard to human health and the ecosystem (Cao et al., 2014; Semeraro et al., 2015). The existence of such dyes in receiving water bodies is undesirable as they cut off sunlight and reduce photosynthetic activities of autotrophic organisms (Albadarin et al., 2014). The problem is escalating because these dyes are stable and non-biodegradable (Gorgulu Ari and Celik, 2013); dyes are designed to hold colour on various materials and resist water, soap and oxidizing agents (Khataee et al., 2013). Consequently, the removal of dyes from industrial effluents is a challenging problem and it is essential to optimize dye-removal methods. The low efficiency, high cost, and in some cases, the production of toxic by-products make some physical and chemical approaches such as filtration, coagulation, photocatalytic degradation and advanced oxidation processes impractical and expensive to operate (Kabbout and Taha, 2014). Biosorption has been proven as an effective and cheap process, especially when using biowastes and agricultural by-products as the biosorbent (Albadarin et al., 2011). The search for low-cost and locally available waste materials for the biosorption of dyes continues and, recently, has been extensively accelerated (Abdolali et al., 2014; Guerrero-Coronilla et al., 2015; Guo et al., 2014; Magriotis et al., 2014; Wang et al., 2015). Olive crops cover a global cultivated area of approx. 10 million hectares. One main by-product produced in olive oil extraction and pitted table olive manufacture is olive stone. In Spain during the 2009/2010 season, olive oil and table olives world production result in 0.17 and 2.10 million tons, respectively (The Int. Olive Coun. 2012). This by-product is mainly turned into bioethanol or directly burnt to produce energy (Cuevas et al., 2015; Valentina Hernández et al., 2014). Using raw olive stones as biosorbent is another economic and environmental alternative (Ronda et al., 2013). This offers the olive processing industry an opportunity to make valuable use of the huge quantities of olive stones generated every year.

Hence, olive stone (OS) was employed in this study for the biosorption of some dyes. Among the hazardous dyes, Alizarin Red S (ARS) and Methylene Blue (MB) are prime contaminants in the environment, and hence, these were selected as model dye systems. Alizarin Red S is a water soluble anthraquinone dye, is used extensively in the textile industry as a staining agent. It is considered to be one of the most recalcitrant and durable pollutants (Sun et al., 2011). This is due to its complex structures of aromatic rings that afford high optical and physicochemical stability (Fu et al., 2011). Methylene Blue is a cationic thiazine dye commonly used in various industrial applications due to its high adsorption ability. It is not regarded as highly toxic, though, it may cause several harmful effects, such as: difficult breathing on inhalation, gastritis, severe headache, painful micturition, and methemoglobinemia-like syndromes if large amounts are swallowed (Bhattacharyya and Sharma, 2005). The studies dealing with the removal of Alizarin Red S using raw biosorbents are scarce. However, previous studies on the removal of ARS onto activated materials showed that adsorption processes are very promising for pollution control (Fu et al., 2011; Zhang et al., 2001). For instant, a small amount of gold nanoparticles loaded on activated carbon (0.015 g) combined with ultrasound device achieved a high adsorption capacity (123.4 mg/g) in 5 min (Roosta et al., 2014). On the other hand, methylene blue biosorption has been investigated widely though the removal mechanism in binary systems has not yet been clearly understood. The main objectives of this study are to investigate: (i) the chemistry and the mechanism of ARS and MB biosorption onto olive stone and the type of OS–ARS, –MB interfaces occurring; (ii) the biosorption equilibrium and kinetic experimental data required for the design and operation of column reactors; (iii) the simultaneous biosorption isotherm of the two dyes in binary systems.

## **2. Materials and Methods**

### *2.1. Olive stone (OS) biomass*

The olive stones were crushed and 1000–355  $\mu\text{m}$  fraction was chosen for the characterization

and biosorption experiments without any pre-treatment. The biomass was washed a number of times with boiled water and finally with distilled water to remove any adhering dirt, and dried at 110 °C for 24 hrs. Full and comprehensive characterization of OS can be found in a previous investigation (Blázquez et al., 2014). However, fourier transform infrared spectroscopy and scanning electron microscopy were employed to characterize the OS before and after ARS and MB biosorption. The FT-IR analyses for olive stones surfaces before and after ARS and MB biosorption were tested using the KBr pressed disc technique using a Perkin Elmer Spectrum 100 within the range of 400–4000  $\text{cm}^{-1}$ . For the SEM analysis, OS samples were coated with gold and vacuumed (5–10 min) for electron reflection prior to analysis on a JEOL-JSM 6400 scanning microscope. The samples used for the FT-IR and SEM analysis were collected from the pH effect experiment (optimum pH).

## 2.2. Procedures

Alizarin Red S (342.2 g/mol) and Methylene Blue (319.8 g/mol) were purchased from Sigma Aldrich, UK. All chemical reagents were of analytical grades. Synthetic dye solutions used in the experiments were prepared with distilled water (resistivity 18.24  $\Omega\text{cm}$ ). Concentrations were measured using a UV–VIS spectrophotometer (Perkin Elmer LAMBDA 25, UK) at a maximum wavelength  $\lambda_{\text{max}} = 668$  nm for MB (Albadarin et al., 2014). Measurement of ARS concentration was carried out at  $\lambda_{\text{max}} = 425\text{--}514$  nm (Roosta et al., 2014) to minimize the pH effect on ARS concentration determination. It is known that, depending on the isosbestic point, ARS will change colour i.e. pale yellow at pH = 2; yellow orange at pH = 3–4.9; red at pH = 6.2–9 and violet at pH = 11 (Olivier Thomas and Burgess, 2007). The experiments of ARS and MB biosorption from aqueous solutions were carried out in a series of 50  $\text{cm}^3$  glass jars; samples were regularly shaken (mechanical shaker, GerhardT type LS 5) at 100 rpm and 20 °C for 72 hrs to ensure reaching the equilibrium. The effect of initial solution pH on the removal of ARS and MB was examined in the range of 2–9, containing 25  $\text{cm}^3$  of dye solution with  $C_0$  of 110

mg/dm<sup>3</sup> and biomass dosage of 5.0 g/dm<sup>3</sup>. The pH was altered using 0.1 M HCl or 0.1 M NaOH. The same procedures were employed to investigate the effect of contact time and biosorption isotherms. The initial concentrations ranging from 30 to 205 mg/dm<sup>3</sup> for ARS and MB were employed for the contact time experiment. For the biosorption isotherm studies in single and binary systems,  $C_o = 5-105$  mg/dm<sup>3</sup> for ARS and MB were used. The isotherm studies in binary system were investigated at pH 3.4 and 7.2. ARS and MB uptake,  $q$  (mg/g), and percentage of removal (%) were calculated according to Eq. (1) and (2), respectively:

$$q = \left[ \frac{C_o - C_e}{M} \right] \times V \quad (1)$$

$$\text{The percentage removal} = \left[ 1 - \frac{C_e}{C_o} \right] \times 100\% \quad (2)$$

where  $C_o$  and  $C_e$  are the initial and equilibrium concentrations of ARS and MB in mg/dm<sup>3</sup>,  $M$  is the amount of dry biomass in grams and  $V$  is the volume of the ARS/MB solution in dm<sup>3</sup>.

### 3. Results and Discussion

#### 3.1. Effect of contact time and initial dye concentration

The effect of contact time on the biosorption capacity of OS for ARS and MB was studied at

five different initial dye concentrations as revealed in Table 1. As expected, the biosorption capacity of OS increased with an increase in the initial dye concentrations. The ARS removal decreased from 85% to 50% as the ARS concentration was increased from 32 to 190 mg/dm<sup>3</sup>. While the MB removal decreased from 75% to 40% when the dye concentration increased from 30 to 205 mg/dm<sup>3</sup>. Figure 1 shows that the biosorption at various concentrations is fast in the initial stages and steadily decreases with the progress of biosorption until the equilibrium is reached. The difference in the biosorbed concentration of ARS and MB at equilibrium ( $q_e$ ) and at time  $t$  ( $q_t$ ) provides the key driving force to overcome all mass transfer resistances of the dye between the aqueous and solid phases (Liao et al., 2012).

### 3.2. Kinetic modelling

In the current study, the pseudo first-order model (Lagergren, 1898), pseudo second-order model (Ho and McKay, 1999), Intraparticle diffusion model (Weber and Morris, 1963) and Boyd kinetic model (Boyd et al., 1947a) were tested.

#### 3.2.1. Pseudo first- and second-order kinetic models

The pseudo first-order model equation is given as follow:

$$q_t = q_e \left(1 - e^{-k_1 t}\right) \quad (3)$$

The pseudo second-order equation is given as;

$$q_t = \frac{k_2 q_e^2}{(1 + k_2 q_e t)} t \quad (4)$$

where  $k_1$  (1/min) and  $k_2$  (g/mg min) are the rate constants for first- and second-order models.

Table 1 summarizes the parameters of the pseudo first- and second-order kinetic models for ARS and MB biosorption onto OS. The highest  $R^2$  values and well closer calculated  $q_{e,cal}$  to those acquired by experiments,  $q_{e,exp}$ , confirmed that the biosorption process for both dyes is best described by the pseudo-second-order equation (Figure 1). The above conclusion reveals

that the biosorption is a chemical process and the dye uptake capacity is proportional to the number of active sites (Glocheux et al., 2013; Weifeng Liu et al., 2011). Also, in Table 1, the nonlinear relations between the initial concentrations,  $C_0$ , of the dye and the rate constant,  $k_1$ , implies that mechanisms such as ion exchange and chelation are involved in the biosorption process. The decrease in rate constant,  $k_2$ , of the second-order model is attributable to the competition between higher levels of dye molecules (Albadarin et al., 2012; Albadarin et al., 2014).



### 3.2.2. Intraparticle diffusion model

The intraparticle diffusion model was employed in order to distinguish the different resistances to diffusion of ARS and MB onto olive stone. The model links the pollutant adsorbed at a given time with the time  $t$  following the Equation (5):

$$q_t = k_{di} t^{0.5} + C_{di} \quad (5)$$

$k_{di}$ , the intraparticle diffusion rate is constant and expressed in  $\text{mg/g.h}^{0.5}$  where  $i$  represents the diffusion phase number;  $C_{di}$  is proportional to the boundary layer thickness.

It can be seen in Table 2 that MB diffuses faster than ARS at low and high concentration. The plot of  $q_t$  versus  $t^{0.5}$  is linear when the intraparticle diffusion is the main resistance step in the experimental conditions. In this study, several regions were observed for the diffusion of ARS and MB in the porous olive stone materials; none of the plots passed through the origin ( $C_{di} \neq 0$ ) (see supplementary data: SD1). The values of intercept increased when the initial dye concentration was increased;  $C_{di}$  values give an idea about the boundary layer thickness; the larger the intercept, the greater is the boundary layer effect (values not shown here). The presence of different linear regions in the plot of  $q_t$  versus  $t^{0.5}$  implies that the intraparticles diffusion is not the only operative mechanism and that the biosorption kinetics of dyes on OS was controlled by both surface and intraparticle diffusion processes. At low concentration, the difference is more obvious and MB followed a three-step diffusion process while ARS seems to follow a two-step diffusion process. The difference in diffusion steps may be related to the molecular mass i.e. the higher the molecular mass, the slower the rate of diffusion. The higher charge density of MB compared to ARS enables a faster diffusion in OS biomass. In terms of diffusion parameters, the difference between ARS and MB biosorption is clearly observed for the first intraparticle diffusion step. The diffusion coefficients for MB biosorption are more than double those for ARS biosorption (Table 2). The correlating coefficients,  $R^2$ , reported in Table 2 for the intraparticle diffusion kinetic model are generally lower than that of the pseudo second-

26 order kinetic for the biosorption of ARS and MB onto OS. These findings further confirm that  
27 the pseudo second-order mechanism is dominant and the overall rate of biosorption process is  
28 controlled by several portions.

### 29 3.2.3. Boyd kinetic model

30 The Boyd kinetic model was employed to confirm the actual rate-controlling step involved in  
31 the ARS and MB biosorption onto the OS. The Boyd kinetic equations are defined as (Boyd  
32 et al., 1947b):

$$33 \quad F = 1 - \left( \frac{6}{\pi^2} \right) \exp(-Bt); \quad \text{where } F = q_t/q_e \quad (6)$$

$$34 \quad B \times t = -0.4977 - \ln(1 - F) \quad (7)$$

35 If a plot  $Bt$  versus  $t$  is a straight line passing through the origin, it indicates a particle diffusion  
36 mechanism; contrarily, film-diffusion or chemical reaction control the adsorption rate. The  
37 plots (not shown here) revealed that the experimental data for both dyes do not follow the Boyd  
38 model and therefore particle diffusion does not control the rate of the biosorption process. Once  
39 again, this suggests that film-diffusion or chemical reaction controls the rate of biosorption.  
40 The biosorption systems were, in general, controlled by chemisorption including valence forces  
41 as covalent bonds/ion exchange between the adsorbent and dye molecules until the surface  
42 active sites were fully occupied. After that, dye molecules diffused into the biosorbent for  
43 further interactions (Tavlieva et al., 2013).

### 44 3.3. pH effect

45 The solution pH plays a significant role in the chemistry of both the OS biomass and dye  
46 molecules, and has a major effect on electrostatic charges that are imparted by ionized dye  
47 molecules. As illustrated in Figure 2, the removal of ARS and MB from aqueous solution is  
48 greatly dependent on the pH of the solution, and various functional groups such as hydroxyl,  
49 carbonyl and amine groups distributed on the surface of OS were affected by the solution pH

50 (Blázquez et al., 2014). At pH above 5, the amount of ARS biosorption decreases noticeably  
51 following a typical anionic adsorption behaviour (Silvina Pirillo et al., 2009). For the anionic  
52 dye, ARS, the adsorption capacity decreased from 14.31 to 0.662 mg/g when the pH increased  
53 from 3.28 to 8.16. This is predominantly attributed to the deprotonation of the biosorbent  
54 surface and the presence of excess OH<sup>-</sup> ions competing with ARS molecules, which exist  
55 mainly in a monoanionic form (Olivier Thomas and Burgess, 2007). On the other hand,  
56 opposite trends were observed for cationic dye, MB. The amount of MB biosorbed increased  
57 with an increase in the pH of the MB solution; the maximum adsorption capacity of MB was  
58 11.35 mg/g, observed at pH 7.2. The point of zero charge of the olive stone biomass has been  
59 previously determined as 5.17 (Ronda et al., 2013). Therefore, these trends could also be well  
60 explained by the electrostatic interaction between the negatively charged surfaces of the  
61 biosorbent, at pH > pHPZC, and the cationic dye (Galán et al., 2013). The results are in  
62 agreement with previous studies in which maximum biosorption of anionic dyes were observed  
63 at pH below 5, and the optimal removal of cationic dyes reported at basic pH values (Peng et  
64 al., 2014). It is worth noting that during/after dyes biosorption, the pH of the dye solution  
65 changed and this is a strong indication of a dye–hydrogen ion exchange and complexation  
66 processes. The amount of dye biosorbed, mmol/g, was calculated and compared to the number  
67 of H<sup>+</sup> ions released/adsorbed. The molar ratio of the biosorbed dye to released/adsorbed H<sup>+</sup>  
68 ions was 2.926 and 1.014 for ARS and MB, respectively.

### 69 3.4. Isotherm experiments

#### 70 3.4.1. Single systems

71 Figure 3 shows the equilibrium isotherms of ARS and MB dyes onto OS biosorbent. Langmuir,  
72 Freundlich, Redlich-Peterson and Temkin isotherms were applied to the experimental data  
73 using non-linear regression in SigmaPlot Version 11 and the summary of the fits is presented  
74 in Table 3. The data demonstrates that the Langmuir ( $R^2 = 0.995$ ) isotherm is the best model

75 for describing the biosorption of MB onto OS. For the ARS and MB dye, the Redlich-Peterson  
76 isotherm ( $R^2 = 0.994$  and  $R^2 = 0.998$ ) gives the best description of the experimental data  
77 (Temkin and Levich, 1946). For MB biosorption, the value of  $\beta$  obtained using the Redlich-  
78 Peterson isotherm was close to unity (1.101), indicating that the isotherm is approaching the  
79 Langmuir rather than the Freundlich isotherm from (Redlich and Peterson, 1959). Also, the  
80 good fit of MB experimental equilibrium data to the Langmuir isotherm indicates the  
81 monolayer coverage and chemisorption of MB onto OS. According to Table 3, the olive stone  
82 has the monolayer Langmuir biosorption capacities of 16.10 and 13.20 mg/g for ARS and MB,  
83 respectively. At the high  $C_0$  values used in this study, ion exchange sites and functional groups  
84 are more significant than the surface area ( $0.16 \text{ m}^2/\text{g}$  (Blázquez et al., 2014)) for biosorption,  
85 where chemical precipitation of the dye anions/ cations may play a dominant role in the dye  
86 removal. This may explain the high biosorption capacities despite the relatively small surface  
87 area of OS. The value of  $1/n$  obtained from the Freundlich isotherm for ARS was 0.457 and  
88 0.426 for MB, which shows that the biosorption of ARS and MB onto OS is favourable  
89 (Albadarin et al., 2012). The slightly higher value of  $K_F$  for ARS dye indicates that OS  
90 possesses a higher biosorption capacity for ARS compared to MB dye. Table 4 provides a  
91 comparison between the biosorption capacities of ARS and MB dyes with earlier studies (Ai et  
92 al., 2011; Albadarin et al., 2014; Banat et al., 2003; Fu et al., 2011; Ghaedi et al., 2011; Gürses  
93 et al., 2006; Janoš et al., 2003; Wu et al., 2004). Keeping in mind that the olive stone used here  
94 is cheap, was used without any treatment and required very little preparation, the biosorption  
95 capacities for ARS and MB onto OS are very similar to those of alternative materials from  
96 earlier investigations.

#### 97 3.4.2. Binary systems

98 The ARS and MB dyes used in this study have very similar isotherms; ARS and MB structures  
99 contain three benzene rings in a linear structure with no side chain. Ignoring the molecular

100 charge, this suggests that in the case of competitive biosorption between the dyes, the process  
101 can be considered as a single-component biosorption of a pseudo-component with properties  
102 between the properties of the real components (Wouter Delée et al., 1998). Hence, the next  
103 step of the present work was to discuss the simultaneous biosorption isotherm of two dyes at  
104 their optimum pH (3.4 and 7.2).

105 The amount of dye biosorbed was determined and compared to that for the single system so as  
106 to investigate the competitive character of the interaction between the two dyes. In Figure 4,  
107 the curve for the binary dye solution at pH = 7.2 is almost identical to the sum of the curves for  
108 the single-components. The above observations reveal that there is very limited competition  
109 between the two components examined here. However, this competition can be detected and  
110 this explains why the total adsorbed quantity of single-dyes is larger than a mixture of the two  
111 components with the same concentration. This demonstrates that there is an abundant number  
112 of active sites by which the two dyes can be sequestered and for which they will, to some  
113 extent, compete for if co-existing in a multicomponent systems.

114 Furthermore, it can be concluded that when in the binary system (pH = 7.2), the MB dye is first  
115 to penetrate the biosorbent particle and to occupy the biosorption sites. Then, the ARS dye  
116 enters and can only bind to untaken sites in an irreversible equilibrium scenario (George Z.  
117 Kyzas et al., 2013) (Figure 4). If the above assumption is correct, the MB positive molecules  
118 may influence the biosorption of ARS negative molecules by providing a positively charged  
119 phase and consequently decreasing the repulsion between the ARS molecules and enhance the  
120 biosorption affinity. The binary system at pH = 3.4 seems to lower the amount of dyes  
121 biosorbed. This can be due to the high completion between the hydrogen ions and the MB  
122 molecules. However, this needs further investigation and will be considered for future work.

### 123 *3.5. FT-IR and SEM analysis*

124 Olive stone is a lignocellulosic material, with hemicellulose, cellulose and lignin as main

125 components. The FT-IR spectrum for OS biomass in Figure 5 is very similar to those reported  
126 for other biomasses such as tea waste and date stone (Albadarin et al., 2013). Peaks were  
127 detected around 3430 and 2920  $\text{cm}^{-1}$  and can be attributed to  $-\text{NH}_2$ ,  $-\text{OH}$  groups and  $-\text{CH}$   
128 stretching, respectively. Whereas  $>\text{C}=\text{O}$  stretching vibration, symmetric bending of  $\text{CH}_3$ ,  $-\text{OCH}_3$  in ethers, secondary amine group, esters such as  $\text{CH}_3-\text{CO}-\text{O}-$  and  $-\text{SO}_3$  of  
129 hemicelluloses were observed between 1750 and 1047  $\text{cm}^{-1}$ . The FT-IR spectra in Figure 6  
130 shows changes in surface properties and functional groups of the OS biomass after the  
131 biosorption of ARS and MB, confirmed by the change in the peak heights and shifts of  
132 functional group bands due to dyes biosorption.

134 The difference in the absorbance reading from 1 hour to 72 hours, although negative for ARS  
135 but positive for MB, is very similar, indicating that almost the same number of dye molecules  
136 are attached to the olive stone surface. The shifts and shape-changes occurring in the  $-\text{OH}$   
137 stretching band at 3430  $\text{cm}^{-1}$  shows that the dye is attached to the oxygen atoms creating  
138 monodentate, bidentate or tridentate bonds and replacing the water molecules (Benjamin and  
139 Leckie, 1981). This conclusion is in agreement with the previous findings for the molar ratio  
140 between the biosorbed dye and  $\text{H}^+$  released or adsorbed in section 3.3 and confirms that ARS  
141 formed a tridentate complex whereas MB formed a monodentate complex with OS sites.

142 The topography of the olive stone before and after biosorption of ARS and MB are shown in  
143 Figure 6. It is clear that the OS surface is non-homogeneous and rough with some visible pores  
144 and fibre-like structures. These surface characteristics will provide an increase in the uptake  
145 capacity of dye solution. After the biosorption of ARS and MB dyes, the OS surface is  
146 smoother indicating that the dyes were densely and homogeneously adhered to the surface of  
147 OS.

#### 148 **4. Conclusions**

149 Raw biomass of olive stones was proven useful for biosorption of Alizarin Red S and

150 Methylene Blue dyes. The biosorption reactions were shown to be dependent on pH, initial dye  
151 concentration and contact time. The kinetic of the biosorption process was well described by  
152 the pseudo-second order model. From the diffusion models, it was concluded that film-  
153 diffusion or chemical reaction controls the rate of biosorption. Process mechanisms, namely  
154 ion exchange and chelation, were involved in the biosorption. ARS maximum capacity was  
155 found at pH = 2, whereas MB maximum capacity was obtained at pH = 7.2. it can be concluded  
156 that ARS and MB formed tridentate and monodentate complexes, respectively, with OS sites.  
157 FT-IR analysis confirmed the interactions between olive stone biosorbent surface and ARS and  
158 MB dye molecules.

### 159 **Acknowledgment**

160 The authors would like to thank Maria del Carmen Trujillo Miranda from University of  
161 Granada, Spain, for facilitating the supply of the olive stone material.

### 162 **References**

- 163 The International Olive Council. *Olivae*. Off Mag Int Olive Counc. 2012.
- 164 Abdolali, A., Guo, W.S., Ngo, H.H., Chen, S.S., Nguyen, N.C., Tung, K.L., 2014. Typical  
165 lignocellulosic wastes and by-products for biosorption process in water and wastewater  
166 treatment: A critical review. *Bioresource Technology* 160, 57-66.
- 167 Ai, L., Zhou, Y., Jiang, J., 2011. Removal of methylene blue from aqueous solution by  
168 montmorillonite/CoFe<sub>2</sub>O<sub>4</sub> composite with magnetic separation performance. *Desalination*  
169 266, 72-77.
- 170 Albadarin, A.B., Mangwandi, C., Al-Muhtaseb, A.a.H., Walker, G.M., Allen, S.J., Ahmad,  
171 M.N.M., 2012. Kinetic and thermodynamics of chromium ions adsorption onto low-cost  
172 dolomite adsorbent. *Chemical Engineering Journal* 179, 193-202.
- 173 Albadarin, A.B., Mangwandi, C., Walker, G.M., Allen, S.J., Ahmad, M.N., 2011. Biosorption  
174 characteristics of sawdust for the removal of Cd(II) Ions: Mechanism and thermodynamic  
175 studies. *Chemical Engineering Transactions*, 1297-1302.
- 176 Albadarin, A.B., Mangwandi, C., Walker, G.M., Allen, S.J., Ahmad, M.N.M., Khraisheh, M.,  
177 2013. Influence of solution chemistry on Cr(VI) reduction and complexation onto date-pits/tea-  
178 waste biomaterials. *Journal of Environmental Management* 114, 190-201.
- 179 Albadarin, A.B., Mo, J., Glocheux, Y., Allen, S., Walker, G., Mangwandi, C., 2014. Preliminary  
180 investigation of mixed adsorbents for the removal of copper and methylene blue from aqueous  
181 solutions. *Chemical Engineering Journal* 255, 525-534.
- 182 Banat, F., Al-Asheh, S., Al-Makhadmeh, L., 2003. Evaluation of the use of raw and activated  
183 date pits as potential adsorbents for dye containing waters. *Process Biochemistry* 39, 193-202.
- 184 Benjamin, M.M., Leckie, J.O., 1981. Multiple-site adsorption of Cd, Cu, Zn, and Pb on

185 amorphous iron oxyhydroxide. *Journal of Colloid and Interface Science* 79, 209-221.

186 Bhattacharyya, K.G., Sharma, A., 2005. Kinetics and thermodynamics of Methylene Blue  
187 adsorption on Neem (*Azadirachta indica*) leaf powder. *Dyes and Pigments* 65, 51-59.

188 Blázquez, G., Calero, M., Ronda, A., Tenorio, G., Martín-Lara, M.A., 2014. Study of kinetics  
189 in the biosorption of lead onto native and chemically treated olive stone. *Journal of Industrial  
190 and Engineering Chemistry* 20, 2754-2760.

191 Boyd, G.E., Adamson, A.W., Myers Jr, L.S., 1947a. The exchange adsorption of ions from  
192 aqueous solution by organic zeolites II: Kinetics. *Journal of the American Chemical Society*  
193 69, 2836-2848.

194 Boyd, G.E., Adamson, A.W., Myers, L.S., 1947b. The Exchange Adsorption of Ions from  
195 Aqueous Solutions by Organic Zeolites. II. Kinetics1. *Journal of the American Chemical  
196 Society* 69, 2836-2848.

197 Cao, J.-S., Lin, J.-X., Fang, F., Zhang, M.-T., Hu, Z.-R., 2014. A new absorbent by modifying  
198 walnut shell for the removal of anionic dye: Kinetic and thermodynamic studies. *Bioresource  
199 Technology* 163, 199-205.

200 Cuevas, M., Sánchez, S., García, J.F., Baeza, J., Parra, C., Freer, J., 2015. Enhanced ethanol  
201 production by simultaneous saccharification and fermentation of pretreated olive stones.  
202 *Renewable Energy* 74, 839-847.

203 Fu, F., Gao, Z., Gao, L., Li, D., 2011. Effective Adsorption of Anionic Dye, Alizarin Red S,  
204 from Aqueous Solutions on Activated Clay Modified by Iron Oxide. *Industrial & Engineering  
205 Chemistry Research* 50, 9712-9717.

206 Galán, J., Rodríguez, A., Gómez, J.M., Allen, S.J., Walker, G.M., 2013. Reactive dye  
207 adsorption onto a novel mesoporous carbon. *Chemical Engineering Journal* 219, 62-68.

208 George Z. Kyzas, Nikolaos K. Lazaridis, Kostoglou, M., 2013. On the simultaneous adsorption  
209 of a reactive dye and hexavalent chromium from aqueous solutions onto grafted chitosan.  
210 *Journal of Colloid and Interface Science* 407, 432-441.

211 Ghaedi, M., Hassanzadeh, A., Kokhdan, S.N., 2011. Multiwalled carbon nanotubes as  
212 adsorbents for the kinetic and equilibrium study of the removal of Alizarin red S and morin.  
213 *Journal of Chemical and Engineering Data* 56, 2511-2520.

214 Glocheux, Y., Pasarín, M.M., Albadarin, A.B., Allen, S.J., Walker, G.M., 2013. Removal of  
215 arsenic from groundwater by adsorption onto an acidified laterite by-product. *Chemical  
216 Engineering Journal* 228, 565-574.

217 Gorgulu Ari, A., Celik, S., 2013. Biosorption potential of Orange G dye by modified *Pyracantha  
218 coccinea*: Batch and dynamic flow system applications. *Chemical Engineering Journal* 226,  
219 263-270.

220 Guerrero-Coronilla, I., Morales-Barrera, L., Cristiani-Urbina, E., 2015. Kinetic, isotherm and  
221 thermodynamic studies of amaranth dye biosorption from aqueous solution onto water hyacinth  
222 leaves. *Journal of Environmental Management* 152, 99-108.

223 Guo, J.-Z., Li, B., Liu, L., Lv, K., 2014. Removal of methylene blue from aqueous solutions by  
224 chemically modified bamboo. *Chemosphere* 111, 225-231.

225 Gürses, A., Doğar, Ç., Yalçın, M., Açıkyıldız, M., Bayrak, R., Karaca, S., 2006. The adsorption  
226 kinetics of the cationic dye, methylene blue, onto clay. *Journal of Hazardous Materials* 131,  
227 217-228.

228 Ho, Y.S., McKay, G., 1999. Pseudo-second order model for sorption processes. *Process  
229 Biochemistry* 34, 451-465.

230 Janoš, P., Buchtová, H., Rýznarová, M., 2003. Sorption of dyes from aqueous solutions onto  
231 fly ash. *Water Research* 37, 4938-4944.

232 Kabbout, R., Taha, S., 2014. Biodecolorization of Textile Dye Effluent by Biosorption on  
233 Fungal Biomass Materials. *Physics Procedia* 55, 437-444.

234 Khataee, A.R., Vafaei, F., Jannatkah, M., 2013. Biosorption of three textile dyes from



235 contaminated water by filamentous green algal *Spirogyra* sp.: Kinetic, isotherm and  
236 thermodynamic studies. *International Biodeterioration & Biodegradation* 83, 33-40.

237 Lagergren, S., 1898. Zur theorie der sogenannten adsorption gelöster stoffe *Kungliga Svenska*  
238 *Vetenskapsakademiens, Handlingar* 24, 1–39.

239 Liao, P., Malik Ismael, Z., Zhang, W., Yuan, S., Tong, M., Wang, K., Bao, J., 2012. Adsorption  
240 of dyes from aqueous solutions by microwave modified bamboo charcoal. *Chemical*  
241 *Engineering Journal* 195–196, 339-346.

242 Magriotis, Z.M., Vieira, S.S., Saczk, A.A., Santos, N.A.V., Stradiotto, N.R., 2014. Removal of  
243 dyes by lignocellulose adsorbents originating from biodiesel production. *Journal of*  
244 *Environmental Chemical Engineering* 2, 2199-2210.

245 Olivier Thomas, Burgess, C., 2007. *UV-visible Spectrophotometry of Water and Wastewater*.  
246 Elsevier.

247 Peng, X., Huang, D., Odoom-Wubah, T., Fu, D., Huang, J., Qin, Q., 2014. Adsorption of  
248 anionic and cationic dyes on ferromagnetic ordered mesoporous carbon from aqueous solution:  
249 Equilibrium, thermodynamic and kinetics. *Journal of Colloid and Interface Science* 430, 272-  
250 282.

251 Redlich, O., Peterson, D.L., 1959. A Useful Adsorption Isotherm. *The Journal of Physical*  
252 *Chemistry* 63, 1024–1024.

253 Ronda, A., Martín-Lara, M.A., Calero, M., Blázquez, G., 2013. Analysis of the kinetics of lead  
254 biosorption using native and chemically treated olive tree pruning. *Ecological Engineering* 58,  
255 278-285.

256 Roosta, M., Ghaedi, M., Mohammadi, M., 2014. Removal of Alizarin Red S by gold  
257 nanoparticles loaded on activated carbon combined with ultrasound device: Optimization by  
258 experimental design methodology. *Powder Technology* 267, 134-144.

259 Semeraro, P., Rizzi, V., Fini, P., Matera, S., Cosma, P., Franco, E., García, R., Ferrándiz, M.,  
260 Núñez, E., Gabaldón, J.A., Fortea, I., Pérez, E., Ferrándiz, M., 2015. Interaction between  
261 industrial textile dyes and cyclodextrins. *Dyes and Pigments* 119, 84-94.

262 Silvina Pirillo, María Luján Ferreira, Rueda, E.H., 2009. The effect of pH in the adsorption  
263 of Alizarin and Eriochrome Blue Black R onto iron oxides. *Journal of Hazardous Materials*  
264 168, 168–178.

265 Sun, J., Lu, H., Du, L., Lin, H., Li, H., 2011. Anodic oxidation of anthraquinone dye Alizarin  
266 Red S at Ti/BDD electrodes. *Applied Surface Science* 257, 6667-6671.

267 Tavlieva, M.P., Genieva, S.D., Georgieva, V.G., Vlaev, L.T., 2013. Kinetic study of brilliant  
268 green adsorption from aqueous solution onto white rice husk ash. *Journal of Colloid and*  
269 *Interface Science* 409, 112-122.

270 Temkin, M., Levich, V., 1946. Adsorption equilibrium on heterogeneous surfaces. *Journal of*  
271 *Physical Chemistry* 20, 1441-1457.

272 Valentina Hernández, Juan M. Romero-García, Javier A. Dávila, Eulogio Castro, Cardona,  
273 C.A., 2014. Techno-economic and environmental assessment of an olive stonebased  
274 biorefinery. *Resources, Conservation and Recycling* 92, 145–150.

275 Wang, M.-X., Zhang, Q.-L., Yao, S.-J., 2015. A novel biosorbent formed of marine-derived  
276 *Penicillium janthinellum* mycelial pellets for removing dyes from dye-containing wastewater.  
277 *Chemical Engineering Journal* 259, 837-844.

278 Weber, W.J., Morris, J.C., 1963. Kinetics of adsorption on carbon from solution. *J. Sanitary Eng.*  
279 *Div. American Society of Civil Engineering* 89, 31-59.





280 Weifeng Liu, Jian Zhang, Cheng Cheng, Guipeng Tian, Zhang, C., 2011. Ultrasonic-assisted  
281 sodium hypochlorite oxidation of activated carbons for enhanced removal of Co(II) from  
282 aqueous solutions. *Chemical Engineering Journal* 175, 24-32.

283 Wouter Delée, Cliona O'Neill, Freda R. Hawkes, Pinheiro, H.M., 1998. Anaerobic treatment of  
284 textile effluents: A review. *Journal of Chemical Technology and Biotechnology* 73, 323–335.



285 Wu, Z., Ahn, I.-S., Lee, C.-H., Kim, J.-H., Shul, Y.G., Lee, K., 2004. Enhancing the organic  
286 dye adsorption on porous xerogels. *Colloids and Surfaces A: Physicochemical and Engineering*  
287 *Aspects* 240, 157-164.  
288 Zhang, J., Li, J.-n., Deng, P.-h., 2001. Adsorption voltammetry of the scandium-alizarin red S  
289 complex onto a carbon paste electrode. *Talanta* 54, 561-566.  
290  
291

292

293

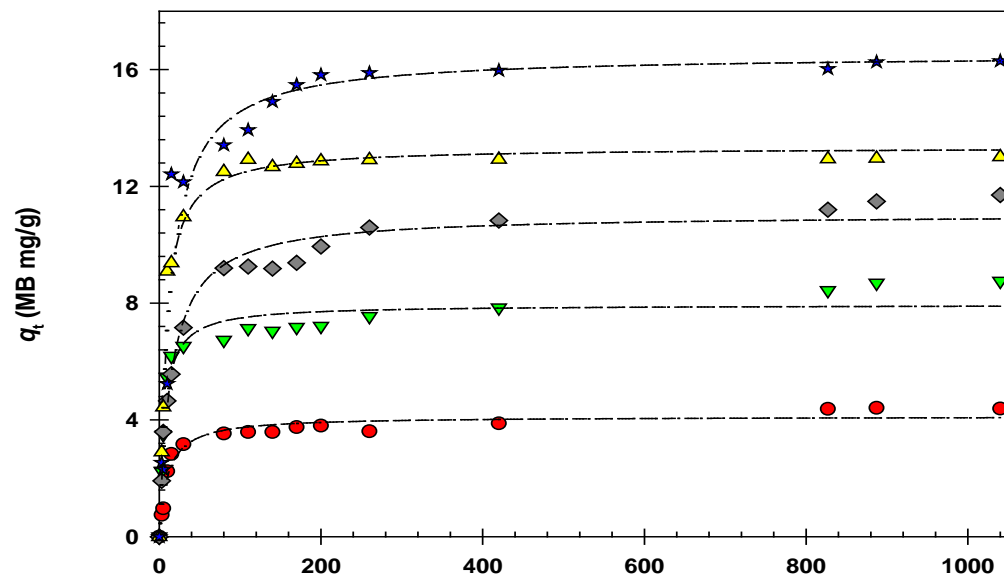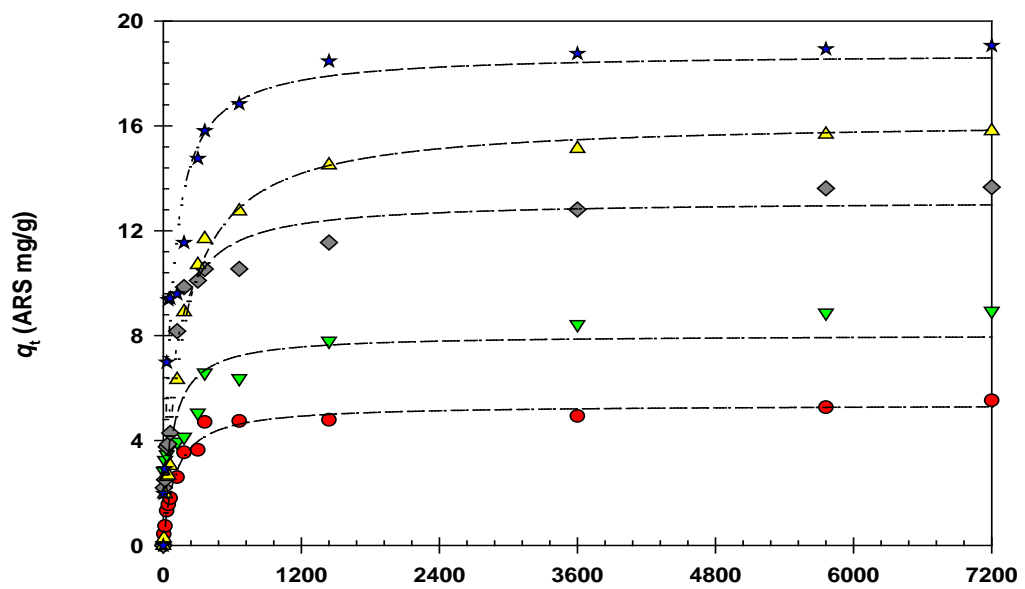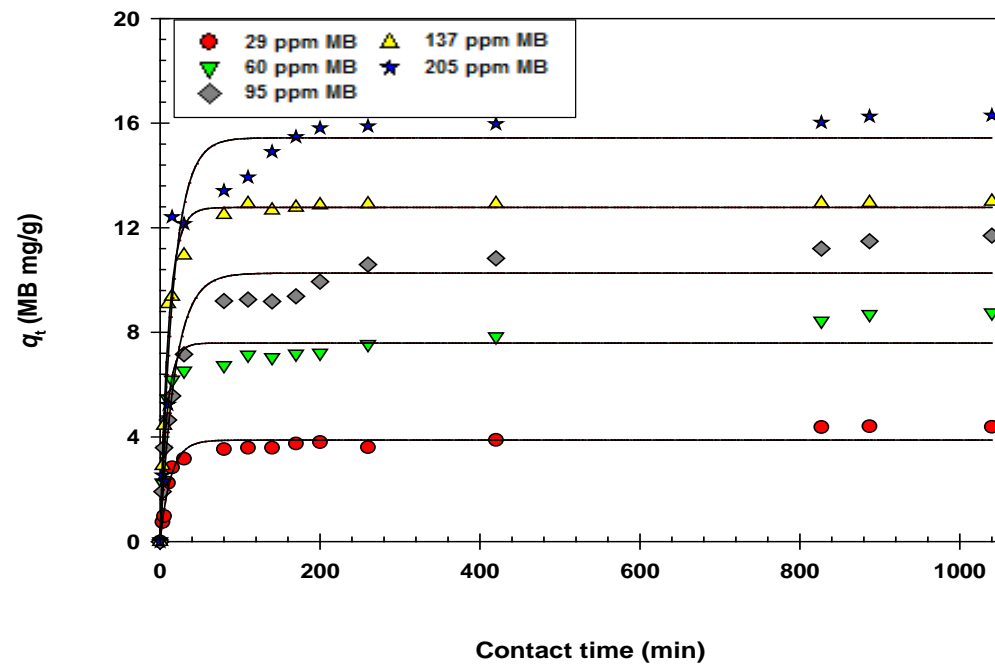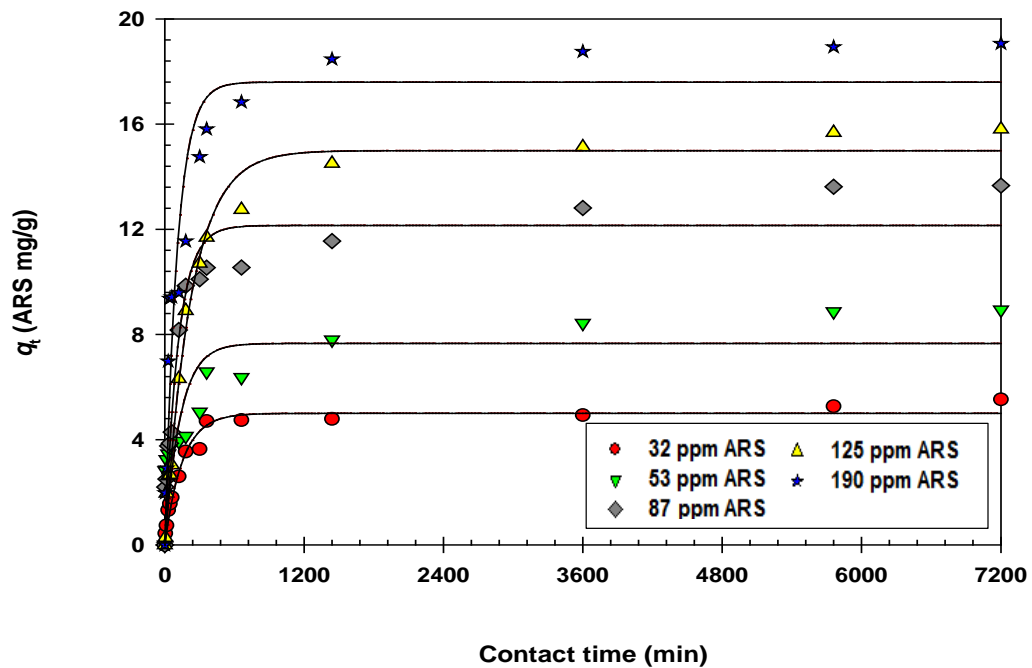



295 Figure 1: The fitting of pseudo first- (continuous line), second-order (short-dash line) models.

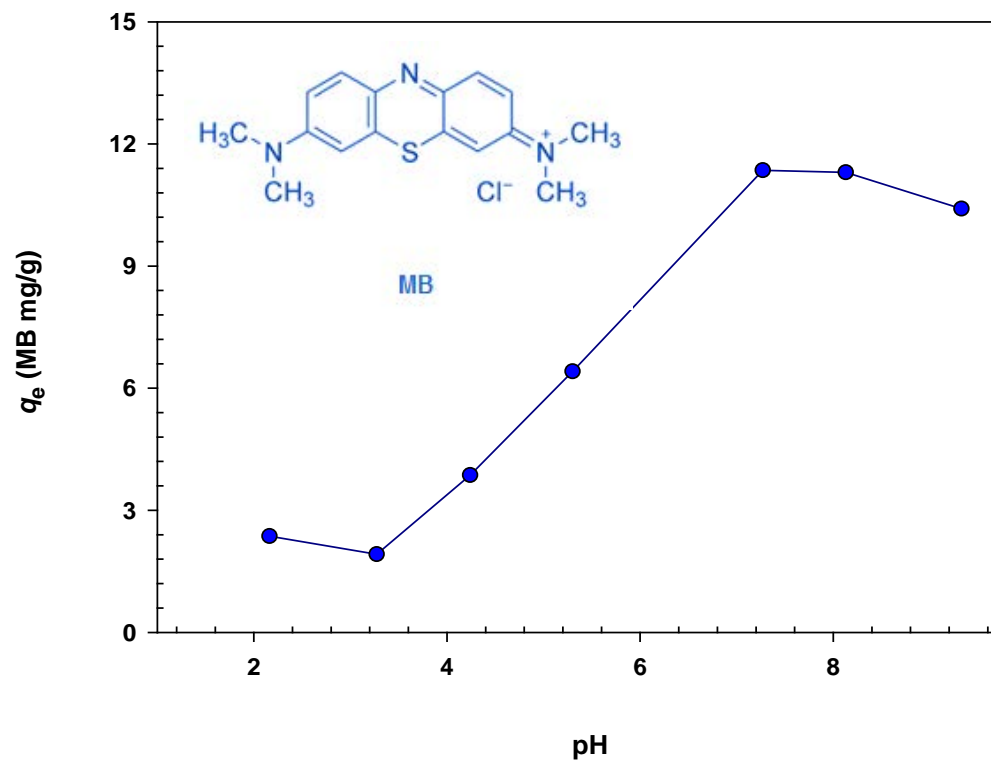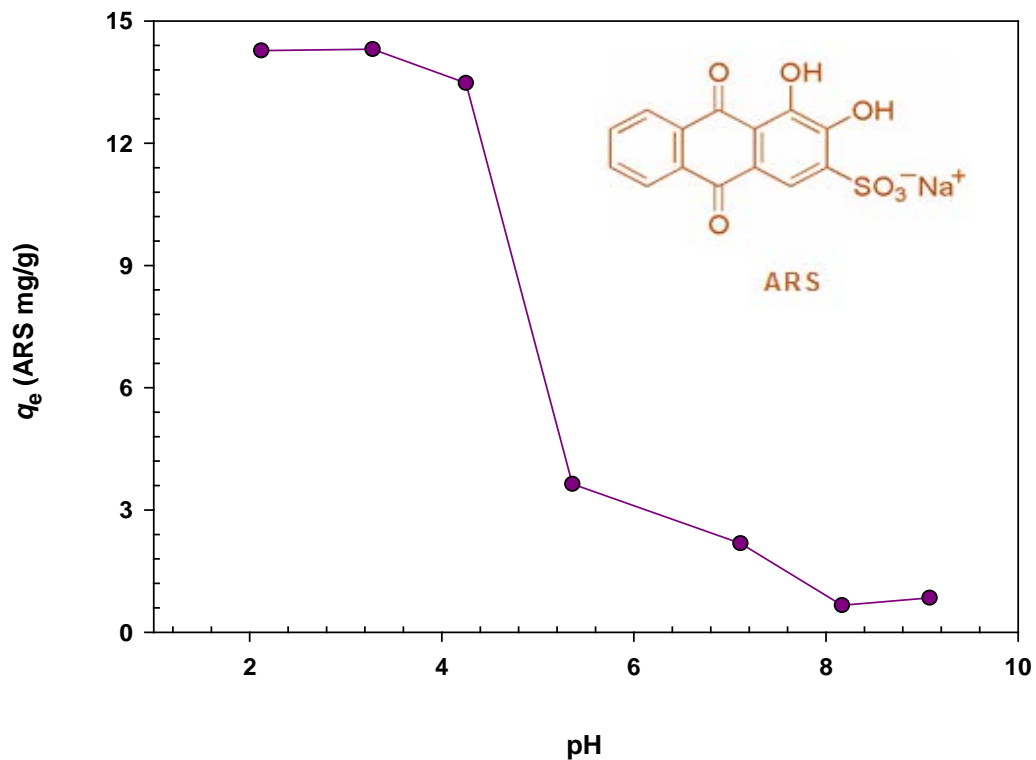

296 Figure 2: Biosorption of Alizarin Red S (ARS) and Methylene Blue (MB) onto olives stone as a function of pH. Experimental conditions:  $C_o = 110 \text{ mg/dm}^3$ ;  
297 volume  $25 \text{ cm}^3$ ; biosorbent dosage  $5.0 \text{ g/dm}^3$ ; and shaking speed 100 rpm for 72 hrs.  
298  
299


300  
301  
302  
303  
304

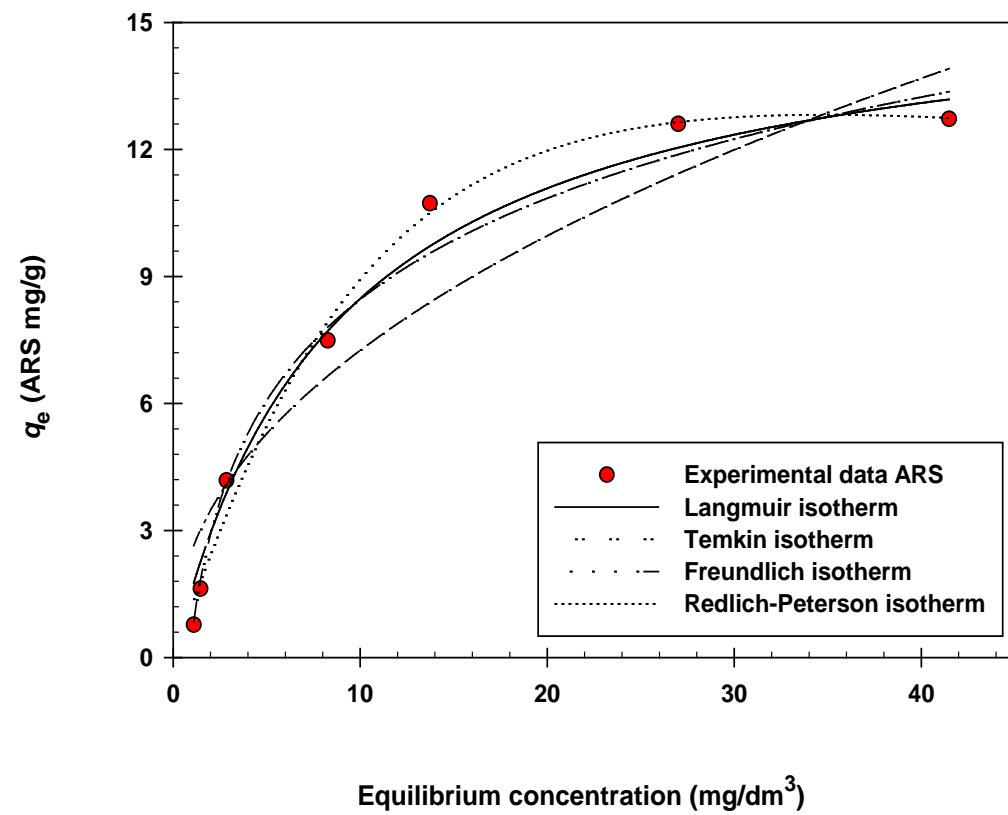

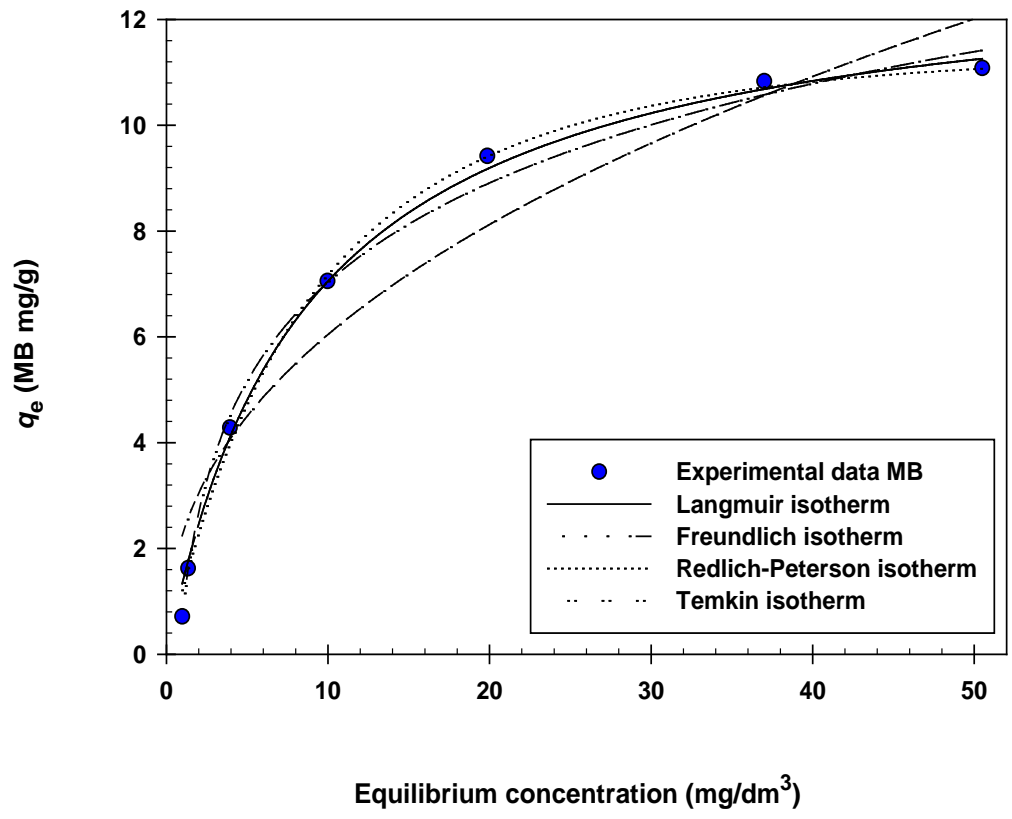


306  
 307  
 308  
 309  
 310  
 311

Figure 3: Non-linear forms of biosorption isotherm plots for ARS and MB biosorption onto OS.

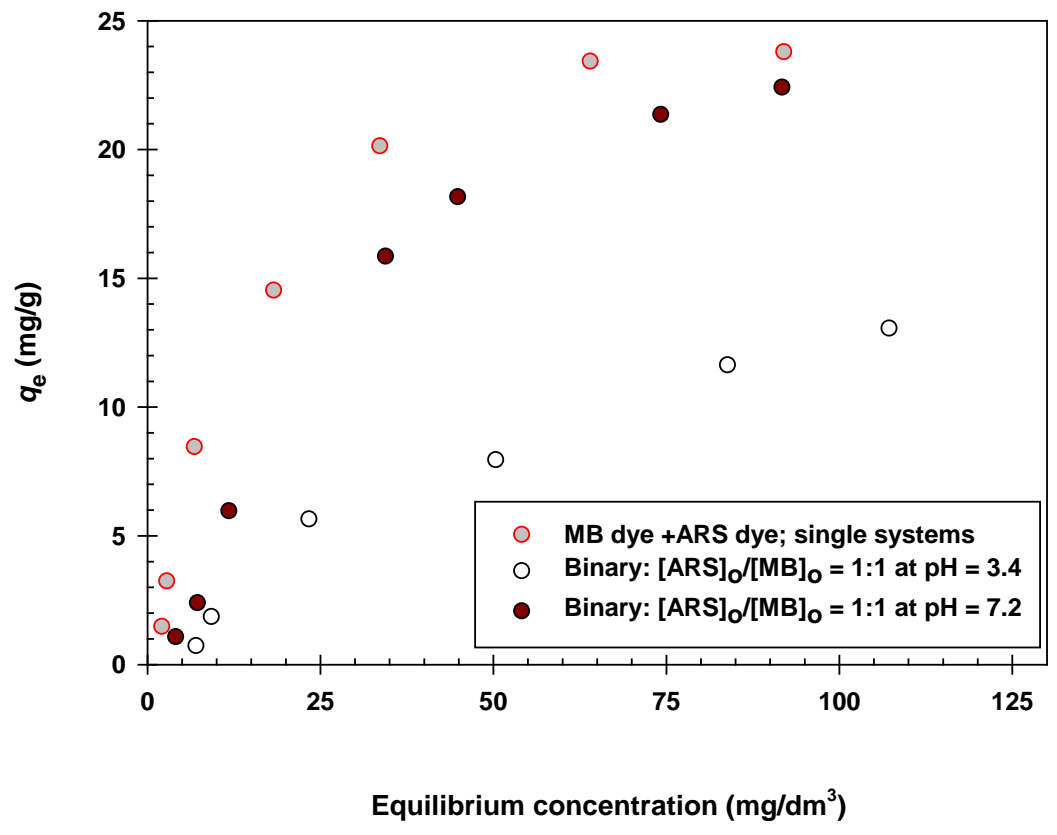




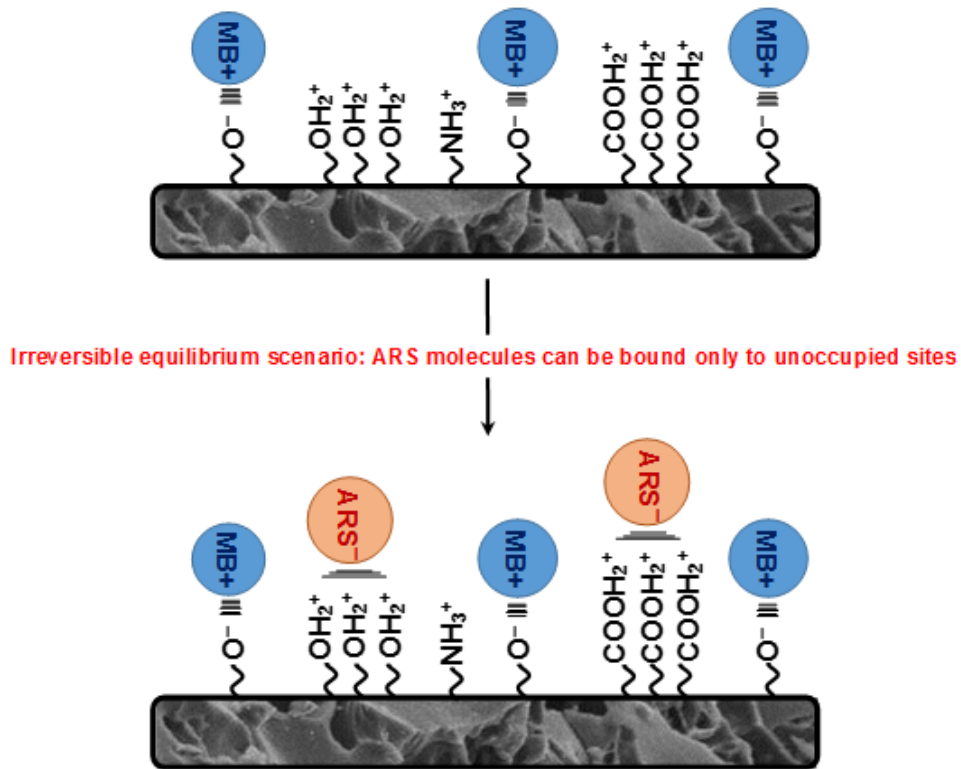


313  
 314  
 315  
 316  
 317  
 318

Figure 4: Comparison between total  $C_e$  vs total  $q_e$  at various pH for ARS and MB biosorption in single and binary mixture: ( $q_e = q_{e,ARS} + q_{e,MB}$ ) and ( $C_e = C_{e,ARS} + C_{e,MB}$ ) and proposed irreversible equilibrium scenario for the biosorption of ARS and MB onto OS in binary system.

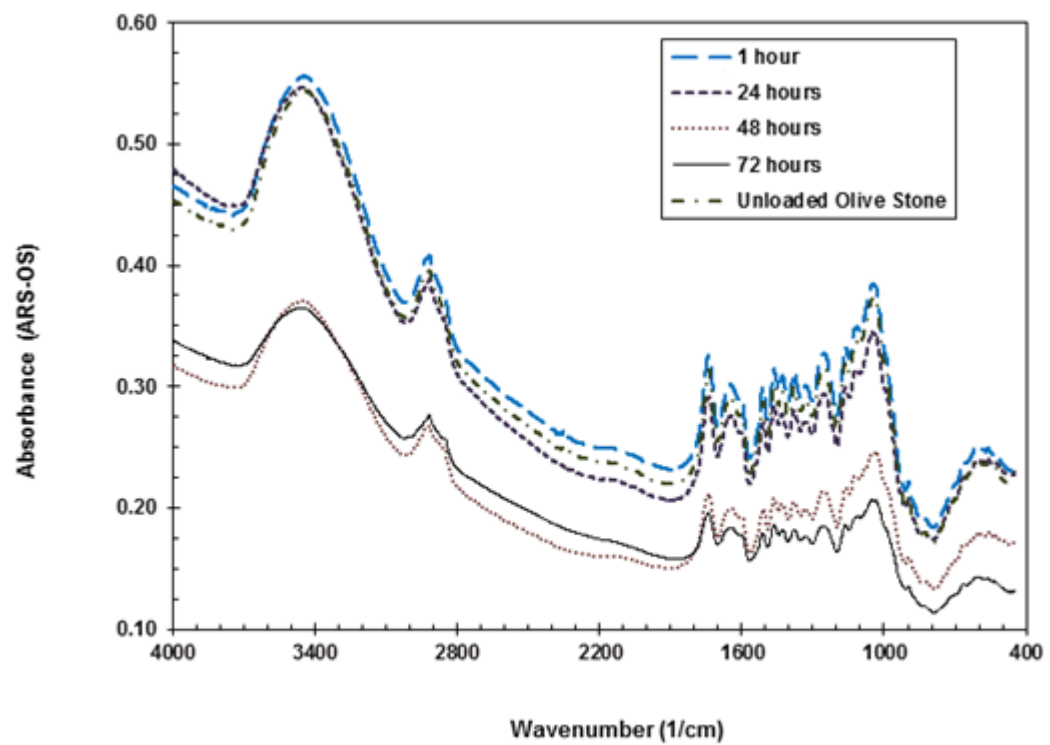


319

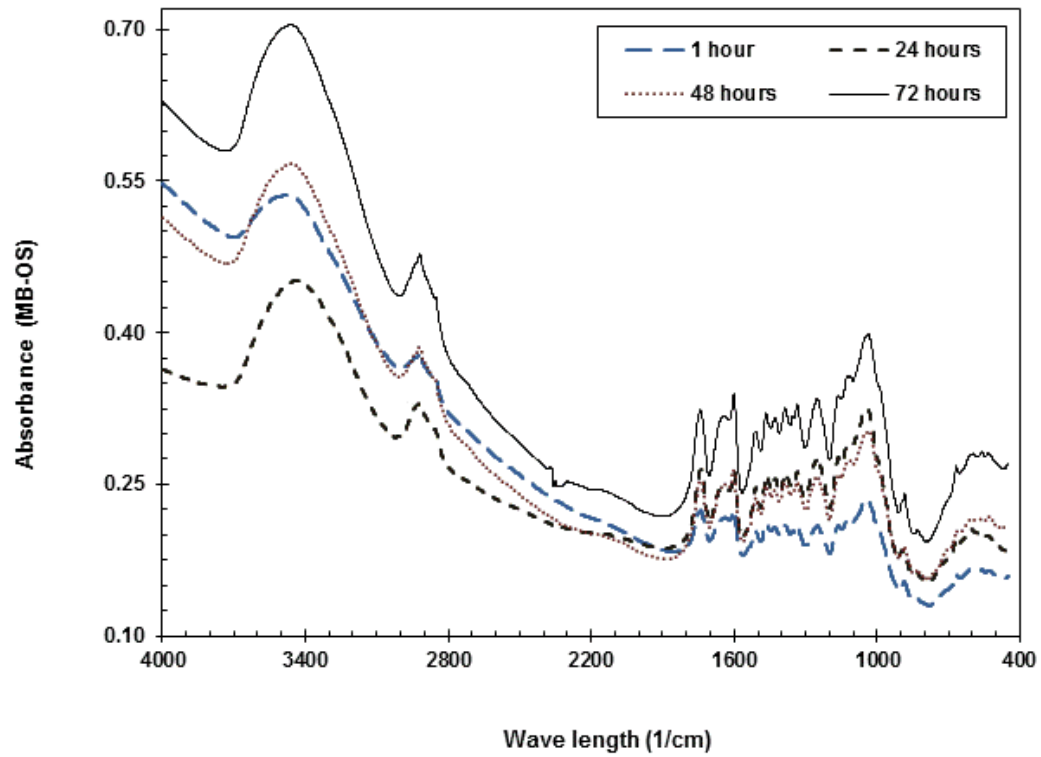


320  
 321  
 322  
 323  
 324  
 325  
 326  
 327  
 328  
 329


Figure 5: Fourier transform infrared (FT-IR) spectroscopy spectra of -unloaded olive stone (OS) and Alizarin Red S- (ARS-OS) and Methylene Blue-loaded olive stone (MB-OS).

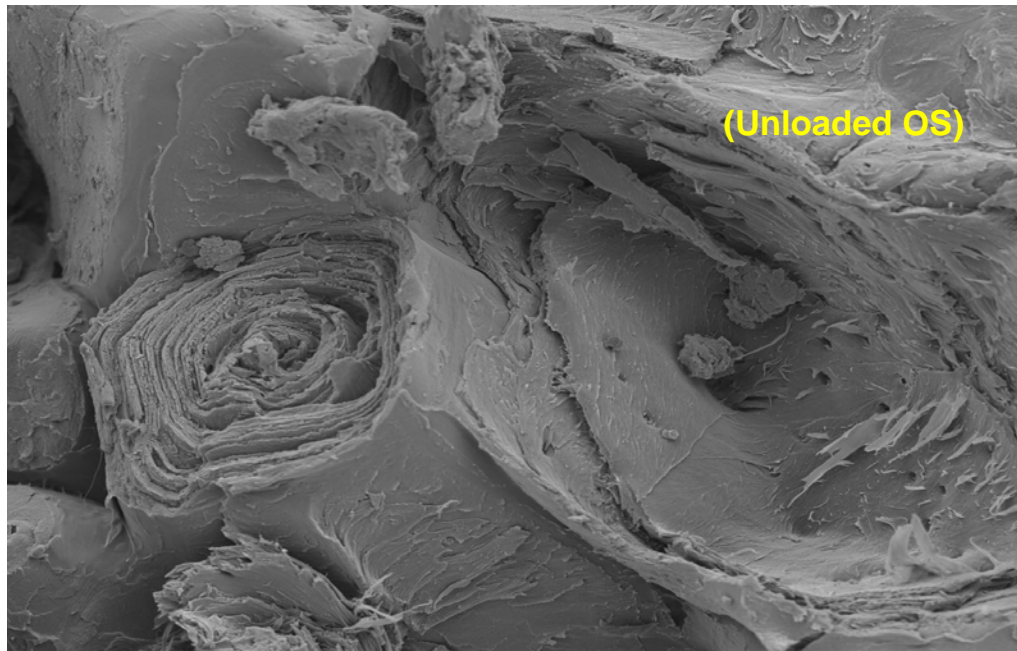


QUB SEI 3.0kV X2,000 WD 9.0mm 10µm

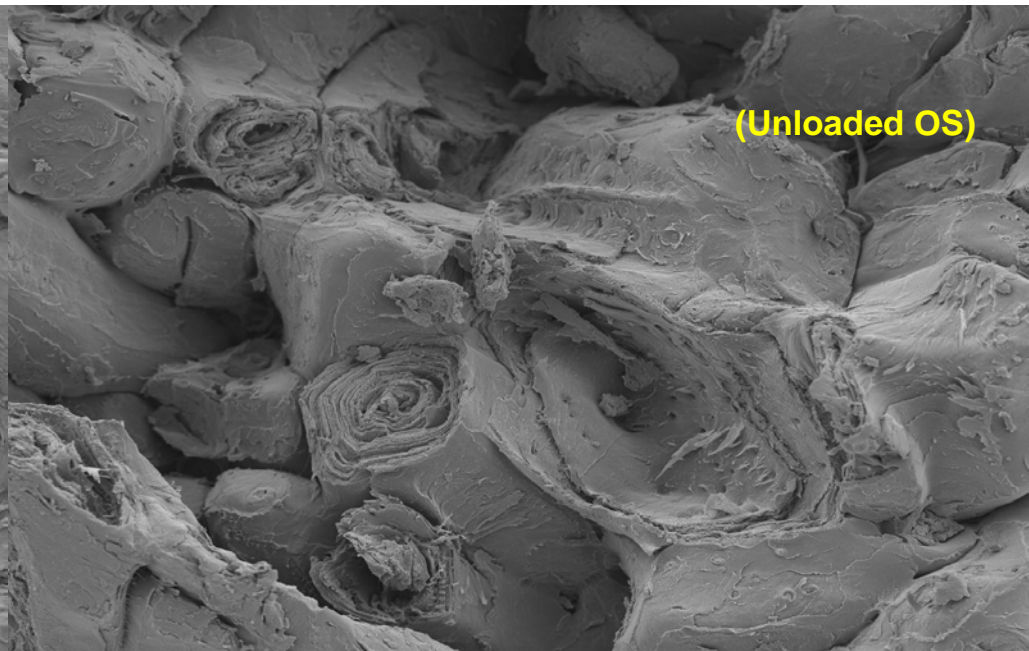

QUB SEI 3.0kV X1,000 WD 9.0mm 10µm

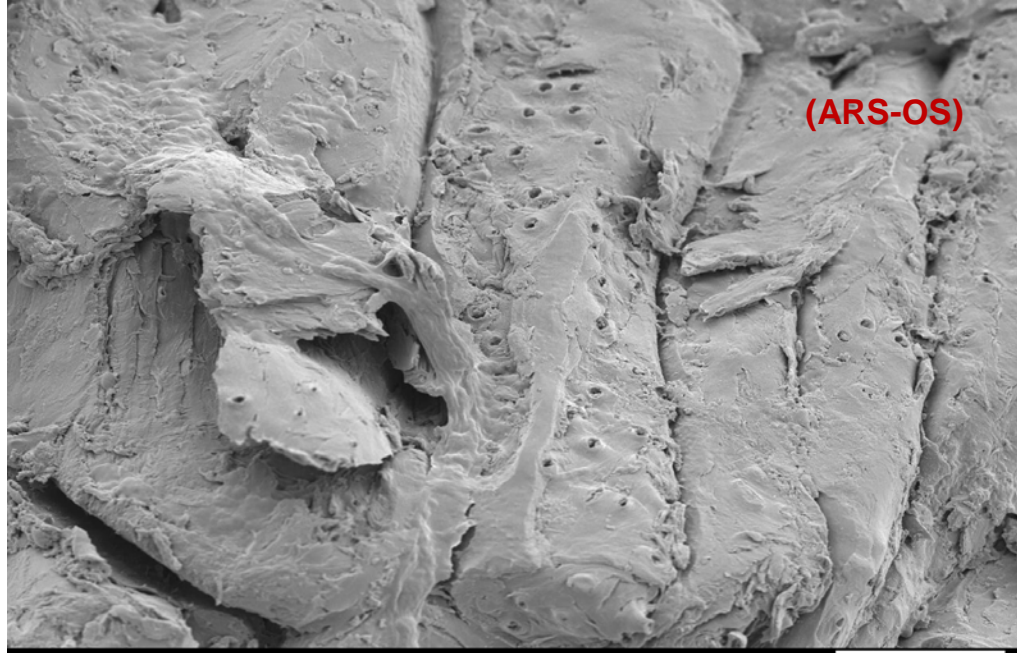

QUB SEI 3.0kV X2,000 WD 9.3mm 10µm

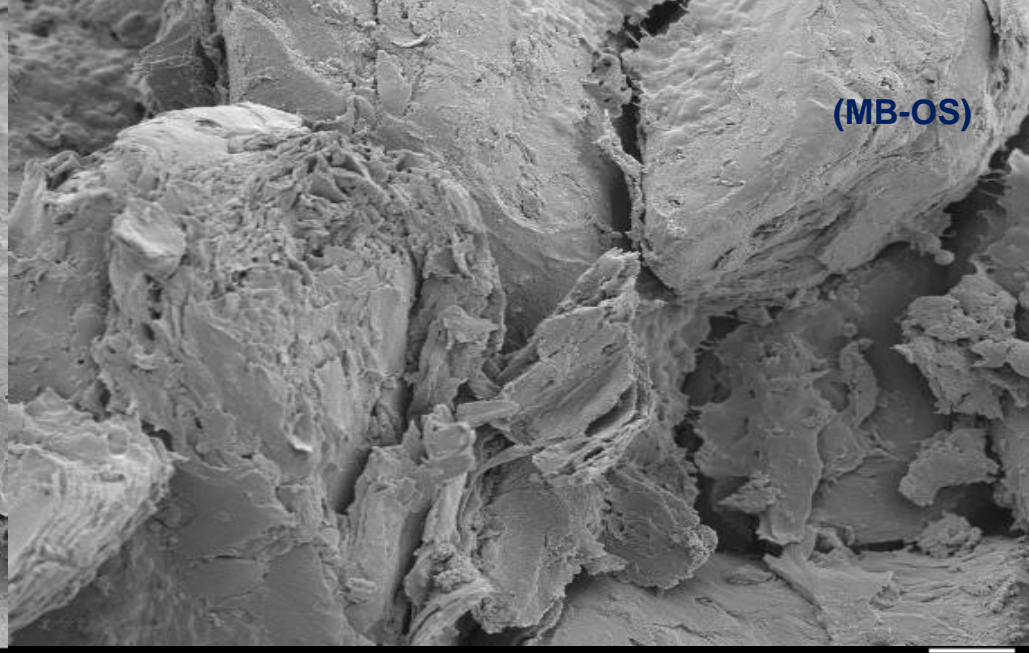

QUB SEI 3.0kV X1,000 WD 9.4mm 10µm

331 Figure 6: Scanning electron microscopy of unloaded olive stone and ARS- and MB-loaded olive stone.

332

333

334 Table 1: Pseudo first-order and pseudo second-order model constants for ARS and MB  
 335 biosorption onto olive stone.

$C_0$	Pseudo first-order model				Pseudo second-order model			
	$q_{e,exp}$ (mg/g)	$q_{e,cal}$ (mg/g)	$k_1$ (1/min)	$R^2$	$q_{e,cal}$ (mg/g)	$k_2$ (g/mg min)	$R^2$	
<b>ARS</b>	<b>32 (mg/dm<sup>3</sup>)</b>	5.531	5.008	0.008	0.987	5.363	$1.80 \times 10^3$	0.992
	<b>53 (mg/dm<sup>3</sup>)</b>	8.942	7.669	0.007	0.819	8.030	$1.70 \times 10^3$	0.910
	<b>87 (mg/dm<sup>3</sup>)</b>	13.66	12.15	0.008	0.973	13.14	$0.90 \times 10^3$	0.986
	<b>125 (mg/dm<sup>3</sup>)</b>	15.81	15.00	0.004	0.991	16.21	$0.40 \times 10^3$	0.997
	<b>190 (mg/dm<sup>3</sup>)</b>	19.06	17.61	0.009	0.959	18.78	$0.30 \times 10^3$	0.986
<b>MB</b>	<b>29 (mg/dm<sup>3</sup>)</b>	4.381	3.878	0.074	0.974	4.117	0.023	0.982
	<b>60 (mg/dm<sup>3</sup>)</b>	8.750	7.588	0.117	0.967	7.938	0.021	0.978
	<b>95 (mg/dm<sup>3</sup>)</b>	11.70	10.26	0.053	0.970	11.03	0.006	0.991
	<b>137 (mg/dm<sup>3</sup>)</b>	13.01	12.77	0.094	0.990	13.33	0.001	0.996
	<b>205 (mg/dm<sup>3</sup>)</b>	16.30	15.43	0.059	0.974	16.50	0.001	0.975

336

337

338

339

340

341

342

343

344

345

346

347

348

349 Table 2: Intraparticle diffusion model parameters for the different diffusion phase

	$C_o$	Intraparticle diffusion coefficients in $\text{mg/g.h}^{0.5}$					
		$k_{d1}$	$R^2$	$k_{d2}$	$R^2$	$k_{d3}$	$R^2$
<b>ARS</b>	<b>32 (mg/dm<sup>3</sup>)</b>	0.280	0.990	0.017	0.671	–	–
	<b>53 (mg/dm<sup>3</sup>)</b>	0.159	0.870	0.025	0.971	–	–
	<b>87 (mg/dm<sup>3</sup>)</b>	0.802	0.963	0.054	0.960	–	–
	<b>125 (mg/dm<sup>3</sup>)</b>	0.557	0.892	0.703	0.979	0.046	0.868
	<b>190 (mg/dm<sup>3</sup>)</b>	2.969	0.874	0.697	0.981	0.031	0.727
<b>MB</b>	<b>29 (mg/dm<sup>3</sup>)</b>	1.039	0.979	0.046	0.893	0.003	0.991
	<b>60 (mg/dm<sup>3</sup>)</b>	2.224	0.990	0.089	0.973	0.051	1.000
	<b>95 (mg/dm<sup>3</sup>)</b>	1.315	0.953	0.193	0.777	0.070	0.907
	<b>137 (mg/dm<sup>3</sup>)</b>	4.353	0.987	0.883	0.990	0.013	0.510
	<b>205 (mg/dm<sup>3</sup>)</b>	0.463	1.000	10.09	0.982	0.118	0.606

350

351

352

353

354

355

356

357

358

359

360

361 Table 3: The Langmuir, Freundlich, Redlich-Peterson and Temkin parameters and correlation  
 362 coefficients for ARS and MB dyes biosorption onto olive stone.

Model	Parameters	ARS	MB
<b>Langmuir isotherm</b> $q_e = \frac{q_{\max} b C_e}{1 + b C_e}$	$q_{\max}$ (mg/g)	16.10	13.20
	$b$ (dm <sup>3</sup> /mg)	0.112	0.115
	$R_{\text{adj}}^2$	0.988	0.995
<b>Freundlich isotherm</b> $q_e = K_F C_e^{1/n}$	$K_F$ (mg/g (dm <sup>3</sup> /mg) <sup>1/n</sup> )	2.529	2.262
	$1/n$	0.457	0.426
	$R_{\text{adj}}^2$	0.944	0.959
<b>Redlich-Peterson isotherm</b> $q_e = \frac{K_R C_e}{1 + a_R C_e^\beta}$	$K_R$ (dm <sup>3</sup> /mg)	1.273	1.306
	$a_R$ ((dm <sup>3</sup> /mg) <sup>1/β</sup> )	0.016	0.063
	$B$	1.407	1.101
	$R_{\text{adj}}^2$	0.994	0.998
<b>Temkin isotherm</b> $q_e = \frac{RT}{b_T} \ln A_T C_e$	$A_T$ (dm <sup>3</sup> /g)	1.163	1.342
	$b_T$	706.7	899.3
	$R_{\text{adj}}^2$	0.992	0.995

363

364

365

366

367

368

369

370



371 Table 4: Comparison of Langmuir biosorption capacities of ARS and MB with results from previous  
 372 studies.


Material	Adsorbate		Reference
	ARS [mg/g]	MB [mg/g]	
Olive Stone	16.01	13.20	This work
Teawaste & Dolomite	–	150.0	(Albadarin et al., 2014)
Clay	–	58.20	(Gürses et al., 2006)
Activated clay modified by iron oxide	32.70	–	(Fu et al., 2011)
Silica		11.21	(Janoš et al., 2003)
M-MCCNT		48.08	(Ai et al., 2011)
MMT/CoFe <sub>2</sub> O <sub>4</sub> composite		97.75	(Ai et al., 2011)
Raw date pits		27.27	(Banat et al., 2003)
Activate Date pits		80.29	(Banat et al., 2003)
Porous Xerogels	8.30 mmol/kg	–	(Wu et al., 2004)
MWCNT	161.3	–	(Ghaedi et al., 2011)

373


374

375 **Supplementary Data**

376

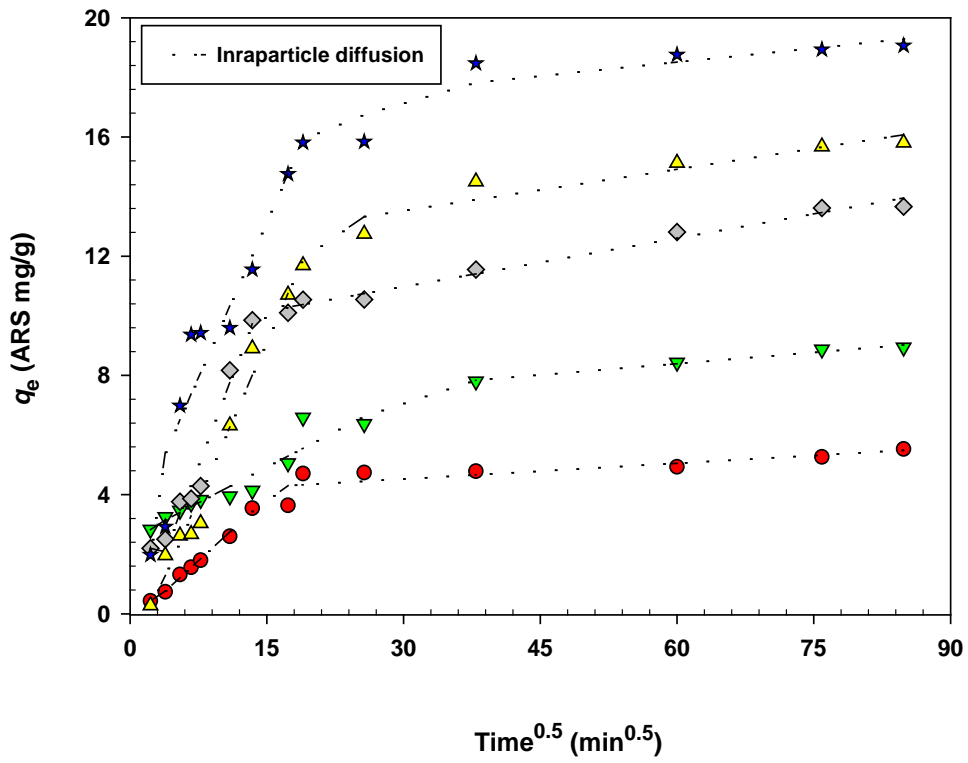

377

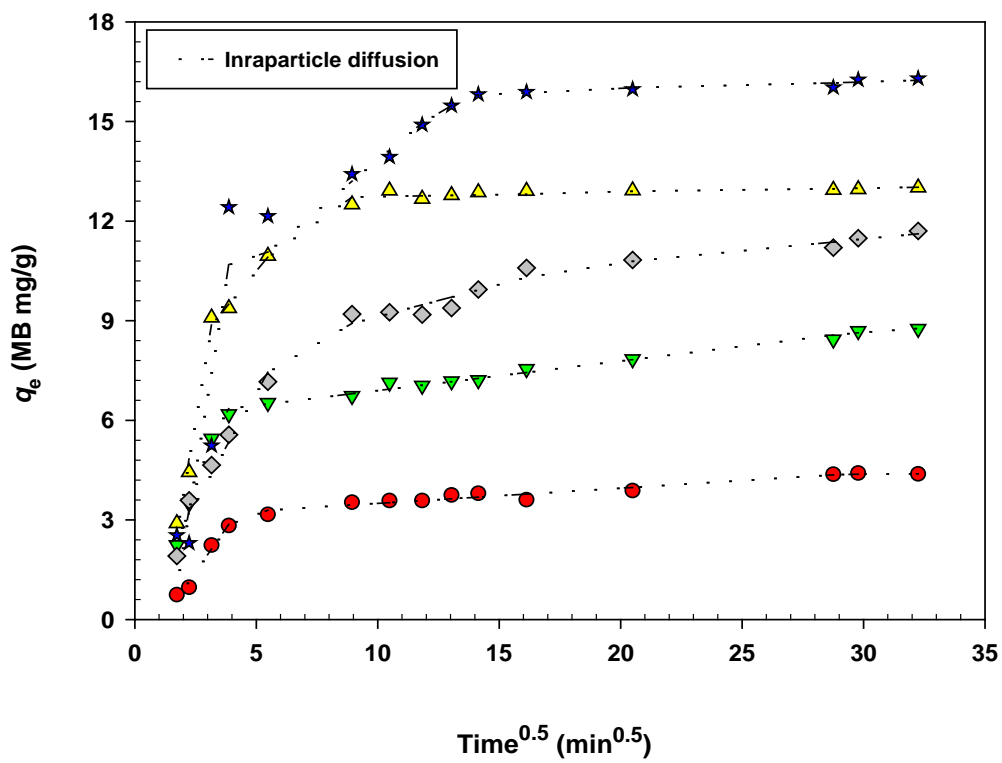

378

379

380 Figure S1: Intraparticle diffusion model ( $\text{time}^{0.5}$  vs  $q_e$  plots) for ARS and MB biosorption onto OS.

381

382