



**QUEEN'S  
UNIVERSITY  
BELFAST**

## Effect of microstructure on the fatigue properties of Ti-6Al-4V titanium alloys

Wu, G. Q., Shi, C. L., Sha, W., Sha, A. X., & Jiang, H. R. (2013). Effect of microstructure on the fatigue properties of Ti-6Al-4V titanium alloys. *Materials and Design*, 46, 668-674.  
<https://doi.org/10.1016/j.matdes.2012.10.059>

**Published in:**  
Materials and Design

**Document Version:**  
Peer reviewed version

**Queen's University Belfast - Research Portal:**  
[Link to publication record in Queen's University Belfast Research Portal](#)

### **Publisher rights**

This is the author's version of a work that was accepted for publication in Materials & Design. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Materials & Design, Vol. 46, 04/2013

### **General rights**

Copyright for the publications made accessible via the Queen's University Belfast Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

### **Take down policy**

The Research Portal is Queen's institutional repository that provides access to Queen's research output. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact [openaccess@qub.ac.uk](mailto:openaccess@qub.ac.uk).

### **Open Access**

This research has been made openly available by Queen's academics and its Open Research team. We would love to hear how access to this research benefits you. – Share your feedback with us: <http://go.qub.ac.uk/oa-feedback>

## Accepted Manuscript

Effect of microstructure on the fatigue properties of Ti-6Al-4V titanium alloys

G.Q. Wu, C.L. Shi, W. Sha, A.X. Sha, H.R. Jiang

PII: S0261-3069(12)00757-1


DOI: <http://dx.doi.org/10.1016/j.matdes.2012.10.059>

Reference: JMAD 4914

To appear in: *Materials and Design*

Received Date: 16 August 2012

Accepted Date: 31 October 2012

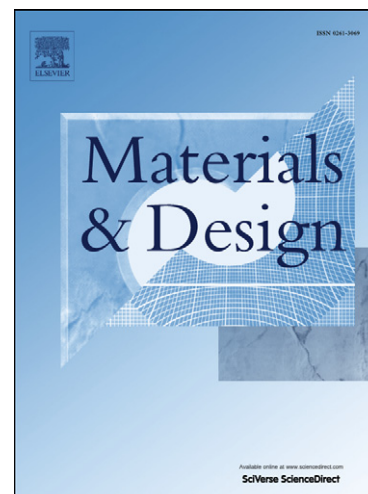

Please cite this article as: Wu, G.Q., Shi, C.L., Sha, W., Sha, A.X., Jiang, H.R., Effect of microstructure on the fatigue properties of Ti-6Al-4V titanium alloys, *Materials and Design* (2012), doi: <http://dx.doi.org/10.1016/j.matdes.2012.10.059>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Effect of microstructure on the fatigue properties of Ti-6Al-4V titanium alloys

G.Q. Wu<sup>1,\*</sup>, C.L. Shi<sup>1</sup>, W. Sha<sup>2</sup>, A.X. Sha<sup>3</sup>, H.R. Jiang<sup>1</sup>

<sup>1</sup>School of Materials Science and Engineering, Beihang University, 37 Xueyuan Road, Haidian District,

Beijing 100191, China

<sup>2</sup>School of Planning, Architecture and Civil Engineering, Queen's University Belfast, Belfast BT7 1NN,

UK

<sup>3</sup>Beijing Institute of Aeronautical Materials, Beijing 100095, China

\*Corresponding Author:

Tel: +86 1082313240; Fax: +86 1082313240

E-Mail: guoqingwu@buaa.edu.cn (G.Q. Wu)

Abstract

Through an analysis on microstructure and high cycle fatigue (HCF) properties of Ti-6Al-4V alloys which were selected from literature, the effects of microstructure types and microstructure parameters on HCF properties were investigated systematically. The results show that the HCF properties are strongly determined by microstructure types for Ti-6Al-4V. Generally the HCF strengths of different microstructures decrease in the order of bimodal, lamellar and equiaxed microstructure. Additionally, microstructure parameters such as the primary  $\alpha$  ( $\alpha_p$ ) content and the  $\alpha_p$  grain size in bimodal microstructures, the  $\alpha$  lamellar width in lamellar microstructure and the  $\alpha$  grain size in equiaxed microstructures, can influence the HCF properties.

**Keywords:** titanium alloy; microstructure; fatigue; quantitative analysis

## 1. Introduction

Due to their excellent properties (high specific strength, high fatigue strength, good corrosion resistance, etc.), titanium components (particularly Ti-6Al-4V) are often used for manufacturing critical systems such as airfoils, undercarriage components, and airframes [1-4] instead of heavy steel components. During these applications titanium structures are often exposed to fatigue loading [1]. Fatigue fracture is an important failure mode for these structures [5].

Depending on the alloy class, the parameters possibly having an influence on the fatigue life of titanium alloys include grain size (phase dimension and morphology), age hardening condition, degree of work hardening, elastic constants, and crystallographic texture [1]. Depending on the thermomechanical treatment or heat treatment of the ( $\alpha + \beta$ ) titanium alloy, such as Ti-6Al-4V, the microstructure and mechanical properties can vary in a wide range [3, 6]. Such influences have been documented in numerous reports in the literature [4, 7-11]. However, due to experimentation limitations, experimental results are not always reproducible, and thus it is difficult to compare among fatigue properties obtained from different tests, even for a same microstructure. There has not been enough data to correlate fatigue properties based on differing microstructures. Based on the comparison of microstructure types of Ti-6Al-4V alloys, Hines and Nalla [12, 13] pointed out that lamellar microstructure had higher HCF strength than bimodal microstructure. However, Zuo et al. [10] and Niinomi et al. [14] obtained the opposite result. Ivanova et al. [15] and Peters and Lütjering [16, 17] proved that bimodal microstructure had higher HCF strength than the equiaxed microstructure, and Peters et al. [17] showed that lamellar microstructure also had higher HCF strength than the equiaxed microstructure. However, it was also reported [2] that equiaxed microstructure had the highest HCF strength, and according to Ivanova and

Adachi [18, 19], lamellar microstructure had a similar HCF strength to bimodal microstructure. The reasons for this contradiction have not been well explained. Additionally, the fatigue strength would be dependent on microstructural parameters of each Ti-6Al-4V alloy, such as the  $\alpha_p$  content and  $\alpha_p$  grain size in bimodal microstructure [15, 18, 20], the  $\alpha$  grain size in the equiaxed microstructure [2, 18, 21], and the lamellar  $\alpha$  width in lamellar microstructure [10, 12, 13].

So, there is differing information in the literature concerning the relative strengths of Ti-6Al-4V alloys based on microstructure type. These authors did not necessarily use the same bimodal, lamellar, and equiaxed microstructures. These differences can make sense if we incorporate the parameters that are listed.

However, the influence of the microstructural parameters on fatigue property is difficult to investigate systematically, because the fatigue test costs a lot of human and material resources. A more comprehensive evaluation of the influence of the individual microstructure parameters on fatigue properties is difficult, because all data presented in a paper are from one research groups. This also limits the ability to evaluate additional effects due to variations in specimen preparation, test procedure, micro-alloy composition differences, heat treatment, rolling or forging procedure affecting texture, etc. [22].

Through an analysis on microstructures and HCF strengths of the Ti-6Al-4V alloys based on the literature dated from 1972 to present, effects of microstructure types and microstructure parameters on HCF properties were investigated systematically. The influences of the microstructure types (bimodal, lamellar, equiaxed) on the HCF properties were investigated. Additionally, the effects of the

microstructure parameters ( $\alpha_p$  content and  $\alpha_p$  grain size, lamellar width) on the HCF properties were investigated.

## 2. Method

In this paper, 75 sets of data in 21 references [10, 12-15, 17-21, 23-33] were collected with information about the HCF strength data and microstructure parameters of Ti-6Al-4V alloys according microstructure types (Fig. 1 and Tables 1-3). No testing was done by the authors but the work relied entirely on the literature data. All fatigue tests were performed in room-temperature air under axial loading conditions with a sine wave on smooth-bar, unnotched hourglass specimens.

[Fig. 1(a); Fig. 1(b); Fig. 1(c)]

Fig. 1. Three typical microstructures.

Most of the microstructural parameters ( $\alpha_p$  content,  $\alpha_p$  grain size and lamellar width) can be obtained from literature, but the ones that are not given clearly are analyzed by the Nano Measurer1.2 software according to the SEM images in the references. All these measured parameters are labelled as \* in Tables 1-3.  $\alpha$  grain size was measured by linear intercept method [34], and  $\alpha$  lamellar width was measured by the way described in [35]. Fatigue strength data were obtained from the stress-life (S-N) curves in the literature.

## 3. Results

According to the different fatigue life ( $10^5$ ,  $10^6$  and  $10^7$  cycles), the fatigue strengths of Ti-6Al-4V alloys with three typical microstructures (bimodal, lamellar and equiaxed) are presented in Fig. 2. The exponential curve fitting is used to show the trend and comparison of the data. Other types of curve could

have been used, but they are expected to show similar trend and comparison. Due to the large scatter of the data, a comparison using the mean and standard deviation of the HCF strength based on the three types of microstructures would not be meaningful, as there will be huge standard deviation values, making it apparent that the means overlap. It can be demonstrated that the HCF strength of the three typical microstructures is dispersive and overlapped, but as a whole, the bimodal data appear above, then lamellar and the equiaxed ones distribute at the bottom. It can be seen from the S-N curves that the fatigue life increases as the loading decreases. Generally the HCF strength of different microstructures decreases in the order of bimodal, lamellar and equiaxed microstructure.

[Fig. 2]

Fig. 2. HCF properties of Ti-6Al-4V alloy with three typical microstructures.

### 3.1 Bimodal microstructure

The effect of  $\alpha_p$  volume fraction ( $V_\alpha$ ) and  $\alpha_p$  size of Ti-6Al-4V alloy with bimodal microstructures on the HCF properties are shown in Fig. 3 and Fig. 4, respectively. Fig. 3(a-c) shows the analysis results of HCF strength at  $10^5$ ,  $10^6$  and  $10^7$  cycles, respectively. It can be seen that the fatigue strength is highest when  $V_\alpha$  is in the range of 30% to 50%. For the convenience of comparison, Fig. 3(d) divides the data into three groups according to the  $\alpha_p$  volume fraction. e.g.,  $V_\alpha < 30\%$ ,  $V_\alpha = 30-50\%$  and  $V_\alpha > 50\%$ . From the average data (Fig. 3(d)), the group of  $V_\alpha = 30-50\%$  has the highest HCF strength. It can be seen that the HCF strength of Ti-6Al-4V alloys with bimodal microstructures will increase at first and then decrease with the increasing  $\alpha_p$  volume fraction. By visually looking at the individual cases, it would appear that most data is similar, with some outliers in the 30-50% region. Fig. 3(d) was obtained by averaging. It summarises available data, but should not be used for quantitative prediction. When



presenting individual cases, we deliberately do not differentiate sources of data, so as to treat all sources equally. For example, there seems to exist really high data at  $V_\alpha = 40\%$ , but we do not go into details of examining whether they are all from one alloy or reference.

[Fig. 3(a); Fig. 3(b); Fig. 3(c); Fig. 3(d)]

Fig. 3. HCF strength of Ti-6Al-4V alloys with bimodal microstructure at different  $\alpha_p$  volume fractions: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

The HCF strength of Ti-6Al-4V alloys with bimodal microstructures as a function of the  $\alpha_p$  size is shown in Fig. 4. Fig. 4(a-c) shows the analysis results of HCF strength at  $10^5$ ,  $10^6$  and  $10^7$  cycles, respectively. It can be seen that all data have some dispersion, but in general the fatigue strength decreases with the increasing of  $\alpha_p$  size from 2.8  $\mu\text{m}$  to 20  $\mu\text{m}$ . For the convenience of comparison, Fig. 4(d) divides the data into three groups according to the  $\alpha_p$  size, e.g.,  $D_\alpha < 5 \mu\text{m}$ ,  $D_\alpha = 5-10 \mu\text{m}$  and  $D_\alpha > 10 \mu\text{m}$ . It can be seen from Fig. 4(d) that the HCF strength of Ti-6Al-4V alloys with bimodal microstructures declines apparently with the increasing of  $\alpha_p$  size from 2.8 to 20  $\mu\text{m}$ . It should be noted that Fig. 4(d) was obtained by averaging. There are individual cases apparently against the trend shown in Fig. 4(d). One should resist the temptation of making a quick conclusion by visually looking at individual cases, which was why averaging is used here. Note also that the range division, i.e.,  $D_\alpha < 5 \mu\text{m}$ ,  $D_\alpha = 5-10 \mu\text{m}$  and  $D_\alpha > 10 \mu\text{m}$ , is somewhat arbitrary, and there is actually no data for  $D_\alpha = 5 \mu\text{m}$  exactly. Different results may be obtained by dividing the range differently.

[Fig. 4(a); Fig. 4(b); Fig. 4(c); Fig. 4(d)]

Fig. 4. HCF strength of Ti-6Al-4V alloy with bimodal microstructure at different  $\alpha_p$  size: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

### 3.2 Equiaxed microstructure

Fig. 5 gives the correlation between HCF strength and  $\alpha$  grain size of Ti-6Al-4V alloys with equiaxed microstructure. Fig. 5(a-c) shows the analysis results of HCF strength at  $10^5$ ,  $10^6$  and  $10^7$  cycles, respectively. It can be seen that, both the HCF strength at  $10^5$  (Fig. 5(a)) and  $10^6$  (Fig. 5(b)) cycles decrease when the average  $\alpha$  grain size increases. However, there are some sets of extremely high HCF strength data around  $10\mu\text{m}$  grain size, as illustrated in Fig. 5(c). The literature containing this data only tested the HCF strength at  $10^7$  cycles. For the convenience of comparison, these six extremely high data in Fig. 5(c) are eliminated and the data are divided into 2 groups according to  $6\mu\text{m}$  grain size, as shown in Fig. 5(d). It can be seen that, the average HCF strength of the group with  $\alpha$  grain size less than  $6\mu\text{m}$  (including  $6\mu\text{m}$ ) is larger than that of the other ones.

[Fig. 5(a); Fig. 5(b); Fig. 5(c); Fig. 5(d)]

Fig. 5. HCF strength of Ti-6Al-4V alloy with equiaxed microstructure at different  $\alpha$  grain size: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

### 3.3 Lamellar microstructure

Fig. 6 gives the connection between the HCF strength and  $\alpha$  lamellar width of Ti-6Al-4V alloys with lamellar microstructure. The linear curve fitting is used to show the trend of the data. Other types of curve could have been used, but they are expected to show a similar trend. From both the limited results and fitting lines (not good fits to the data) of HCF strength at  $10^5$ ,  $10^6$  and  $10^7$  cycles, respectively, the HCF strength declines with the increasing of  $\alpha$  lamellar width. It should be noted that these fitting lines are not good fits to the data, but are used to show trends.

[Fig. 6(a); Fig. 6(b); Fig. 6(c)]

Fig. 6. HCF strength of Ti-6Al-4V alloy with lamellar microstructure at different  $\alpha$  lamellar width: (a)  $10^5$  cycles, (b)  $10^6$  cycles and (c)  $10^7$  cycles.

#### 4 Discussion

From all the results above, the HCF strength of the Ti-6Al-4V alloy with three typical microstructures may overlap among themselves in some ranges because of the limited material manufacturing industry [36]. However, generally the HCF strengths of different microstructures decrease in the order of bimodal, lamellar and equiaxed microstructure [37]. Though the conclusion of the bimodal microstructures having best high cycle fatigue is in contradiction with some literature, there are also ample explanation on the effect of bimodal structure on the crack growth [38], and statements that the bimodal structure generally ensures good fatigue endurance of the Ti-6Al-4V alloy [39] and a bimodal grain structure seems beneficial [40]. These references should be consulted for discussions on the mechanisms. Experimentally, bimodal Ti-6Al-4V alloys with best high fatigue properties has been found in many publications used to develop the analysis in this paper, as well as in publications not used, for example [39]. Therefore, it will be much more beneficial to choose bimodal microstructure if the work pieces need strict fatigue properties. Manufacturers can optimize the HCF strength of bimodal microstructures by controlling the  $\alpha_p$  volume fraction and  $\alpha_p$  size, respectively. From the present analysis results, it is beneficial to choose the microstructure with  $\alpha_p$  volume fraction ranging from 30%-50% and  $\alpha_p$  size as small as possible. For equiaxed or lamellar microstructures, the HCF strength can be controlled by  $\alpha$  grain size or  $\alpha$  lamellar width [37,41]. However, due to the limited data, there is no definite conclusion. Therefore this work will continue until definite conclusions are drawn from the increasing database in the future.

## 5. Conclusion

Through an analysis on the microstructures and HCF strengths of Ti-6Al-4V alloys which dated from 1972 to date, the effects of microstructure types and microstructure parameters on the HCF strength were investigated systematically. Based on this analysis, the following conclusions can be drawn:

(1) The microstructure types of Ti-6Al-4V alloy have significant influence on the HCF strength.

Generally the HCF strengths of different microstructures decrease in the order of bimodal, lamellar and equiaxed microstructure.

(2) The primary  $\alpha$  content and grain size in bimodal microstructure of Ti-6Al-4V alloy has significant influence on the HCF strength. The HCF strength increases at first, then declines with the increasing of the  $\alpha_p$  volume fraction; and the HCF strength decreases with the increasing of the  $\alpha_p$  size.

(3) The  $\alpha$  grain size in equiaxed microstructure or  $\alpha$  lamellar width in lamellar microstructure has significant influence on the HCF strength. The HCF strength declines with the increasing of either  $\alpha$  grain size or  $\alpha$  lamellar width.

## Acknowledgements

This paper is financially supported by the Cheung Kong Scholars and Innovative Research Team Program in University from Ministry of Education (Grant No. IRT0805) and the Beijing Nova Program (2007B016).

## References

- [1] Leyens C, Peters M, editors. Titanium and titanium alloys: fundamentals and applications. Weinheim: Wiley-VCH; 2003.
- [2] Lütjering G, Williams JC. Titanium. 2nd ed. New York: Springer Berlin Heidelberg; 2007.
- [3] Oberwinkler B, Riedler M, Eichlseder W. Importance of local microstructure for damage tolerant light weight design of Ti-6Al-4V forgings. *Int J Fatigue* 2010;32:808-14.
- [4] Knobbe H, Köster P, Christ H, Fritzen C, Riedler M. Initiation and propagation of short fatigue cracks in forged Ti-6Al-4V. *Procedia Eng* 2010;2:931-40.
- [5] Zhang J, Cheng X, Li Z. Total fatigue life prediction for Ti-alloys airframe structure based on durability and damage-tolerant design concept. *Mater Des* 2010;31:4329-35.
- [6] Stoschka M, Tan W, Eichlseder W, Stockinger M. Introduction to an approach based on the ( $\alpha + \beta$ ) microstructure of elements of alloy Ti-6Al-4V. *Procedia Eng* 2009;1:31-4.
- [7] Pilchak AL, Williams REA, Williams JC. Crystallography of fatigue crack initiation and growth in fully lamellar Ti-6Al-4V. *Metall Mater Trans A* 2010;41:106-24.
- [8] Oguma H, Nakamura T. The effect of microstructure on very high cycle fatigue properties in Ti-6Al-4V. *Scr Mater* 2010;63:32-4.
- [9] Chan KS. Changes in fatigue life mechanism due to soft grains and hard particles. *Int J Fatigue* 2010;32:526-34.
- [10] Zuo JH, Wang ZG, Han EH. Effect of microstructure on ultra-high cycle fatigue behavior of Ti-6Al-4V. *Mater Sci Eng A* 2008;473:147-52.

- [11] Szczepanski CJ, Jha SK, Larsen JM, Jones JW. Microstructural influences on very-high-cycle fatigue-crack initiation in Ti-6246. *Metall Mater Trans A* 2008;39:2841-51.
- [12] Hines JA, Lütjering G. Propagation of microcracks at stress amplitudes below the conventional fatigue limit in Ti-6Al-4V. *Fatigue Fract Eng Mater Struct* 1999;22:657-65.
- [13] Nalla RK, Boyce BL, Campbell JP, Peters JO, Ritchie RO. Influence of microstructure on high-cycle fatigue of Ti-6Al-4V: bimodal vs. lamellar structures. *Metall Mater Trans A* 2002;33:899-918.
- [14] Niinomi M, Akahori T, Fukunaga K, Eylon D. Fatigue crack initiation and fatigue life prediction of Ti-6Al-4V ELI. In: Boyer RR, Eylon D, Lütjering G, editors. *Fatigue behavior of titanium alloys*, Warrendale, PA: TMS; 1999, p. 307-14.
- [15] Ivanova SG, Biederman RR, Sisson RD. Investigation of fatigue crack initiation in Ti-6Al-4V during tensile-tensile fatigue. *J Mater Eng Perform* 2002;11:226-31.
- [16] Peters M, Lütjering G. Control of microstructure and texture in Ti-6Al-4V. In: Kimura H, Izumi O, editors. *Titanium '80 science and technology*, New York: AIME; 1980, p. 925-35.
- [17] Peters JO, Lütjering G. Comparison of the fatigue and fracture of  $\alpha + \beta$  and  $\beta$  titanium alloys. *Metall Mater Trans A* 2001;32:2805-18.
- [18] Ivanova SG, Cohen FS, Biederman RR, Sisson RD. Role of microstructure in the mean stress dependence of fatigue strength in Ti-6Al-4V alloy. In: Boyer RR, Eylon D, Lütjering G, editors. *Fatigue behavior of titanium alloys*, Warrendale, PA: TMS; 1999, p. 39-46.
- [19] Adachi S, Wagner L, Lütjering G. Influence of microstructure and mean stress on fatigue strength of Ti-6Al-4V. In: Lütjering G, Zwischer U, Bunk W, editors. *Titanium '84 – science and technology*, vol. 4, Oberusel: Deutsche Gesellschaft für Metallkunde; 1985, p. 2139-46.

- [20] Oguma H, Nakamura T. The effect of microstructures on interior-originating fatigue fractures of Ti-6Al-4V in gigacycle region. In: Lütjering G, Albrecht J, editors. Ti-2003 science and technology, Weinheim: Wiley-VCH; 2004, p. 1783-90.
- [21] Peters M, Gysler A, Lütjering G. Influence of microstructure on the fatigue behavior of Ti-6Al-4V. In: Kimura H, Izumi O, editors. Titanium '80 science and technology, New York: AIME; 1980, p. 1777-86.
- [22] Lütjering G, Gysler A. Fatigue. In: Lütjering G, Zwicher U, Bunk W, editors. Titanium '84 – science and technology, vol. 4, Oberusel: Deutsche Gesellschaft für Metallkunde; 1985, p. 2065-83.
- [23] Peters M, Gysler A, Lütjering G. Influence of texture on fatigue properties of Ti-6Al-4V. Metall Mater Trans A 1984;15:1597-605.
- [24] Morrissey RJ, McDowell DL, Nicholas T. Frequency and stress ratio effects in high cycle fatigue of Ti-6Al-4V. Int J Fatigue 1999;21:679-85.
- [25] Bellows RS, Muju S, Nicholas T. Validation of the step test method for generating Haigh diagrams for Ti-6Al-4V. Int J Fatigue 1999;21:687-97.
- [26] Nagai K, Yuri T, Umeza O, Ogata T, Ishikawa K, Ito Y, Nishimura T. High cycle fatigue properties of Ti-6Al-4V alloys at cryogenic temperatures. In: Froes FH, Caplan IL, editors. Titanium '92 science and technology, Warrendale, PA: TMS; 1993, p. 1827-34.
- [27] Broichhausen J, Kann HV. Influence of forging conditions on the fatigue behaviour of Ti6Al4V. In: Jaffee RI, Burte HM, editors. Titanium science and technology, New York: Plenum Press; 1973, p. 1785-99.

- [28] Hines JA, Peters JO, Lütjering G. Microcrack propagation in Ti-6Al-4V alloys. In: Boyer RR, Eylon D, Lütjering G, editors. Fatigue behavior of titanium alloys, Warrendale, PA: TMS; 1999, p. 15-22.
- [29] Rudinger K, Fischer D. Relationship between primary alpha content, tensile properties and high cycle fatigue behavior of Ti-6Al-4V. In: Lütjering G, Zwischer U, Bunk W, editors. Titanium '84 – science and technology, vol. 4, Oberusel: Deutsche Gesellschaft für Metallkunde; 1985, p. 2123-30.
- [30] Nalla RK, Altenberger I, Noster U, Liu GY, Scholtes B, Ritchie RO. On the influence of mechanical surface treatments—deep rolling and laser shock peening—on the fatigue behavior of Ti-6Al-4V at ambient and elevated temperatures. Mater Sci Eng A 2003;355:216-30.
- [31] Nakanura T, Oguma H, Shiina T. Influence factors on interior-originating fatigue fractures of Ti-6Al-4V in gigacycle region: focusing on stress ratio and internal environment of material. In: Lütjering G, Albrecht J, editors. Ti-2003 science and technology, Weinheim: Wiley-VCH; 2004, p. 1775-82.
- [32] Zuo JH, Wang ZG, Han EH. Fatigue behavior of Ti-6Al-4V alloy in vacuum and at low temperature. Adv Mater Res 2008;41-42:83-90.
- [33] Geisendorfer RF. Titanium 6Al-4V plate from prealloyed powder. In: Kimura H, Izumi O, editors. Titanium '80 science and technology, New York: AIME; 1980, p. 2225-35.
- [34] Tiley J, Searles T, Lee E, Kar S, Banerjee R, Russ JC, Fraser HL. Quantification of microstructural features in  $\alpha/\beta$  titanium alloys. Mater Sci Eng A 2004;372:191-8.
- [35] Wang KX, Zeng WD, Shao YT, Zhao YQ, Zhou YG. Quantification of microstructural features in titanium alloys based on stereology. Rare Metal Mat Eng 2009;38:398-403.



[36] Spanrad S. Fatigue crack growth in laser shock peened aerofoils subjected to foreign object damage.

PhD thesis, University of Portsmouth; 2011.

[37] Altenberger I, Nalla RK, Sano Y, Wagner L, Ritchie RO. On the effect of deep-rolling and laser-peening on the stress-controlled low- and high-cycle fatigue behavior of Ti-6Al-4V at elevated temperatures up to 550 °C. *Int J Fatigue* 2012; 44:292-302.

[38] Vinogradov A, Kawaguchi T, Kaneko Y, Hashimoto S. Fatigue crack growth and related microstructure evolution in ultrafine grain copper processed by ECAP. *Mater Trans* 2012;53:101-8.

[39] Janeček M, Nový F, Stráský J, Harcuba P, Wagner L. Fatigue endurance of Ti-6Al-4V alloy with electro-eroded surface for improved bone in-growth. *J Mech Behav Biomed* 2011;4:417-22.

[40] Mughrabi H, Höppel HW. Cyclic deformation and fatigue properties of very fine-grained metals and alloys. *Int J Fatigue* 2010;32:1413-27.

[41] Sen I, Gopinath K, Datta R, Ramamurty U. Fatigue in Ti-6Al-4V-B alloys. *Acta Mater* 2010;58:6799-809.

Table and figure captions

Table 1. Database of bimodal microstructure parameters and HCF data of Ti-6Al-4V alloys

Table 2. Database of equiaxed microstructure parameters and HCF data of Ti-6Al-4V alloys

Table 3. Database of lamellar microstructure parameters and HCF data of Ti-6Al-4V alloys

Fig. 1. Three typical microstructures: (a) bimodal [10], (b) equiaxed [24], (c) lamellar [12]

Fig. 2. HCF properties of Ti-6Al-4V alloy with three typical microstructures.

Fig. 3. HCF strength of Ti-6Al-4V alloys with bimodal microstructure at different  $\alpha_p$  volume fractions: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

Fig. 4. HCF strength of Ti-6Al-4V alloy with bimodal microstructure at different  $\alpha_p$  size: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

Fig. 5. HCF strength of Ti-6Al-4V alloy with equiaxed microstructure at different  $\alpha$  grain size: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

Fig. 6. HCF strength of Ti-6Al-4V alloy with lamellar microstructure at different  $\alpha$  lamellar width: (a)  $10^5$  cycles, (b)  $10^6$  cycles and (c)  $10^7$  cycles.

Table 1. Database of bimodal microstructure parameters and HCF data of Ti-6Al-4V alloys

No.	Ref.	Bimodal/ $\mu\text{m}$		Frequency/Hz	Stress ratio (R)	HCF strength/MPa			
		$V_\alpha$	$D_\alpha$			$10^5$	$10^6$	$10^7$	
1	Bellows et al. [25]	60	13*	60	-1	450	400	390	
					0.1	667	611	556	
					0.5	860	800	640	
					0.8	950	920	900	
2	Hines and Lütjering [12]	35	7.5*	90	-1	545	470	445	
					0.1	-	-	467	
3	Ivanova et al. [15]	60.5	8	30	0.1	-	-	467	
		24.8	8.5			830	620	550	
						( $3 \times 10^4$ )	( $2 \times 10^6$ )		
4	Nalla et al. [13]	64	20	25	0.1	700	600	540#	
					0.5	850	780	640#	
5	Peters and Lütjering [17]	60	20	90	-1	480	400	375	
6	Zuo et al. [10]	55	10	20000	-1	-	546	518	
7	Oguma and Nakamura [20]	-	4	120	0.1	900	865	850	
			10			860	810	650	
8	Nagai et al. [26]	-	4	20	0.01	800	720	640	
			4†			800	720	690	
			2.8			800	740	720	
9	Broichhausen and Kann [27]	-	-	-	-1	588	547	539	
10	Peters et al. [21]	-	6	80	-1	710	675	675	
11	Hines et al. [28]	-	9.7*	90	-1	470	400	380	
					0.1	700	550	500	
					0.5	-	-	650	
12	Ivanova et al. [18]	60.5	8	30	-1	462	441	414	
		24.8	8.5			455	421	407	
		28.7	5.5			510	497	490	
		60.5	8			0.1	720	582	491
		24.8	8.5			720	613	551	
		28.7	5.5	798	751	720			

13	Rudinger and Fischer [29]	20†	-	130	0	725	700	680
			-			-	775	580
		50	-			700	590	480
14	Adachi et al. [19]	40†	10	90	-1	-	-	550
					0.2	-	-	700
					-1	-	-	540
					0.2	-	-	600
			6		-1	-	790	770
					0.2	1125	1075	1050
					-1	740	730	730
					0.2	1100	875	800
15	Nalla et al. [30]	64	20	5	-1	450		
16	Nakanura et al. [31]	-	4	120	-1	660	660	660
		-			-0.5	827	827	827
		-			0.1	911	878	844
17	Zuo et al. [32]	55	10	25	-1	570	530	-

\*Measured by the authors.

#Frequency is 1000 Hz.

†Fatigue specimens with different textures.

Table 2. Database of equiaxed microstructure parameters and HCF data of Ti-6Al-4V alloys

No.	Ref.	$\alpha$ grain size/ $\mu\text{m}$	Frequency/Hz	Stress ratio (R)	HCF strength/MPa		
					$10^5$	$10^6$	$10^7$
1	Hines and Lütjering [12]	2.5*	90	-1	550	505	485
2	Nalla et al. [13]	1.5*	25	0.1	710	610	570
				0.5	860	800	740
3	Zuo et al. [10]	1.5*	20000	-1		533	492
4	Ivanova et al. [18]	0.92	30	-1	510	490	483
				0.1	782	736	704
5	Rudinger and Fischer [29]	-	130	0	700	660	600
					660	620	620
					690	660	660
6	Adachi et al. [19]	0.5	90	-1	740	690	680
				0.2	-	1050	1000
7	Niinomi et al. [14]	1.5*	10	0.1	750	660	600


\*Measured by the authors.

Table 3. Database of lamellar microstructure parameters and HCF data of Ti-6Al-4V alloys


No.	Ref.	Lamellar width/ $\mu\text{m}$	Frequency/Hz	Stress ratio/R	HCF strength/MPa			
					$10^5$	$10^6$	$10^7$	
1	Peters et al. [23]	1.5 $\dagger$	80	-1	650	630	620	
					750	730	720	
					700	690	690	
					660	630	625	
					620	590	590	
2	Morrissey et al. [24]	5.7*	70	0.1	-	-	722	
					400	-	-	778
			70	0.5	-	-	800	
					400	-	-	880
					1800	-	-	1040
			70	0.8	-	-	1000	
					400	-	-	1000
3	Ivanova et al. [15]	6.8	30	0.1	830 ( $3.5 \times 10^5$ )	-	467	
					8.5	830 ( $2.4 \times 10^5$ )	620 ( $3 \times 10^6$ )	451
4	Peters et al. [21]	2	80	-1	650	625	620	
					12	530	500	500
5	Ivanova et al. [18]	6.8	30	-1	483	435	400	
					8.5	421	393	366
		6.8			0.1	689	536	444
						8.5	673	551

\*Measured by the authors.

 $\dagger$ Fatigue specimens with different textures.

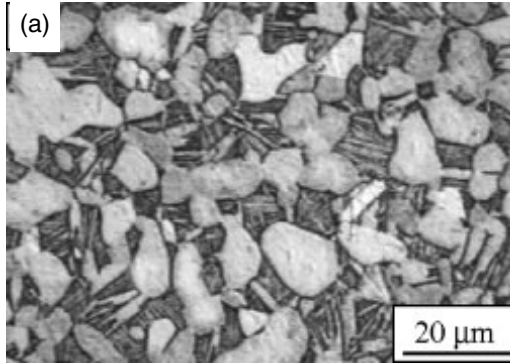

(a) bimodal [10]

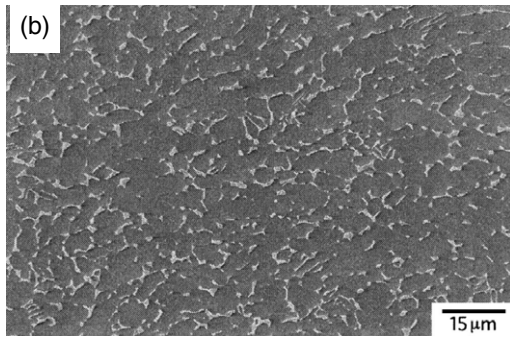

(b) equiaxed [24]



(c) lamellar [12]

Fig. 1. Three typical microstructures.

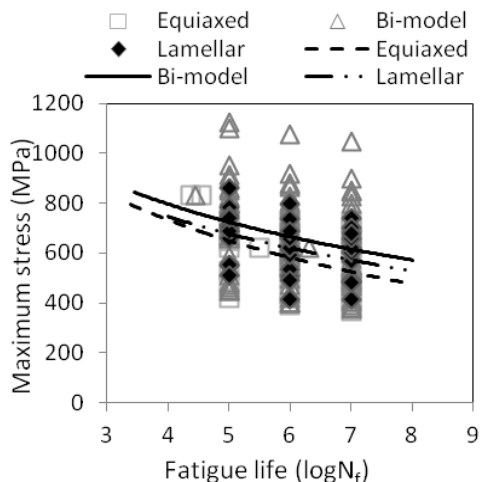


Fig. 2. HCF properties of Ti-6Al-4V alloy with three typical microstructures.

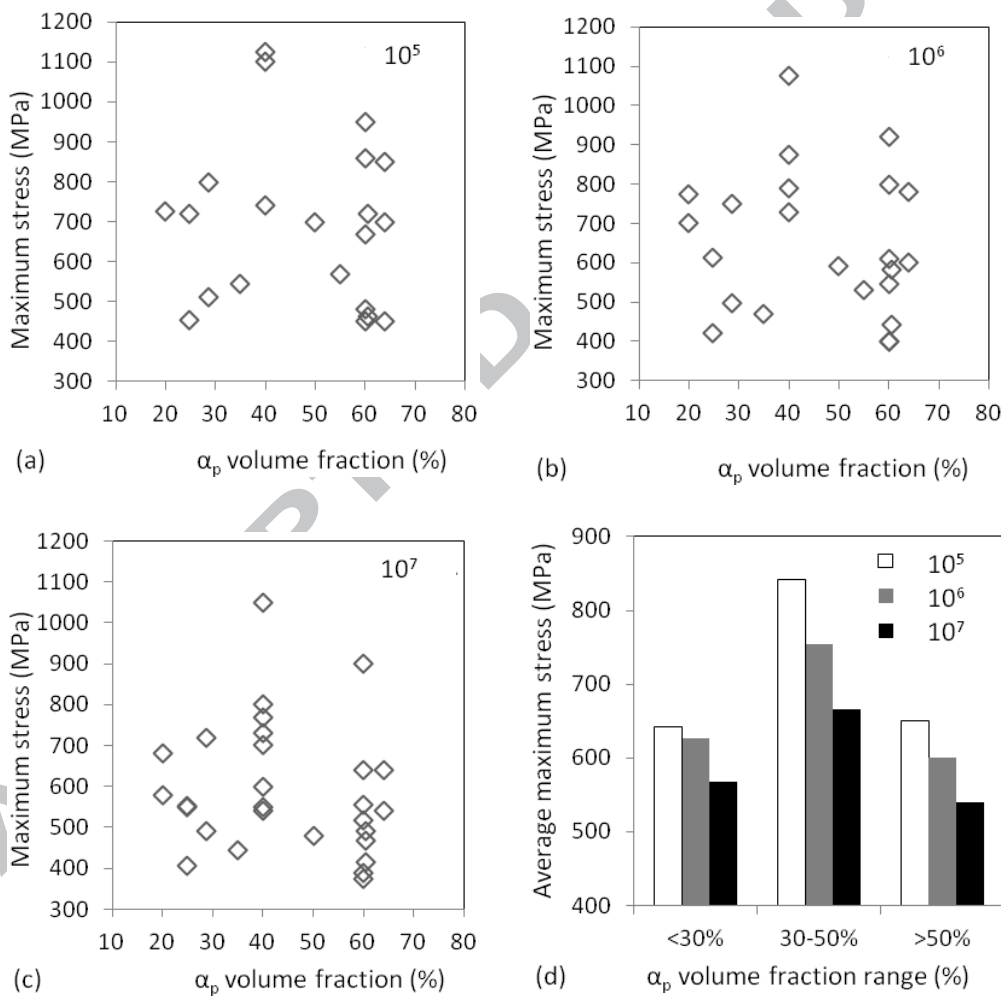


Fig. 3. HCF strength of Ti-6Al-4V alloys with bimodal microstructure at different  $\alpha_p$  volume fractions: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.



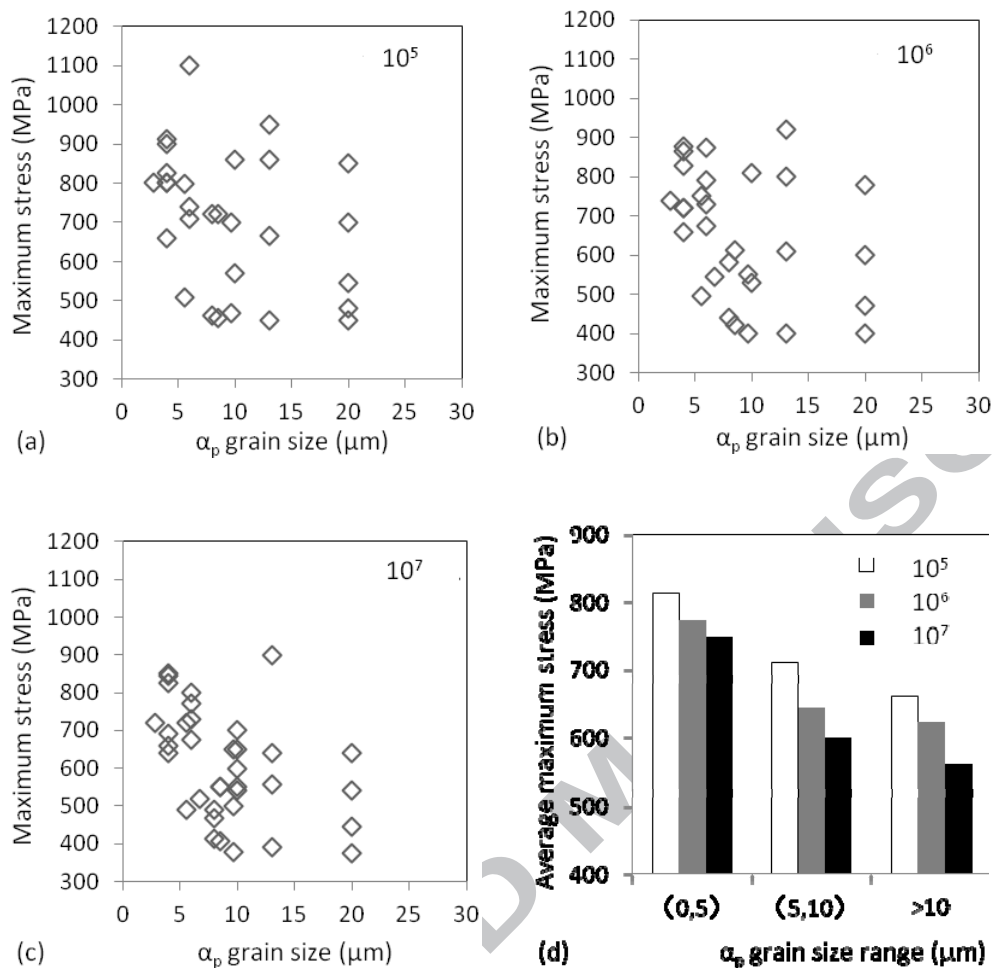


Fig. 4. HCF strength of Ti-6Al-4V alloy with bimodal microstructure at different  $\alpha_p$  size: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

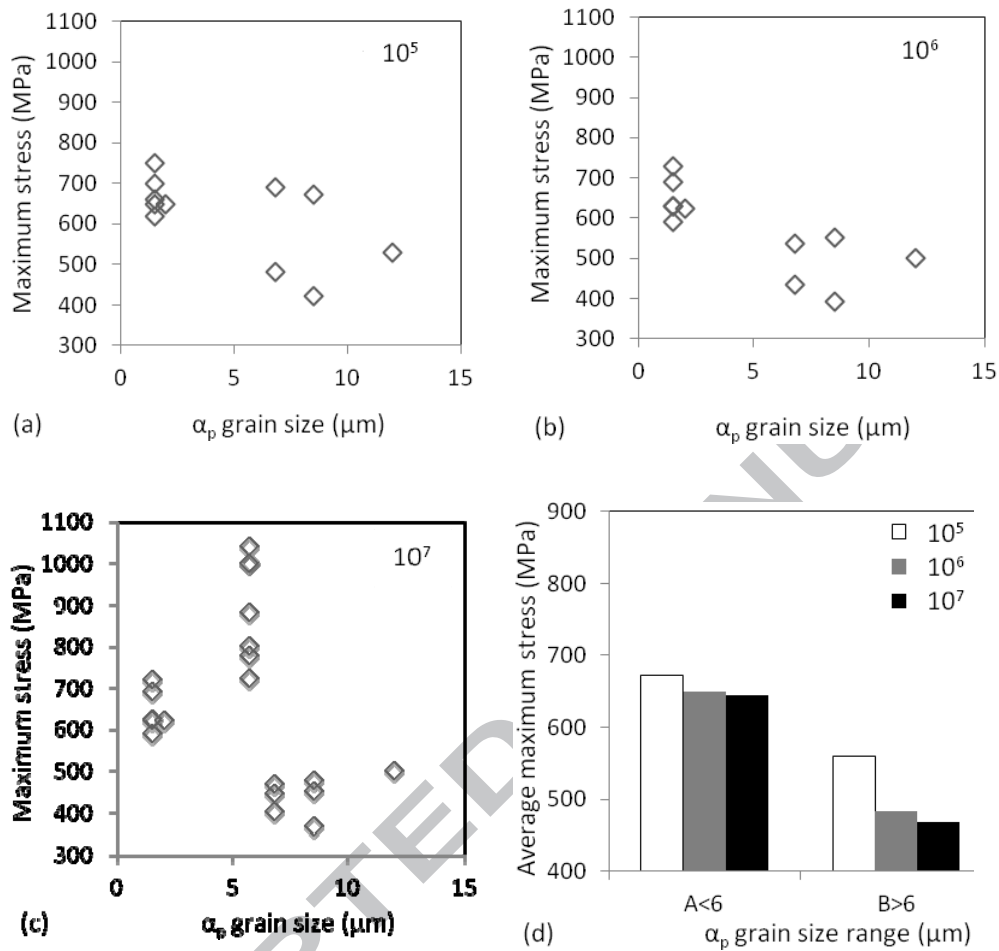


Fig. 5. HCF strength of Ti-6Al-4V alloy with equiaxed microstructure at different  $\alpha$  grain size: (a)  $10^5$  cycles, (b)  $10^6$  cycles, (c)  $10^7$  cycles and (d) analysis in groups.

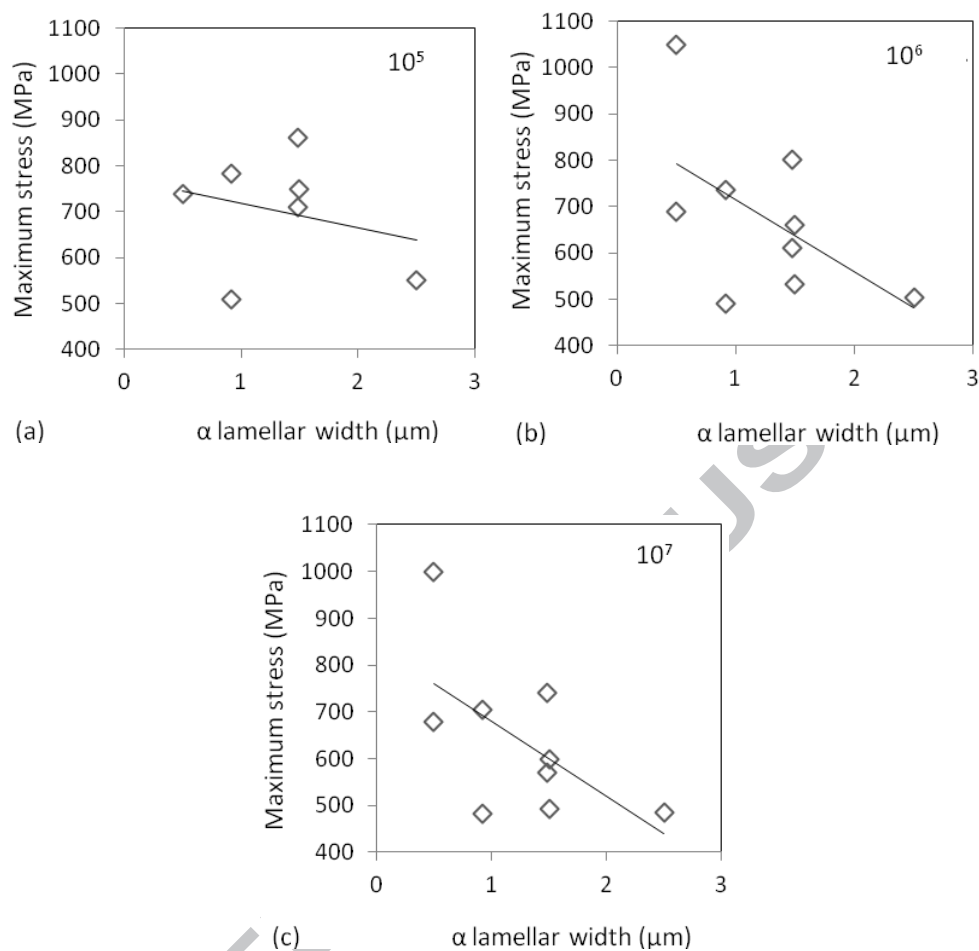


Fig. 6. HCF strength of Ti-6Al-4V alloy with lamellar microstructure at different  $\alpha$  lamellar width: (a)  $10^5$  cycles, (b)  $10^6$  cycles and (c)  $10^7$  cycles.

## Highlights

- The effects of microstructure on fatigue properties were studied
- Fatigue strength decreases in the order of bimodal, lamellar, and equiaxed microstructure
- A method of choosing microstructure for fatigue property was established
- Fatigue properties are functions of microstructural parameters

ACCEPTED MANUSCRIPT