



**QUEEN'S  
UNIVERSITY  
BELFAST**

## **The Role of Water Content and Paste Proportion on Physico-mechanical Properties of Alkali Activated Fly Ash–Ggbs Concrete**

Vinai, R., Rafeet, A., Soutsos, M., & Sha, W. (2016). The Role of Water Content and Paste Proportion on Physico-mechanical Properties of Alkali Activated Fly Ash–Ggbs Concrete. *Journal of Sustainable Metallurgy*, 2(1), 51-61. <https://doi.org/10.1007/s40831-015-0032-6>

### **Published in:**

Journal of Sustainable Metallurgy

### **Document Version:**

Peer reviewed version

### **Queen's University Belfast - Research Portal:**

[Link to publication record in Queen's University Belfast Research Portal](#)

### **Publisher rights**

© 2015 Springer

The final publication is available at Springer via <http://link.springer.com/article/10.1007%2Fs40831-015-0032-6>

### **General rights**

Copyright for the publications made accessible via the Queen's University Belfast Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

### **Take down policy**

The Research Portal is Queen's institutional repository that provides access to Queen's research output. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact [openaccess@qub.ac.uk](mailto:openaccess@qub.ac.uk).

### **Open Access**

This research has been made openly available by Queen's academics and its Open Research team. We would love to hear how access to this research benefits you. – Share your feedback with us: <http://go.qub.ac.uk/oa-feedback>

# The role of water content and paste proportion on physico-mechanical properties of alkali activated fly ash-ggbs concrete

Raffaele Vinai\*, Ali Rafeet, Marios Soutsos, Wei Sha

School of Planning, Architecture and Civil Engineering, Queen's University Belfast, BT9 5AG United Kingdom

\*corresponding author: [r.vinai@qub.ac.uk](mailto:r.vinai@qub.ac.uk), tel. +44 (0)28 9097 4032

## Abstract

The growth of the construction industry worldwide poses a serious concern on the sustainability of the building material production chain, mainly due to the carbon emissions related to the production of Portland cement. On the other hand, valuable materials from waste streams, particularly from the metallurgical industry, are not used at their full potential. Alkali activated concrete (AAC) has emerged in the last years as a promising alternative to traditional Portland cement based concrete for some applications. However, despite showing remarkable strength and durability potential, its utilisation is not widespread, mainly due to the lack of broadly accepted standards for the selection of suitable mix recipes fulfilling design requirements, in particular workability, setting time and strength. In this paper, a contribution towards the design development of AAC synthesized from pulverised fuel ash (60%) and ground granulated blast furnace slag (40%) activated with a solution of sodium hydroxide and sodium silicate is proposed. Results from a first batch of mixes indicated that water content influences the setting time and that paste content is a key parameter for controlling strength development and workability. The investigation indicated that, for the given raw materials and activator compositions, a minimum water to solid (w/s) ratio of 0.37 was needed for an initial setting time of about 1 hour. Further work with paste content in the range of 30% to 33% determined the relationship between workability and strength development and w/s ratio and paste content. Strengths in the range of 50 – 60 MPa were achieved.

**Keywords:** alkali activated concrete, mix design, setting time, slag valorisation, activated slag

## Acknowledgements

This research was carried out in the framework of the SUS-CON “Sustainable, Innovative and Energy-Efficient Concrete, based on the Integration of All-Waste Materials” project, which has received funding from the European Union Seventh Framework Programme (FP7/2007-2013) under Grant Agreement No. 285463 (Call FP7-2011-NMP ENV-ENERGY-ICT-EeB).

## 1. Introduction

The worldwide annual production of cement is estimated to be about 4 billion tonnes [1], whereas the building sector is estimated to consume more than 40% of global energy [2]. The construction industry represents about 8.8% of Gross Domestic Product, 29% of industrial employment and had a turnover of 92.5 billion euros in 2013 in EU28 [3], and therefore it could offer the possibility of absorbing high volume of waste and by-products, in particular slags produced by metallurgical industry, if reliable and efficient recycling strategies for their use as construction materials are available. This would allow not only the reutilisation of slags (and the consequent benefit in terms of environmental impact of the whole value chain) but also the avoidance of the emissions related to the production of Portland cement (PC), which are estimated to represent about 8% of the worldwide carbon emissions [4]. Ground granulated blast furnace slag (ggbs) is a by-product from the production of iron which has enormous potential for being used as a binder in concrete. Although already used with Portland cement (PC) in traditional concrete, its utilisation for the development of PC-free concrete by alkali activation of aluminosilicate precursors is gaining attention [5]. The chemistry on which the reaction of these materials is based differs significantly from that of PC, and no broadly accepted methodology for the development of mix design guidelines that allow the control of fresh and hardened properties is available in the technical literature.

Literature on alkali activated materials (AAM) is vast and comprehensive reviews have been compiled and made available in recent years. An up-to-date picture of the research development, achieved milestones and perspectives for the future of the alkali activated materials is presented in [6]. Alkali activated concrete is currently commercialised in USA, Australia, India, UK and the Netherlands, and patents [7, 8] have been issued on alkali activated concrete (often also referred to as ‘geopolymer concrete’). Studies focused on fly ash concrete [9-13] indicated that the parameters influencing the properties of fly-ash based concrete are mainly dosages of activators, water-to-solid ratio (w/s), curing temperature (in the range of 60 to 100 °C) and its duration, along with physical properties of precursor material. Reinforced concrete structural elements such as beams and columns were reported to have elastic and strength properties similar to those of PC concretes [14, 15]. Slag based AACs were also compared with PC based concrete [16, 17], showing that, at similar binder content and water/binder ratio, the compressive strength for alkali activated slag concrete (AASC) cured at ambient temperature (20 °C) was higher at both 28 and 90 days than that of Portland cement [17]. The quick setting of slag-rich mixes has been highlighted in the literature without pointing out solutions to tackle this issue. Examples can be found in the available literature on fly ash blended with slag to produce AAC [18-22].

1 While compressive strength was found to increase with the increase in slag content, a decrease of the  
2 workability, attributed to the accelerated reaction of the calcium and the angular shape of slag particles, was  
3 observed. Setting time was also reported to decrease as the amount of slag increased. Maximum slag proportion  
4 (as partial replacement of pfa) suggested from the literature was 15% – 20% [19], with some authors proposing  
5 up to 30% [22]. Technical issues such as setting time and workability were highlighted in alkali activated slag  
6 and fly ash/slag systems.  
7

8 In this study, a blend of 60% pulverised fuel ash (pfa) and 40% ground granulated blast furnace slag (ggbs) was  
9 used for concrete production. The objective of this study was to analyse the effects of binder content, paste  
10 content and water to solid ratio on fresh and hardened properties of the concrete.  
11

## 12 **2. Materials and methods**

13 Pulverised fuel ash (pfa) was supplied by Power Minerals Ltd., Drax Power Station, North Yorkshire, UK. X-  
14 ray diffraction was carried out using pure copper-K-Alpha 1 radiation with wavelength 1.54 Å. The X-ray  
15 generator was set to 40 kV and 40 mA, the recorded angular range was 5 to 70° (2θ) with a step close to 0.017°.  
16

17 A quantitative estimation of the amorphous and crystalline fractions was carried out by applying the Rietveld  
18 method, adding and blending 20% in weight of corundum (Al<sub>2</sub>O<sub>3</sub>) as internal standard. The amorphous content  
19 was 86%, whereas quartz (4.6%), mullite (8.1%), hematite (0.5%) and magnetite (0.8%) were the main  
20 crystalline phases detected. Ground-granulated blast-furnace slag (ggbs) was supplied by Civil and Marine Ltd –  
21 Hanson Company and member of the HeidelbergCement Group, West Thurrock, Essex, UK. Akermanite and  
22 gehlenite in crystalline state were detected by X-ray diffraction, whereas the amorphous content was > 95%.

23 X-ray fluorescence (XRF) analysis was carried out on a fuse bead sample, which is a technique for removing  
24 both grain size and mineralogical effects. The procedure consists of heating the sample in the presence of air at  
25 high temperature (1000°C-1200°C) in a platinum crucible with lithium borates. This process converts metals  
26 and salts to oxides. Results are therefore shown in terms of oxides in their final form. For example, iron oxides  
27 detected by XRF are reported as Fe<sub>2</sub>O<sub>3</sub>, whereas crystalline phases identified with XRD in pfa were Fe<sub>2</sub>O<sub>3</sub> as  
28 well as Fe<sub>3</sub>O<sub>4</sub>. Main oxide compositions of the raw materials are shown in Table 1, whereas Table 2 shows their  
29 physical properties.  
30

31 Commercial chemicals were used for activating the raw materials, namely solid NaOH of commercial grade  
32 (99% purity) and sodium silicate solution with SiO<sub>2</sub>:Na<sub>2</sub>O molar ratio = 2.055. Mass composition of the  
33 commercial sodium silicate solution, provided by Fisher Scientific, was Na<sub>2</sub>O 12.8%, SiO<sub>2</sub> 25.5%, water 61.7%,  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

in weight. NaOH solution was prepared by dissolving solid NaOH in tap water. Molar concentration was 10M, corresponding to 30% in wt.% (300 g of NaOH dissolved in 700g of tap water). The dosage of the activators in the mix was described by the alkali dosage (M+) and the alkali modulus (AM). M+ is defined as the mass ratio of total sodium oxide (Na<sub>2</sub>O) in the activating solution (i.e. Na<sub>2</sub>O from sodium hydroxide solution + Na<sub>2</sub>O from sodium silicate solution) to the binder (dry mass of pfa + ggbs):

$$M+ = \frac{Na_2O}{pfa+ggbs} (mass) \quad (1)$$

Alkali modulus (AM) is the mass ratio of sodium oxide to silica in the activating solution:

$$AM = \frac{Na_2O}{SiO_2} (mass) \quad (2)$$

In the literature, silica modulus is often used, i.e. the ratio SiO<sub>2</sub>/Na<sub>2</sub>O, which corresponds to 1/AM. Either mass ratio or molar ratio can be used. The mass ratio approach was followed in this research, as it was more convenient for calculating the quantities of chemicals in the mix.

A previous study on the effect of chemical dosages on the reaction development for low Ca system (100% pfa) and high Ca system (30% pfa and 70% ggbs) indicated that strength increases with the increase of the AM, then it decreases until a residual value, presumably due to the reduced amount of available silica that needs to be involved in the 'reorganisation-gelation-polymerisation' steps of the geopolymer formation. The optimum value of AM was found in the range 0.95 – 1.25. The effect of the M+ increase was also associated with an increase in the compressive strength, but the incremental gain narrowed when M+ was higher than 9.5% for pure pfa system and higher than 7.5% for high ggbs content systems. Higher dosages were found to be detrimental also for the triggering of fast setting behaviour. In order to ensure proper strength development, initial setting time and also considering that high dosages imply high production costs, alkali dosages were fixed at M+ = 7.5% and AM = 1.25. Some details can be found in [23].

The water/solids ratio is defined as the ratio between total mass of water (i.e. tap water + water in the alkali solutions) and the total solid mass (i.e. mass of binder + mass of alkali solids). Crushed basalt of two sizes (4/10 mm and 10/20 mm) and Lough sand (0/4 mm) were used as aggregate in the following proportions (in volume): 40% sand over total aggregate, ratio between coarse aggregate sizes equal to 40%/60% for 4/10 mm and 10/20 mm. The grain size distribution of the aggregate mix is shown in figure 1. Aggregates were first oven-dried at 105°C overnight for avoiding the inclusion of unknown water mass in the system. Subsequently, they were wetted with a mass of water calculated according to their 1-hour absorption rate (Table 3), bringing them to saturated-surface-dry condition. The aim of this operation was to avoid aggregate to absorb water that should be available for the lubrication and for the chemical reaction of the system. The water used for the saturation of the

1 aggregate was not considered in the overall water/solid ratio. Bulk density of the aggregate mix has been  
2 measured with a 7 l container in a loose and vibrated state. Void contents in the two states were calculated  
3 accordingly and results are shown in Table 4.  
4

5 The composition of the concrete, in terms of volumes of its constituents, is shown in figure 2. Binder content is  
6 defined as the mass of solid precursors (pfa + ggbs) per cubic metre of concrete. Paste volume is defined as the  
7 volume of the solid precursor + activating solutions + added water, per cubic metre of concrete. Paste content is  
8 defined as the percentage of paste volume over the total concrete volume.  
9

10 Mixes were prepared according to the mix proportion reported in Table 5. 100 mm cube concrete samples were  
11 cast for compressive strength measurement. Samples were cured in plastic boxes (>90% relative humidity) and  
12 kept at 20 °C throughout the curing period. Curing temperature was ensured by the setting of the curing room,  
13 whereas relative humidity in plastic boxes was checked regularly through a portable digital humidity reader  
14 positioned inside one of the boxes. Three cubes were tested in compression at each designated time (1, 7 and 28  
15 days). Average strength and standard deviation were calculated. A 2000 kN capacity compression testing  
16 machine (Samuel Denison Ltd.) was used for all testing with a loading rate of 3.33 kN/s, within the range  
17 specified in BS 1881-116:1983 [24]. Measurement of the initial and final setting time was carried out on  
18 mortars. The method described in BS EN 196-3 involving the use of the Vicat apparatus on paste was not  
19 suitable, since the water content necessary for achieving the required paste consistency was too low resulting in  
20 short setting times. This method was also not applicable for mortars since sand grains may interfere with the  
21 penetration depth of the needle. The procedure described in the American Society for Testing and Materials  
22 (ASTM) standard C403M – 08 - Standard Test Method for Time of Setting of Concrete Mixtures by Penetration  
23 Resistance [25] was considered more suitable for the assessment of the setting time of mortars. A manual  
24 penetrometer, consisting of a spring loaded device graduated from 1 to 100 dekanewton (daN), coupled with  
25 needles of different print areas (650 to 16 mm<sup>2</sup>), was used. The initial setting time is conventionally read from  
26 the experimental curves when a pressure of 3.45 MPa is reached, whereas the final setting time is read when a  
27 pressure of 27.6 MPa is required for the needle penetration.  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52

### 53 **3. Results and discussion**

#### 54 *3.1. Phase 1 – effect of binder content and w/s ratio on strength and workability*

55 In phase 1, a preliminary analysis of the effects of binder content and w/s ratio on workability and strength  
56 development was carried out, varying the binder content in the range 350 – 514 kg/m<sup>3</sup> and the w/s ratio in the  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 range 0.30 – 0.45. A spreadsheet was developed for the calculation of the quantities for cubic metre of activating  
2 solutions, added water and aggregate for each combination of binder content (i.e. mass of solid precursor pfa +  
3 ggbs) and w/s ratio. The aim was the understanding of the main trends and the assessment of preliminary  
4 reference values for fresh and hardened properties. Ten mixes (labelled C1 to C10, Table 5 and 6) were cast for  
5 phase 1. Table 6 summarises the mix parameters. Some mixes were unsuccessful: C2 set in the mixer; C5 was  
6 too dry and only 6 cubes were cast; C9 was too dry and no cubes were cast. Measured compressive strength and  
7 slump fall are shown in figures 3 and 4 respectively.  
8  
9

10 The following observations can be made from the results:  
11  
12

- 13 - As expected, the higher the binder content, the higher the compressive strength at 28 days. The only  
14 exception was the mix with the highest binder content (514 kg/m<sup>3</sup>), which had a lower strength at all the  
15 three testing ages compared to the ones with binder contents of 400 and 450 kg/m<sup>3</sup>. A possible explanation  
16 could be the high paste proportion (higher than 43%) which might have led to segregation of the aggregate.  
17 The final strength may therefore have been affected by an uneven aggregate distribution in the matrix. This  
18 phenomenon is related mainly to the viscosity of the paste, the grading of the aggregate (in particular the  
19 amount of fine fraction) and the vibration procedure. Higher relative volume of fine aggregate, higher  
20 viscosity of paste and shorter vibration time could result in a reduction of the segregation effects on  
21 samples with high paste volume.  
22  
23
- 24 - Binder content of 450 kg/m<sup>3</sup> led to the highest strength (around 72 MPa after 28 days). An increase in the  
25 w/s ratio from 0.34 to 0.37 seemed to result in a decrease in strength at 28 days, although such decrease  
26 was very small. The same trend was observed for the 400 kg/m<sup>3</sup> binder content.  
27  
28
- 29 - Slump fall was higher than 190 mm when binder content was higher than 350 kg/m<sup>3</sup>, even for w/s ratio as  
30 low as 0.34. For low binder content (350 kg/m<sup>3</sup>) slump values lower than 50 mm were recorded for w/s  
31 ratios up to 0.40.  
32  
33
- 34 - Mixes with low w/s ratios set very quickly. When a w/s = 0.30 was used (mix C2), casting was not  
35 possible as the mix set in the mixer bowl. It can be concluded that the reduction of w/s ratio is not always  
36 an option for controlling the workability of the mixes, as it can result in short setting times.  
37  
38
- 39 - Some of the mixes were too dry for proper casting (C5, C9) of cubes. In the case of C5, a paste volume of  
40 29.4% resulted in a mix that was difficult to cast and only 6 cubes were successfully compacted/cast. The  
41 w/s ratio of 0.37 did not present any problems with other mixes of higher paste volume. C9 proved very  
42 difficult to compact and no cubes were cast. This is believed to have been due to the combined effect of  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

paste content and relatively low w/s ratio. The w/s ratio of 0.34 might have been low for this mix but it was satisfactory for mixes with higher paste contents, e.g. 36.4% for mix C8.

- Increasing the binder content from 350 to 450 kg/m<sup>3</sup> resulted in a strength increase of about 14 MPa. However, the strength of 60 MPa was also achievable with lower binder contents.
- w/s ratio effect on strength was moderate (reduction of about 2 MPa) for values as low as 0.40. For higher w/s ratios the strength decrease was more pronounced.
- When plotting the workability and strength data versus the paste proportion, it is possible to define a range of paste volume (30% – 33%) in which compressive strength is close to the highest possible whilst having a desired workability (see figure 5).

### 3.2. *Effect of w/s ratio on initial setting time*

Following the experiments described above, an investigation on the effect of w/s ratio on setting time was carried out. Five mortars were prepared with the same binder blend (60/40 pfa/ggbs) and the same activator dosages (M+ 7.5%, AM 1.25) of the investigated concrete, keeping a fixed sand content of 1375 kg/m<sup>3</sup> which resulted in a paste content of 48.9%. The w/s ratio was varied in the range 0.33 – 0.42. Mortar samples were tested according to the method described in section 2. Results are shown in figure 6. It can be seen that the initial setting time is noticeably affected by the w/s ratio of the mortar: the higher the w/s ratio, the longer the initial setting time. Figure 7 summarises the results and shows the relationship between initial setting time and w/s ratio. This diagram was plotted using data in figure 6, specifically the times corresponding to the initial setting time pressure. It can therefore be concluded that a w/s ratio above a certain minimum is necessary for ensuring the initial setting time required for the specific application (e.g. 0.37 for setting time of about 60 min).

### 3.3. *Phase 2 – effect of paste volume proportion and w/s ratio on strength and workability*

Following the results described above, in order to improve our understanding of factors affecting fresh and hardened properties of AAC, a further 11 mixes of 60/40 pfa/ggbs blend were investigated, focusing on paste proportion in the range of 30% to 33%. Details of the mixes for this second phase are shown in Table 5 and 7. The w/s ratio 0.33 (C11) proved not to be sufficient for the preparation of concrete with 33% paste proportion, since the mix set in the drum before cubes could be cast. This therefore confirmed that low w/s ratios lead to fast setting. Compressive strength results are shown in figure 8.

The following observations can be made from the results:



- The maximum strength obtained was about 60 MPa for a paste proportion of 33% (C12, C14). It was observed that at the w/s ratio of 0.39 (C13, C17, C19) the reduction in paste volume did not result in a significant strength reduction.
- w/s ratio effect on strength was moderate for values as high as 0.41, and then the strength reduction was more pronounced.
- Slump fall with the investigated paste proportions was better controlled than during phase 1. Workability of produced concrete varied from very stiff (class S1) to very fluid (class S5) by changing w/s ratio and paste proportion (see figure 9).

### 3.4. Discussion

The study aimed at understanding the effects of paste proportion and w/s ratio on workability, setting time, and strength development for a 60%/40% pfa/ggbs based alkali activated concrete. It is known that also aggregate composition, inclusion of admixtures, and activator dosages can have an influence on the physico-chemical properties of alkali activated concrete, but these effects were out of the scope of this paper. The influence of paste proportion on workability was confirmed in the two phases of the study: paste proportion higher than 33% led to slump values greater than 200 mm. The paste plays a role of a lubricant that depends on its viscosity and on the setting time: the more viscous the paste and the fastest the reaction, the smaller the slump. This result is confirmed by findings from literature: in [17], a binder content of 400 kg/m<sup>3</sup> led to slump greater than 180 mm, whereas in [26] a correlation was found between the slump and the paste/aggregate ratio for 100% slag alkali activated concrete with binder content higher than 450 kg/m<sup>3</sup>. Compressive strength was also found to be influenced by the paste proportion, but the strength increment narrowed for binder content higher than 400 kg/m<sup>3</sup>. This observation can also be found in [17].

Ggbs inclusion in the system allows the hardening of the concrete at room temperature (i.e. no need for thermal curing), but it can lead to fast setting, as reported also in [19]. W/s ratio was found to influence the setting time of the system: a direct relationship was found between the initial setting time and the w/s ratio. This delay of the reaction with the increase in w/s ratio was previously reported in ggbs activated with sodium silicate solution and was ascribed to the dilution effect of the activators [27]. W/s ratio also affects the strength development, but the behaviour of a pfa/ggbs blend differs from results on 100% pfa, where the reduction in strength with the increase in water content was found to be linear [9]. The presence of ggbs reduced the negative effects of water content increase, as reported also in [26]. The increase of the workability with higher w/s ratio was also

1 observed, and it is presumably due to the lubricant effect of the water in the system, which affects the viscosity  
2 of the paste.

3  
4 Visual inspection on crushed samples indicated that the bond between aggregates and binder matrix was  
5 stronger for 28-day specimens compared to 1-day and 7-day specimens: coarse particles were not easily  
6 detached from the matrix, fracture surfaces sometimes went through the aggregate and the failure was the  
7 typical double pyramid. 1 day and 7 days samples did not show these failure patterns. There are suggestions [17]  
8 that the denser (compared to PC concrete) structure of the transition zone in AAC could be due to reduction of  
9 the porosity by the condensation of the excess SiO<sub>2</sub> supplied by the activator, and to a potential reaction of the  
10 surfaces of siliceous aggregates with the alkali solution, forming additional reaction products around the  
11 aggregate particles for improved bond resulting in increased strengths.

12  
13 A reduction in the paste content implies the reduction of binder and consequently the reduction of the quantity  
14 of activators (for fixed M<sup>+</sup> and AM), because chemicals are dosed according to the binder mass. Chemical  
15 activators have been identified as being responsible for the main cost and environmental footprint of alkali  
16 activated concrete [28]. Therefore, a reduction of paste proportion has positive implications in terms of cost and  
17 carbon footprint of the alkali activated concrete. For the investigated binder blend, aggregate proportion and  
18 activator dosages, the paste proportion of 30 vol. % can be considered sufficient for allowing a satisfactory  
19 development of compressive strength, with a variation of w/s ratio within the range 0.37 – 0.41, where 0.37 was  
20 considered the minimum (in order to avoid fast initial setting) and 0.41 the maximum (in order to avoid high  
21 loss of strength). Other blends might require different ranges. Increasing the paste proportion may be necessary  
22 for achieving higher workability (slump > 100 mm) without compromising the compressive strength.

#### 42 **4. Conclusions**

43  
44 In this study, mixes of 60% pfa and 40% ggbs were investigated for determining the effects of binder content,  
45 paste content and water-to-solid ratio on fresh and hardened properties of concrete. The investigation was  
46 carried out in two phases. In phase 1 a preliminary analysis of the effect of binder content on workability and  
47 strength development was carried out, with the aim of understanding the main trends and assessing preliminary  
48 desired values for fresh and hardened properties. In phase 2 the optimisation of mix proportions was  
49 investigated, with the aim of controlling the workability without major impact on strength development.

50  
51 The main conclusions from phase 1 are:

- 52  
53 (a) High binder contents (more than 400 kg/m<sup>3</sup>) made it very difficult to control the workability, although

compressive strengths up to 70 MPa can be obtained with 450 kg/m<sup>3</sup>.

- (b) w/s ratio played a role in the setting time, and the relationship between w/s and initial setting time was determined for the investigated blend.
- (c) w/s ratio does not affect significantly the strength development except for high values ( $\geq 0.40$ ).
- (d) The reduction of paste volume had a moderate effect on the strength development.

Considering these outcomes, phase 2 was focused on low paste proportions ( $\leq 33\%$ ) for determining the effect of w/s ratio both in terms of slump fall and of strength trends. It was concluded that:

- (e) The development of fresh and hardened properties is controlled by the combined effects of paste proportion and w/s ratio.
- (f) For the investigated binder composition (60/40 pfa/ggbs) a paste proportion of 30% was found to be sufficient to achieve compressive strengths of around 57 MPa, with a w/s ratio within the range of 0.37 – 0.41. The w/s ratio of 0.37 was considered to be the minimum that could be used to avoid fast initial setting of concrete. A w/s ratio higher than 0.41 would lead to significant strength reduction.
- (g) A reduction in paste proportion has positive implications on the cost and on the environmental footprint of alkali activated concrete. Increasing the paste proportion can achieve high workability (slump fall higher than 100 mm) without compromising the compressive strength.

## References

- [1] CEMBUREAU (2015) The European Cement Association, key facts & figures.  
<http://www.cembureau.eu/about-cement/key-facts-figures> Accessed 8 June 2015.
- [2] United Nations Environment Program (2009) Buildings and climate change: Summary for Decision-Makers. <http://www.unep.org/SBCI/pdfs/SBCI-BCCSummary.pdf> Accessed 11 June 2015.
- [3] European Construction Industry Federation (2014) Key Figures 2014 - activity 2013.  
<http://www.fiec.eu/en/library-619/key-figures.aspx> Accessed 11 June 2015.
- [4] Olivier JG (2012) Trends in global CO<sub>2</sub> emissions: 2012 Report. Hague: PBL Netherlands Environmental Assessment Agency.
- [5] Provis J (2014) Green concrete or red herring? – future of alkali activated materials. *Advances in Applied Ceramics*, 113(8): 472–477. doi: 10.1179/1743676114Y.0000000177
- [6] Provis J, van Deventer J (2014) Alkali Activated Materials, State-of-the-Art Report, RILEM TC 224-AAM, Springer

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [7] Van Deventer JSJ, Feng D, Duxson P (2010) Patent no. US7691198 B2.
- [8] Kakebeeke PIJ, Keulen A (2013) Patent no. WO2013176545 A1.
- [9] Joseph B, Mathew G (2012) Influence of aggregate content on the behavior of fly ash based geopolymer concrete. *Scientia Iranica A*, 19(5): 1188–1194. doi: 10.1016/j.scient.2012.07.006
- [10] Olivia M, Nikraz HR (2011) Strength and water penetrability of fly ash geopolymer concrete. *Journal of Engineering and Applied Sciences*, 6(7): 70–78.
- [11] Sofi M, van Deventer JSJ, Mendis PA, Lukey GC (2007) Engineering properties of inorganic polymer concretes (IPCs). *Cement and Concrete Research*, 37(2): 251–257. doi:10.1016/j.cemconres.2006.10.008
- [12] Wongpa J, Kiattikomol K, Jaturapitakkul C, Chindaprasirt P (2010) Compressive strength, modulus of elasticity, and water permeability of inorganic polymer concrete. *Materials and Design*, 31(10): 4748–4754. doi:10.1016/j.matdes.2010.05.012
- [13] Hardjito D, Wallah SE, Sumajouw DMJ, Rangan BV (2004) Factors Influencing the compressive strength of fly ash-based geopolymer concrete. *Civil Engineering Dimension*, 6(2): 88–93.
- [14] Rangan BV, Sumajouw D, Wallah S, Hardjito D (2006) Reinforced low-calcium fly ash-based geopolymer concrete beams and columns. 31<sup>st</sup> Conference on Our World in Concrete & Structures, 16-17 August 2006, Singapore
- [15] Yost JR, Radlińska A, Ernst S, Salera M (2012) Structural behavior of alkali activated fly ash concrete. Part 1: mixture design, material properties and sample fabrication. *Materials and Structures*, 46(3): 435–447. doi: 10.1617/s11527-012-9919-x
- [16] Collins F, Sanjayan J (1999) Workability and mechanical properties of alkali activated slag concrete. *Cement and Concrete Research*, 29: 455–458. doi: 10.1016/S0008-8846(98)00236-1
- [17] Bernal S, de Gutiérrez R, Pedraza A, Provis J, Rodriguez E, Delvasto S (2011) Effect of binder content on the performance of alkali-activated slag concretes. *Cement and Concrete Research*, 41: 1–8. doi: 10.1016/j.cemconres.2010.08.017
- [18] Lee N, Lee H (2013) Setting and mechanical properties of alkali-activated fly ash/slag concrete manufactured at room temperature. *Construction and Building Materials*, 47: 1201–1209. doi:10.1016/j.conbuildmat.2013.05.107
- [19] Deb PS, Nath P, Sarker PK (2014) The effects of ground granulated blast-furnace slag blending with fly ash and activator content on the workability and strength properties of geopolymer concrete cured at ambient temperature. *Materials and Design*, 62: 32–39. doi:10.1016/j.matdes.2014.05.001

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [20] Nath P, Sarker P (2014) Effect of GGBFS on setting, workability and early strength properties of fly ash geopolymer concrete cured in ambient condition. *Construction and Building Materials*, 66: 163–171. doi:10.1016/j.conbuildmat.2014.05.080
- [21] Rajamane NP, Nataraja MC, Jeyalakshmi R, Nithiyantham S (2015) Greener durable concretes through geopolymerisation of blast furnace slag. *Materials Research Express*, 2(5). doi:10.1088/2053-1591/2/5/055502.
- [22] Xin L, Jin-yu X, Weimin L, Erlei B (2014) Effect of alkali-activator types on the dynamic compressive deformation behavior of geopolymer concrete. *Materials Letters*, 124: 310–312. doi:10.1016/j.matlet.2014.03.102
- [23] Rafeet A, Vinai R, Sha W, Soutsos M (2014) Alkali activated fuel ash and slag mixes: optimization study from paste to concrete building blocks. 34<sup>th</sup> Cement and Concrete Science Conference, 14-17 September 2014, University of Sheffield (UK): 349–353.
- [24] BS 1881-116 (1983). Testing concrete. Part 116: Method for determination of compressive strength of concrete cubes.
- [25] ASTM C403 / C403M-08 (2008). Standard Test Method for Time of Setting of Concrete Mixtures by Penetration Resistance. ASTM International, West Conshohocken, PA.
- [26] Hung CC, Chang JJ (2013) The influence of mixture variables for the alkali-activated slag concrete on the properties of concrete. *Journal of Marine Science and Technology*, 21(3): 229-237. doi: 10.6119/JMST-012-0109-4.
- [27] Shi C, Day RL (1996) Some factors affecting early hydration of alkali-slag cements. *Cement and Concrete Research*, 26(3): 439–447. doi:10.1016/S0008-8846(96)85031-9
- [28] Provis JL, Palomo A, Shi C (2015) Advances in understanding alkali-activated materials. *Cement and Concrete Research*, 78 Part A: 110-125. doi:10.1016/j.cemconres.2015.04.013

## Tables

**Table 1.** Chemical components (oxides, mass percentage) as per XRF analysis

Component	pfa	ggbs
<b>Na<sub>2</sub>O</b>	0.89	1.05
<b>MgO</b>	1.33	6.94
<b>Al<sub>2</sub>O<sub>3</sub></b>	22.52	11.23
<b>SiO<sub>2</sub></b>	46.78	29.38
<b>P<sub>2</sub>O<sub>5</sub></b>	0.17	0.00
<b>SO<sub>3</sub></b>	0.90	1.76
<b>Cl</b>	0.00	0.01
<b>K<sub>2</sub>O</b>	4.09	0.93
<b>CaO</b>	2.24	43.72
<b>TiO<sub>2</sub></b>	1.05	0.67
<b>V<sub>2</sub>O<sub>5</sub></b>	0.08	0.01
<b>Cr<sub>2</sub>O<sub>3</sub></b>	0.03	0.02
<b>MnO</b>	0.05	0.51
<b>Fe<sub>2</sub>O<sub>3</sub></b>	9.15	0.36
<b>CoO</b>	0.02	0.00
<b>NiO</b>	0.02	0.00
<b>CuO</b>	0.02	0.00
<b>ZnO</b>	0.06	0.00
<b>SrO</b>	0.04	0.07
<b>BaO</b>	0.10	0.12
<b>WO<sub>3</sub></b>	0.00	0.00
<b>LOI</b>	3.57	2.40

**Table 2.** Physical properties of precursor materials

Parameter	u.o.m.	pfa	ggbs
<b>Volumetric mass density</b>	g/cm <sup>3</sup>	2.42	2.92
<b>Grain size range</b>	μm	0.24 - 88.00	0.24 - 149.00
<b>d<sub>50</sub></b>	μm	18	19
<b>Amorphous content</b>	wt. %	86	> 95

**Table 3.** Physical properties of aggregates

Material name	Particle density on an oven-dried basis [t/m <sup>3</sup> ]	1- hour water absorption [%]
<b>Sand 0/4</b>	2.69	0.92
<b>Crushed basalt 4/10</b>	2.79	1.45
<b>Crushed basalt 10/20</b>	2.75	1.24

**Table 4.** Void content of aggregate mix

<b>Packing condition</b>	<b>Bulk density (kg/m<sup>3</sup>)</b>	<b>Void content (%)</b>
Loose	1797.5	34.3
Vibrated	2125.8	22.3

**Table 5.** Mixes design, quantities in kg (for the production of 1 m<sup>3</sup> of concrete)

<b>Mix label</b>	<b>pfa</b>	<b>ggbfs</b>	<b>Sodium silicate solution</b>	<b>Sodium hydroxide solution</b>	<b>Water</b>	<b>Sand 0/4 mm</b>	<b>Crushed basalt 4/10 mm</b>	<b>Crushed basalt 10/20 mm</b>
<b>C1</b>	308	206	121	99	75	615	385	550
<b>C2</b>	300	200	118	97	30	670	430	600
<b>C3</b>	270	180	106	87	65	670	430	600
<b>C4</b>	240	160	94	77	55	720	450	660
<b>C5</b>	210	140	82	68	50	760	480	690
<b>C6</b>	210	140	82	68	60	750	470	685
<b>C7</b>	240	160	94	77	70	710	430	640
<b>C8</b>	270	180	106	87	50	690	420	630
<b>C9</b>	240	160	94	77	45	730	460	660
<b>C10</b>	210	140	83	67	80	730	460	660
<b>C11</b>	249	166	98	80	40	721	450	661
<b>C12</b>	239	159	94	77	52	721	450	661
<b>C13</b>	230	153	90	74	63	721	450	661
<b>C14</b>	227	151	89	73	66	721	450	661
<b>C15</b>	218	145	86	70	76	721	450	661
<b>C16</b>	219	146	86	70	56	742	464	681
<b>C17</b>	216	144	85	69	59	742	464	681
<b>C18</b>	213	142	84	69	62	742	464	681
<b>C19</b>	209	139	82	67	57	753	470	690
<b>C20</b>	203	136	80	65	63	753	470	690
<b>C21</b>	198	132	78	64	69	753	470	690

**Table 6.** Phase 1 mix proportions, uniaxial compressive strength (UCS), standard deviations (in bracket)

<b>Label</b>	<b>Binder cont. (kg/m<sup>3</sup>)</b>	<b>w/s ratio</b>	<b>Paste volume</b>	<b>UCS 1day (MPa)</b>	<b>UCS 7days (MPa)</b>	<b>UCS 28days (MPa)</b>	<b>Slump (mm)</b>
C1	514	0.37	43.4%	12.2 (1.1)	41.8 (1.6)	61.8 (1.7)	280
C2	500	0.30	37.9%	-	-	-	-
C3	450	0.37	37.9%	14.6 (0.4)	49.0 (2.3)	70.4 (0.1)	280
C4	400	0.37	33.4%	8.2 (0.1)	44.9 (0.7)	69.1 (1.4)	220
C5	350	0.37	29.4%	2.8 (0.3)	35.1 (1.5)	-	10
C6	350	0.40	30.4%	4.0 (0.1)	38.5 (1.0)	60.4 (0.4)	35
C7	400	0.40	34.9%	14.7 (0.5)	42.3 (1.8)	66.7 (1.1)	260
C8	450	0.34	36.4%	15.3 (1.7)	47.0 (0.8)	72.3 (1.4)	190
C9	400	0.34	32.4%	-	-	-	-
C10	350	0.45	32.4%	3.4 (0.5)	33.2 (1.0)	56.1 (1.7)	155

**Table 7.** Phase 2 mix proportions, uniaxial compressive strength (UCS), standard deviations (in bracket)

<b>Label</b>	<b>Binder cont. (kg/m<sup>3</sup>)</b>	<b>w/s ratio</b>	<b>Paste volume</b>	<b>UCS 1day (MPa)</b>	<b>UCS 7days (MPa)</b>	<b>UCS 28days (MPa)</b>	<b>Slump (mm)</b>
C11	416	0.33	33%	-	-	-	-
C12	398	0.36	33%	12.6 (0.8)	40.1 (1.2)	60.6 (2.5)	180
C13	383	0.39	33%	7.9 (0.0)	36.9 (1.0)	58.6 (0.7)	215
C14	378	0.4	33%	8.7 (0.6)	38.4 (1.2)	60.9 (0.5)	230
C15	364	0.43	33%	11.6 (0.2)	33.3 (0.4)	51.2 (1.0)	200
C16	364	0.38	31%	10.7 (1.3)	41.1 (0.3)	58.4 (0.4)	15
C17	360	0.39	31%	9.5 (0.5)	41.6 (0.1)	56.1 (2.3)	95
C18	355	0.4	31%	9.8 (0.2)	37.4 (0.9)	56.3 (2.1)	150
C19	348	0.39	30%	12.8 (0.2)	39.8 (0.5)	56.8 (2.2)	55
C20	339	0.41	30%	9.3 (0.3)	37 (0.9)	55.6 (2.0)	100
C21	331	0.43	30%	1.3 (0.2)	22.3 (0.4)	36.2 (1.3)	220



Figure 1  
Click here to download Figure: Fig1.tif

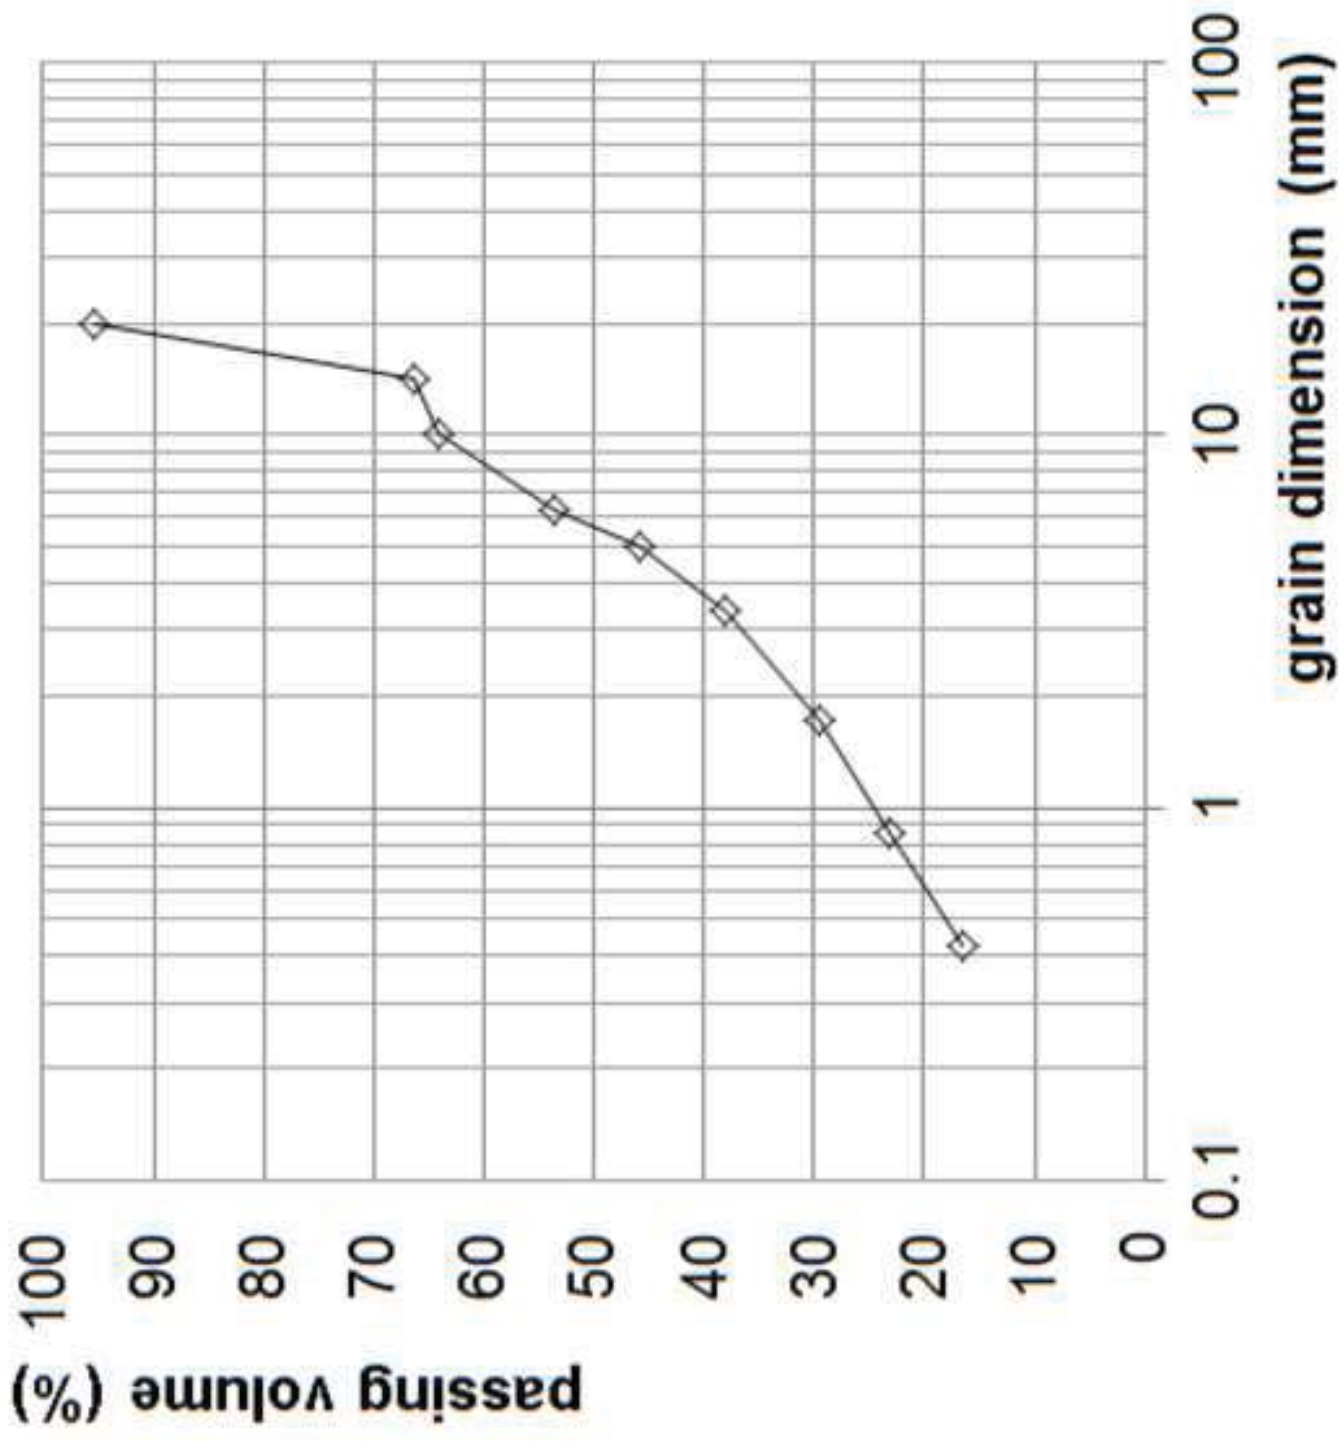


Figure 2  
Click here to download Figure: Fig2.tif

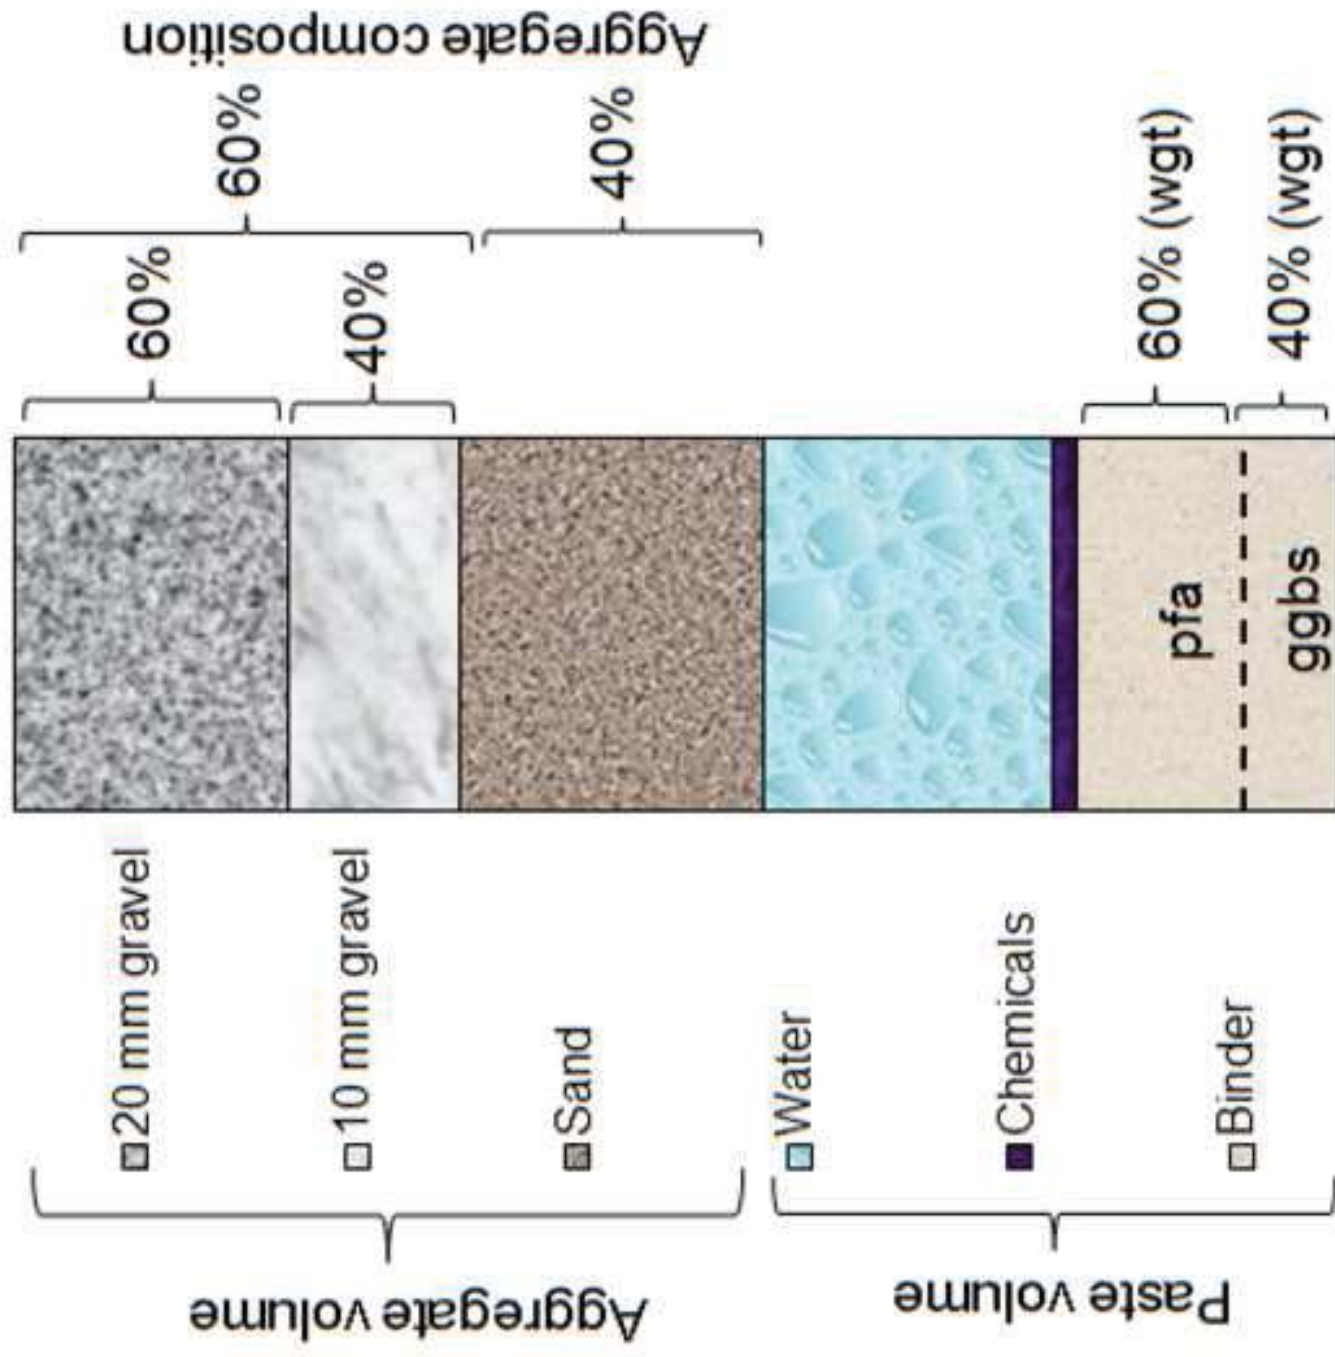


Figure 3  
 Click here to download Figure: Fig3.tif

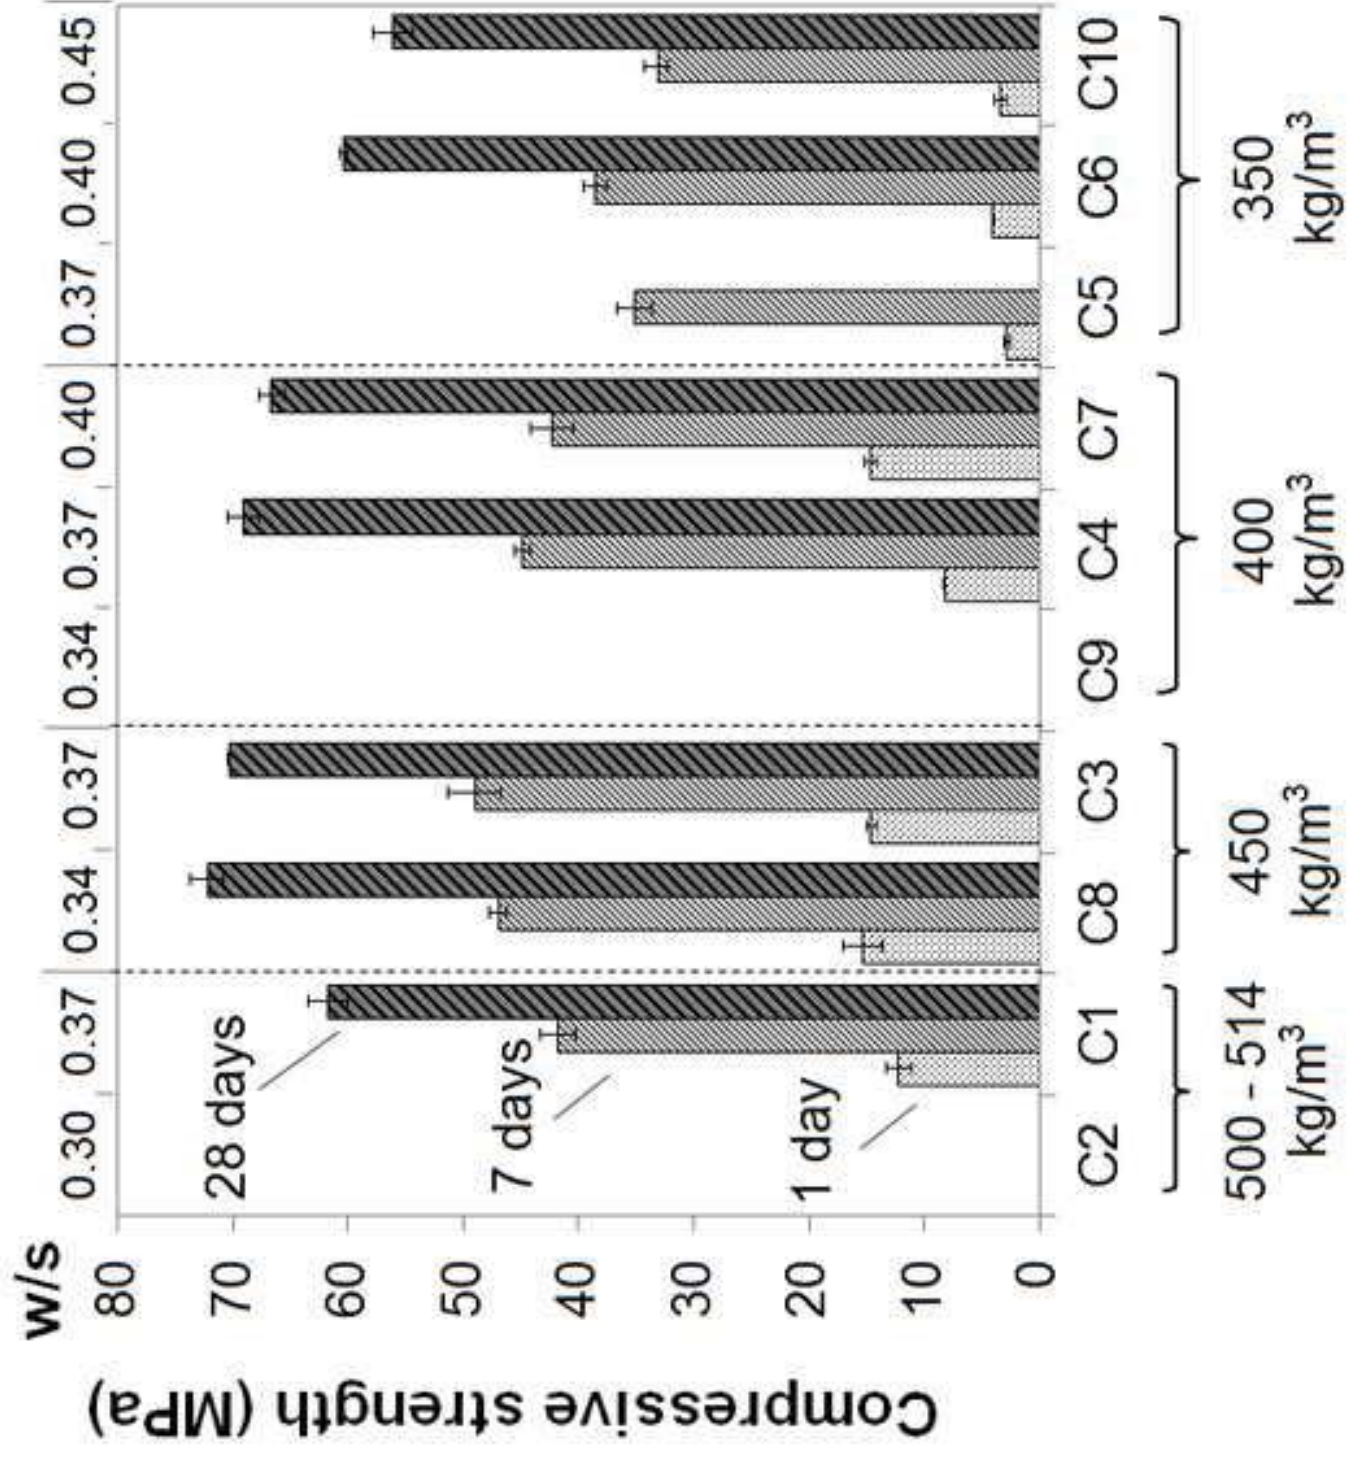
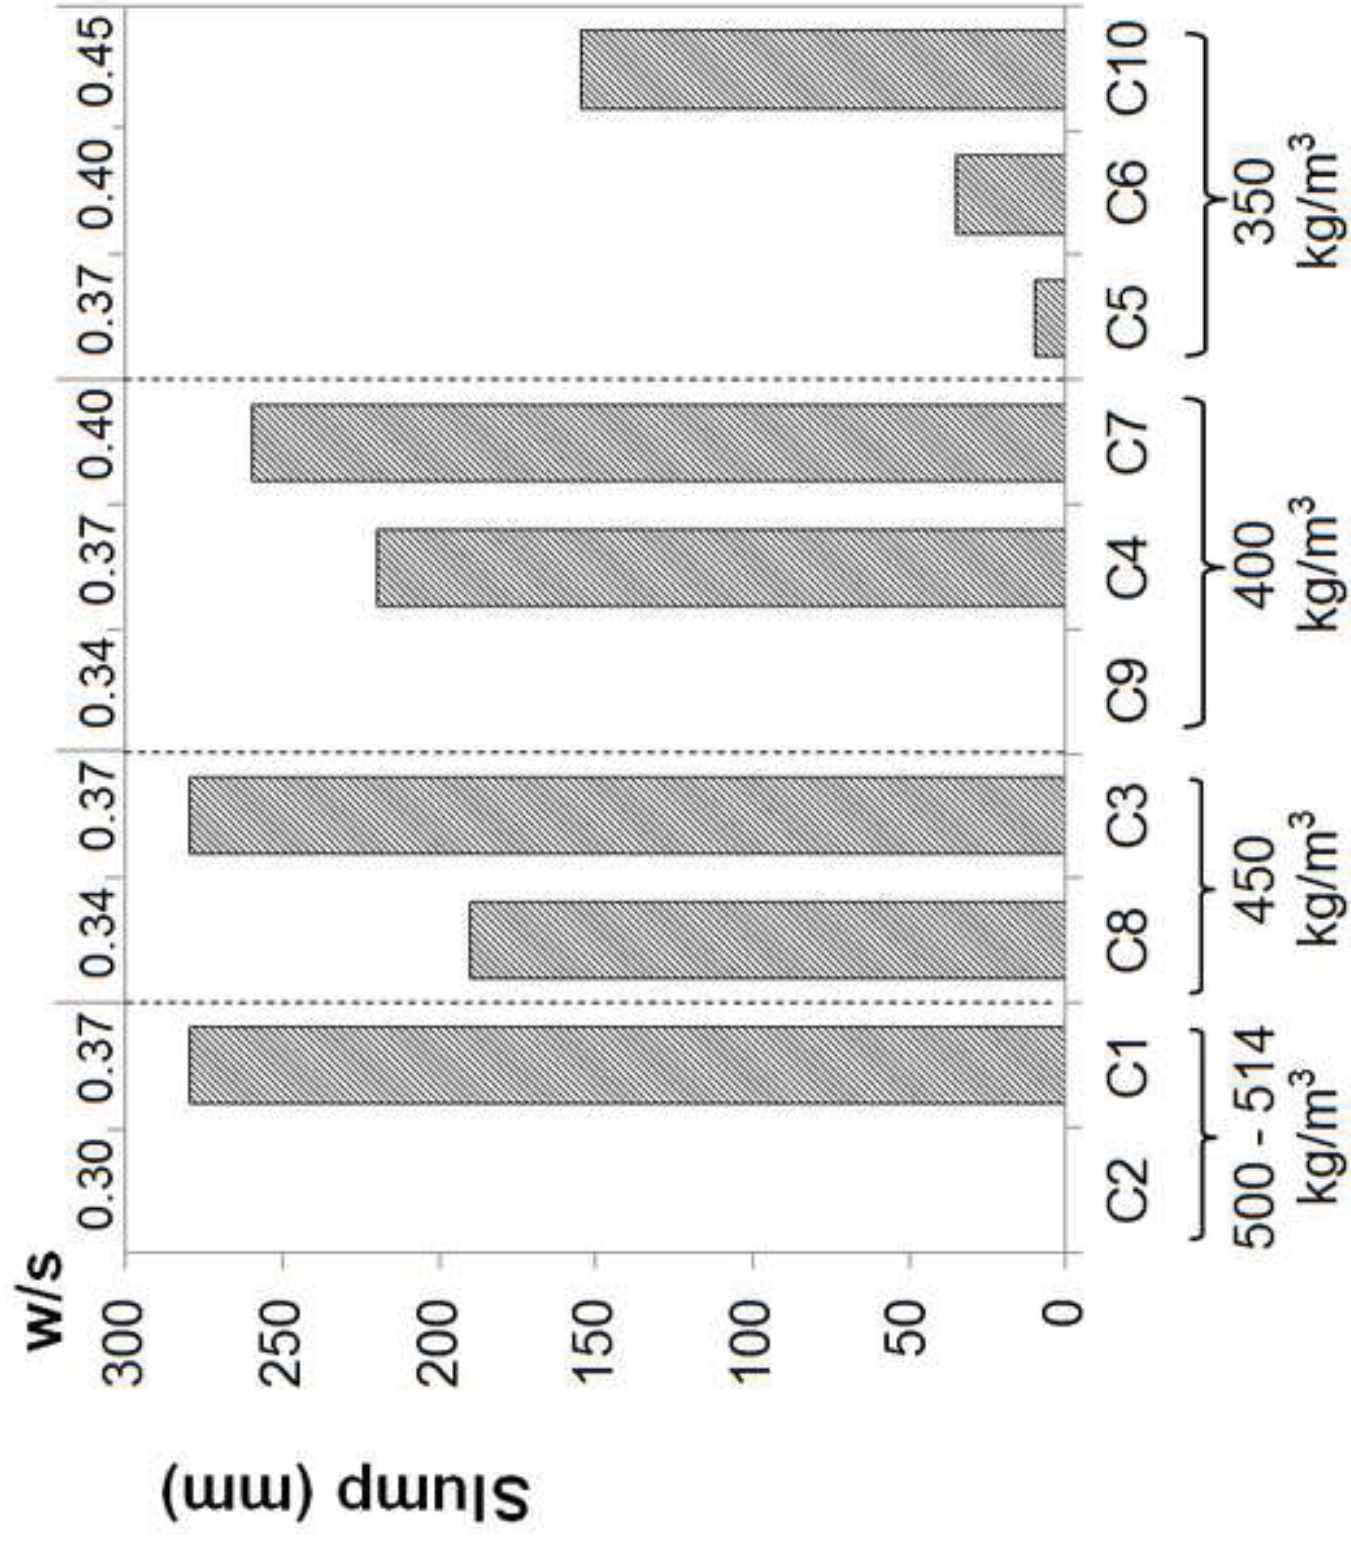
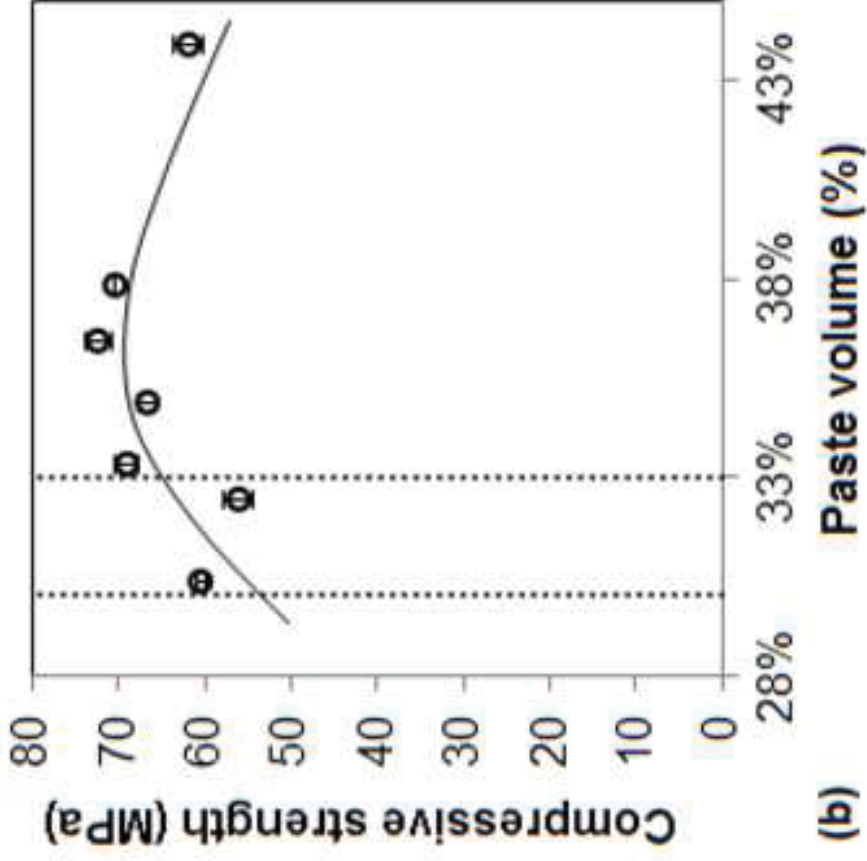
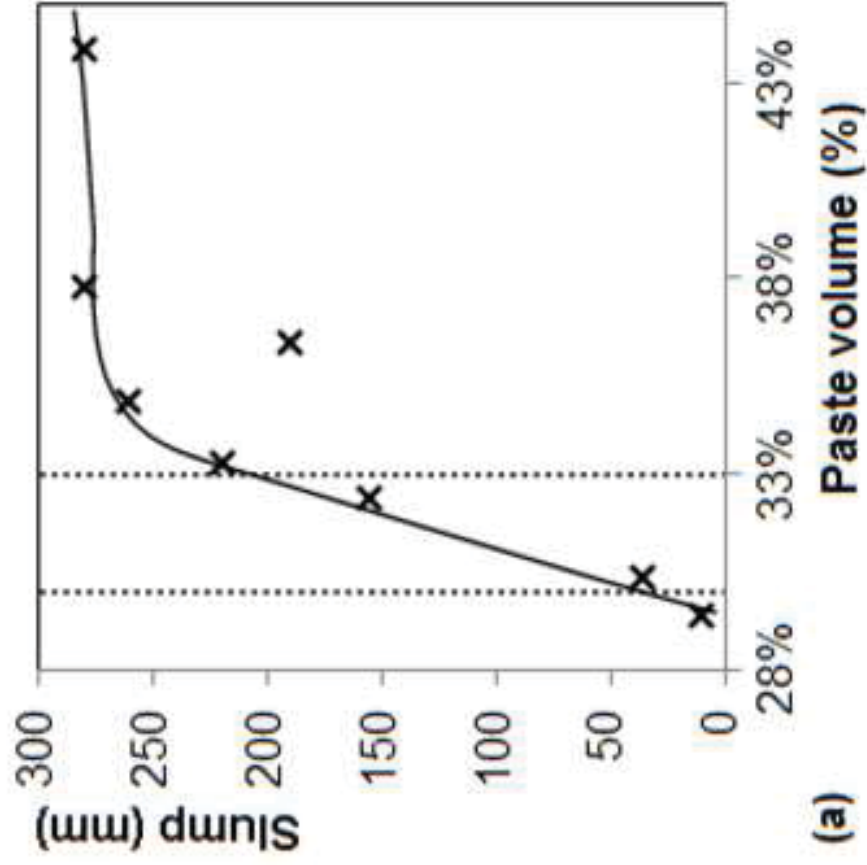


Figure 4  
Click here to download Figure: Fig4.tif





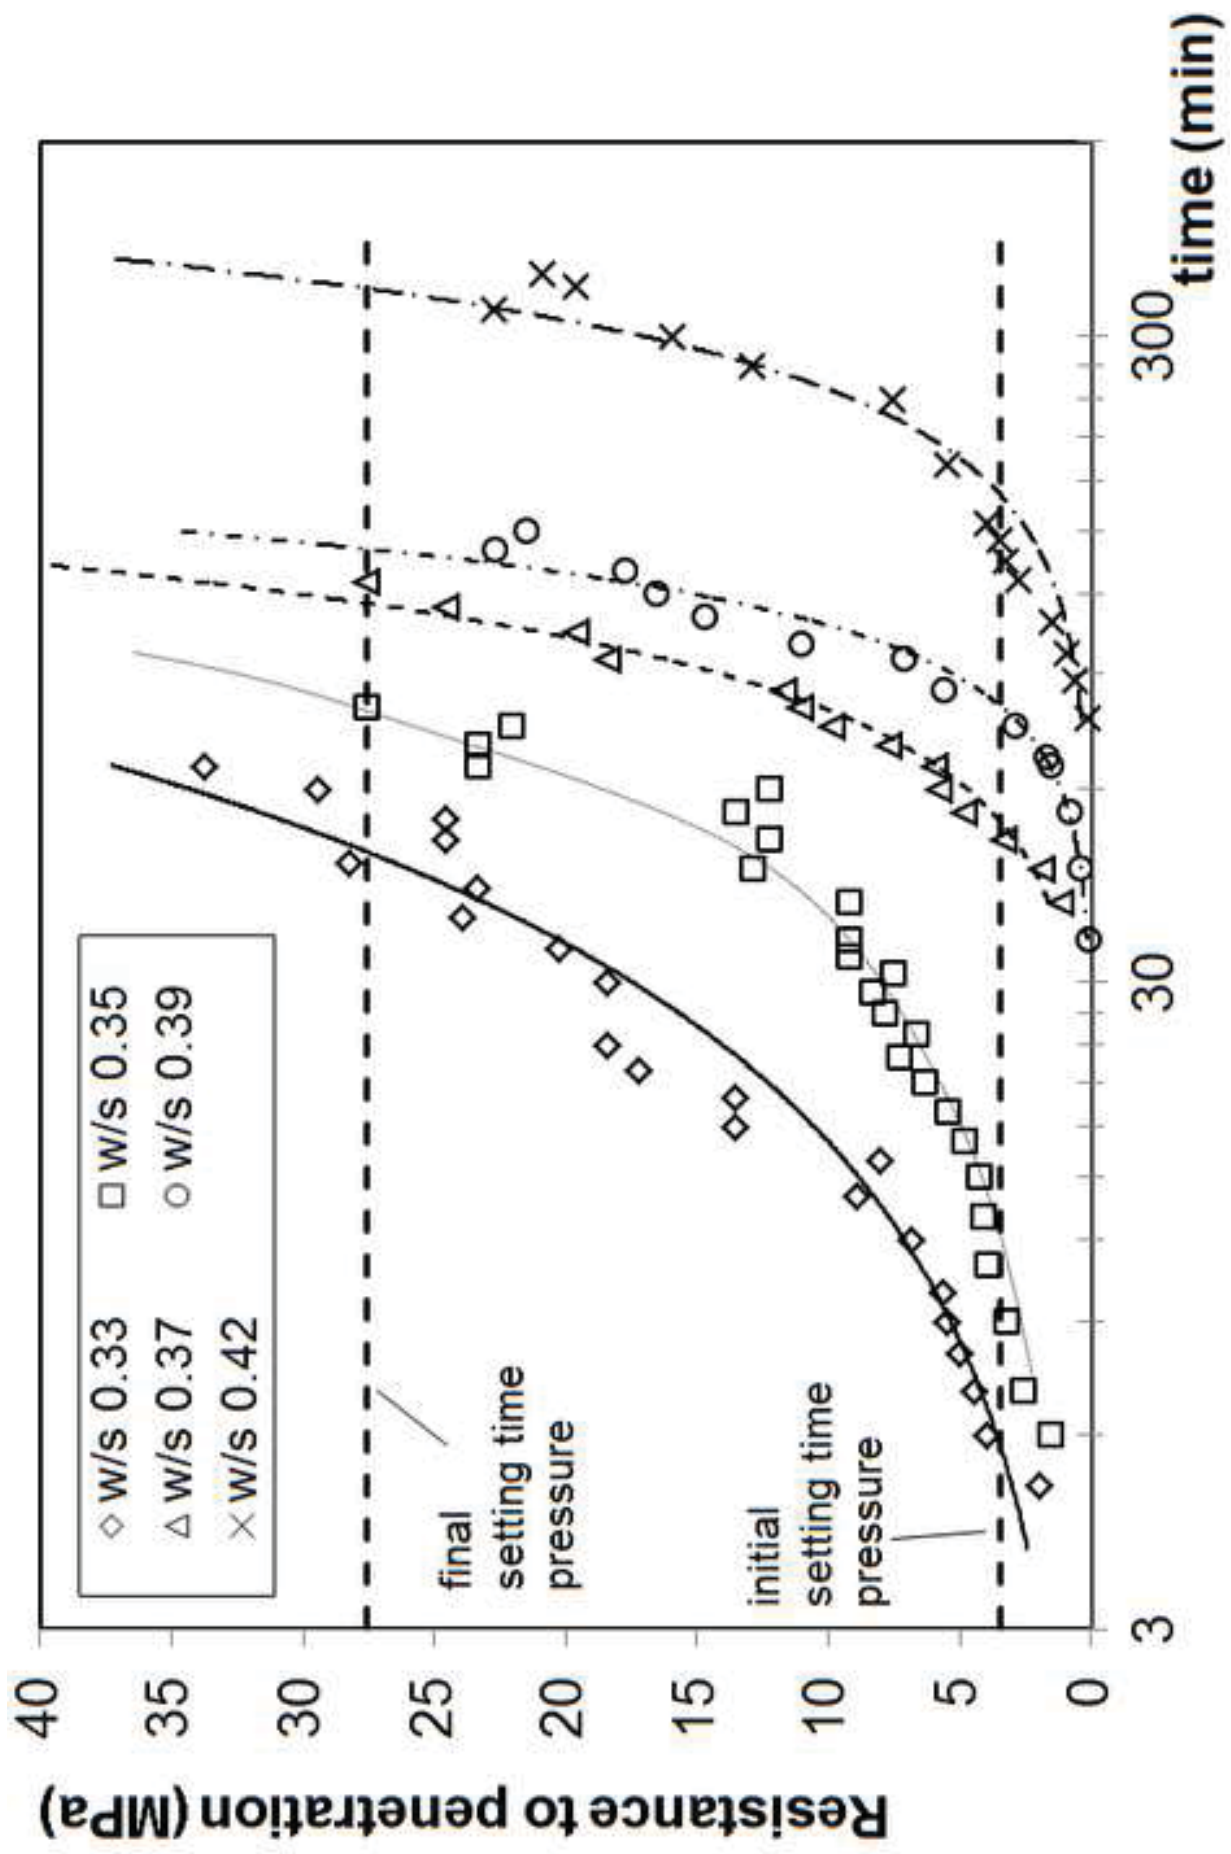


Figure 6  
 Click here to download Figure: Fig6.tif

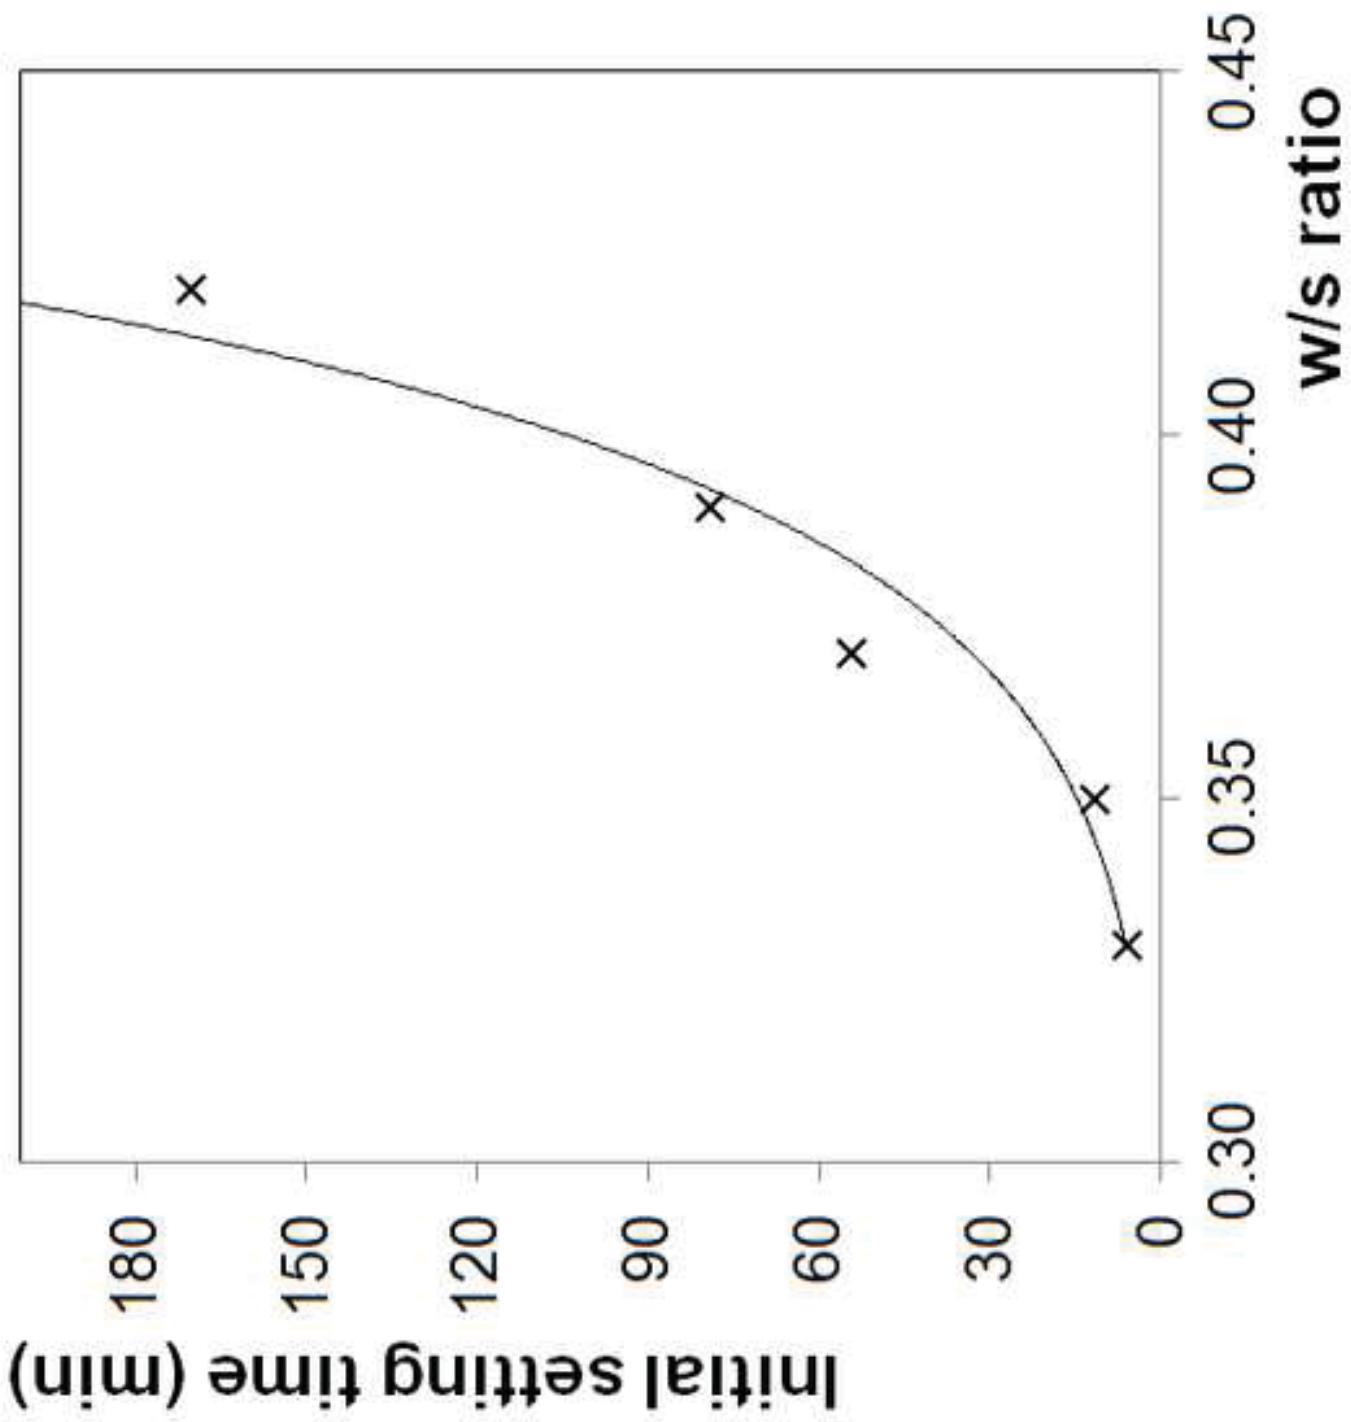


Figure 7  
[Click here to download Figure: Fig7.tif](#)

Figure 8 revised  
Click here to download Figure: Fig8-rev01.tif


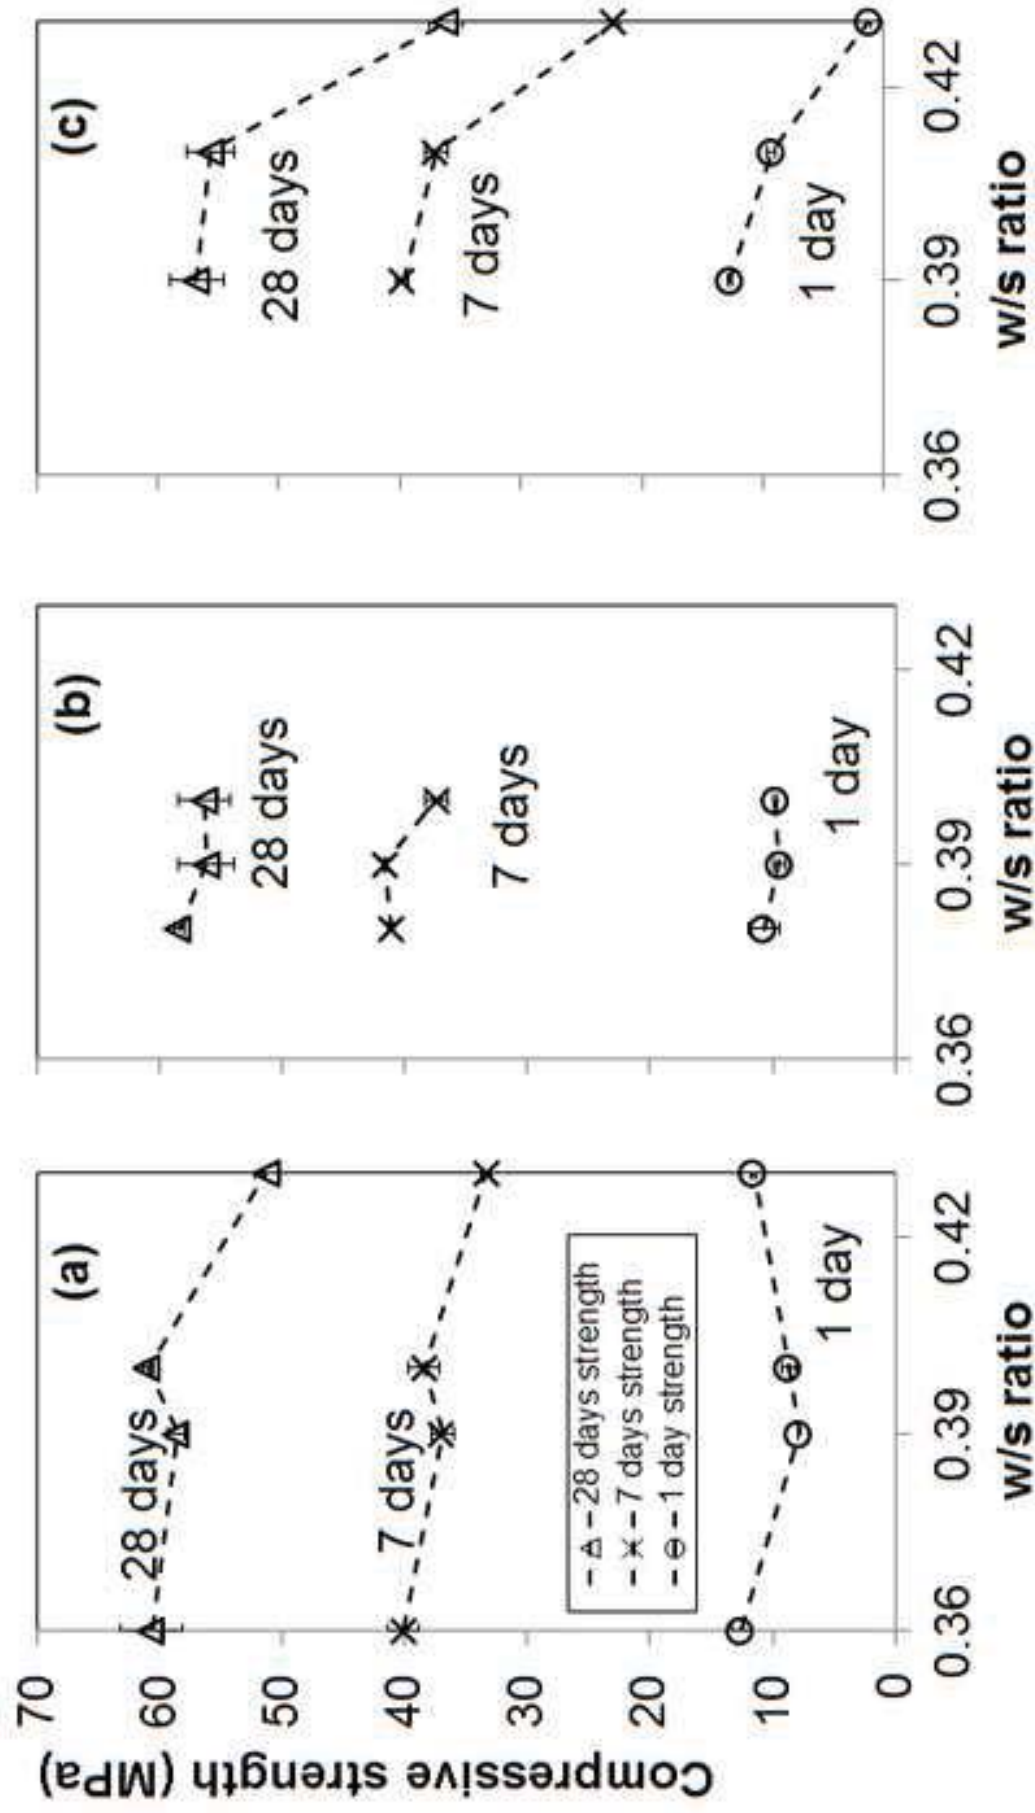




Figure 9  
Click here to download Figure: Fig9.tif

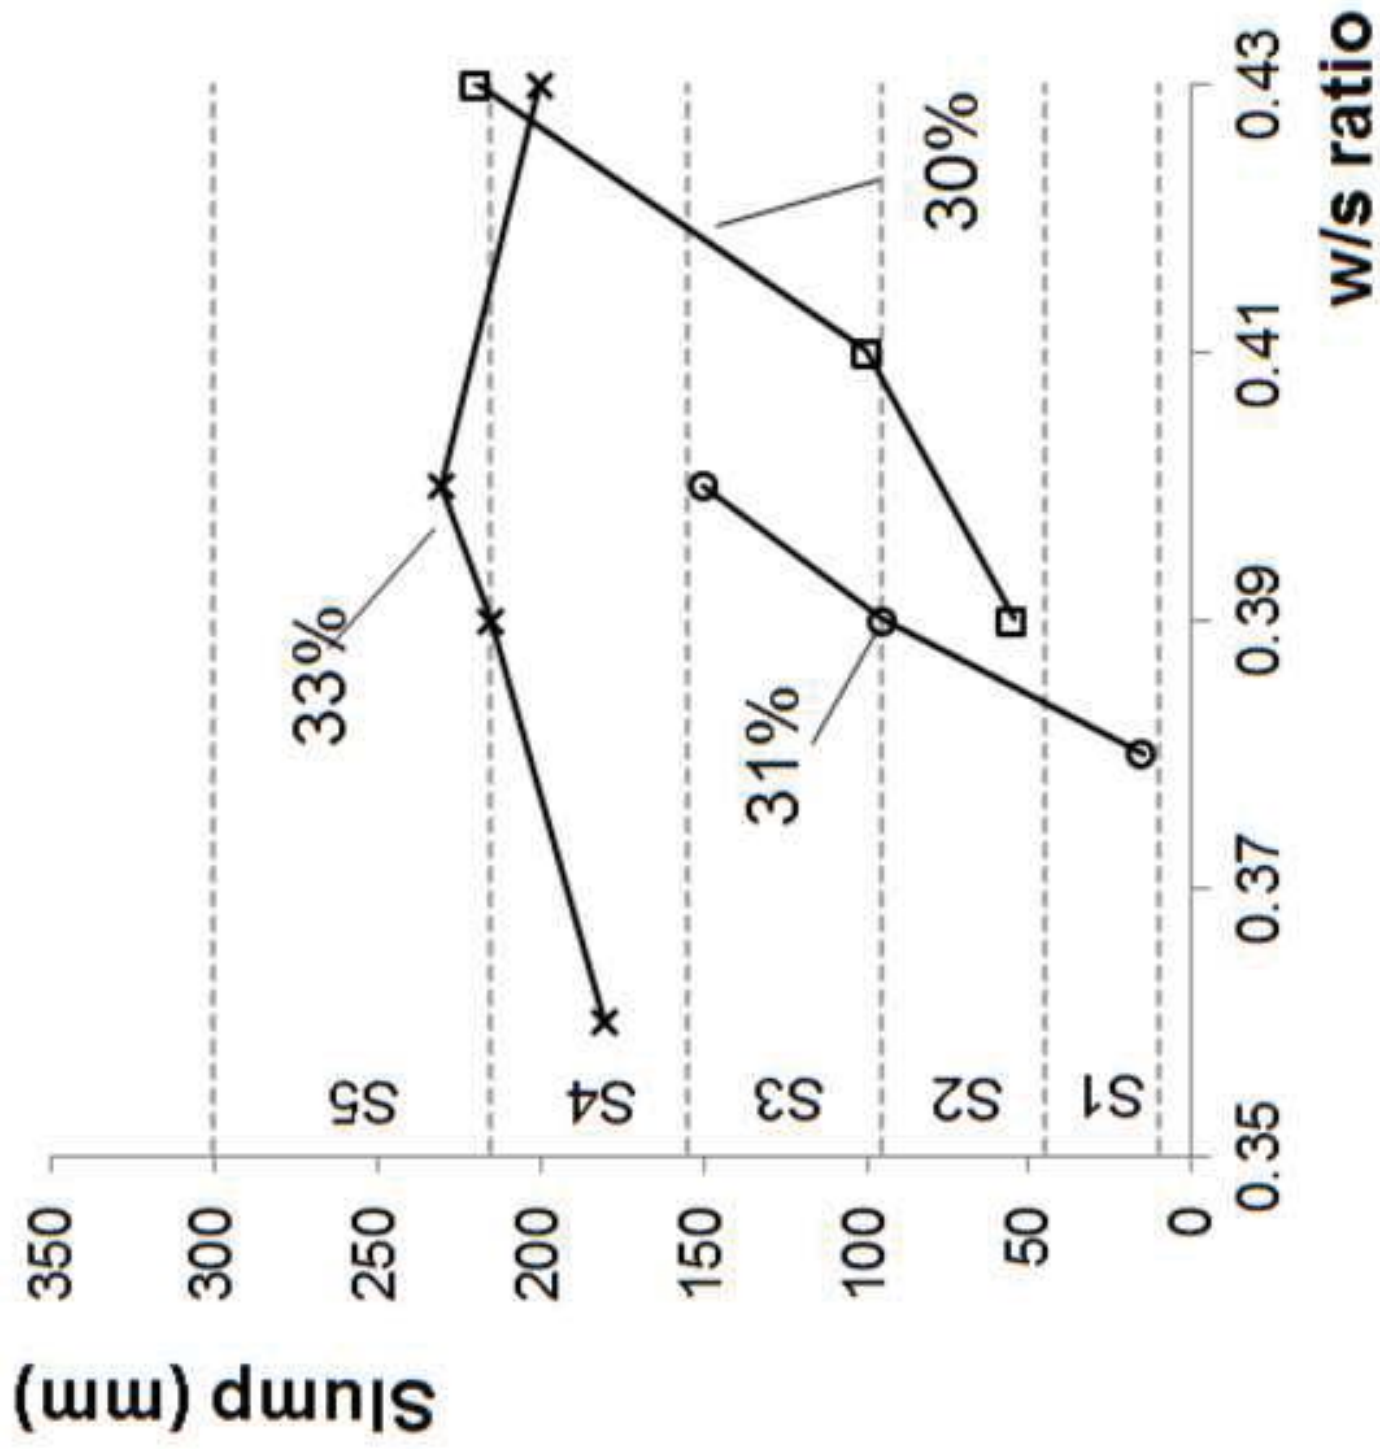

## Figure captions

**Fig. 1** Aggregate particle size distribution

**Fig. 2** Composition of alkali activated concretes

**Fig. 3** Compressive strength development for concretes from phase 1

**Fig. 4** Slump measurements for concretes from phase 1

**Fig. 5** (a) Slump measurements vs. paste volume. (b) Compressive strength at 28 days vs. paste volume. These contain the same data as shown in figures 3 and 4, which are presented differently highlighting the effects of paste volume (%)

**Fig. 6** Mortar penetration tests

**Fig. 7** Relationship between initial setting time and w/s ratio

**Fig. 8** Compressive strength vs. w/s ratio. (a) 33% paste volume; (b) 31% paste volume; (c) 30% paste volume.

Y axis for (b) and (c) is the same as (a)

**Fig. 9** Slump values measured for phase 2 concretes